

Part II

Applications

Multifunctional uses of geosynthetics in civil engineering

C. J. F. P. JONES
Newcastle University, UK

5.1 Introduction

Most geosynthetic materials play a passive role, e.g., geosynthetic barriers stop the passage of liquids; geosynthetic reinforcement provides tensile resistance, but only after an initial strain has occurred; and geo-drains provide a passage for water but do not cause the water to flow. New applications for geosynthetics have been developed by the introduction of new multifunctional geosynthetic materials. These can be identified in three forms, as *composite geosynthetics* which provide two or more conventional functions in one material, *smart geosynthetics* which provide critical management information and *active geosynthetics* that create a change in their environment rather than simply acting in a passive role.

Composite geosynthetics associated with filtration and drainage have been available for many years; recent developments relate to combining reinforcing functions with drainage.

Smart geosynthetics provide information on the development on ground movements, which can influence the performance of geotechnical structures such as road and railway embankments. The identification of these movements is important in maintaining serviceability and safety, particularly where the embankment supports high-speed traffic.

Active geosynthetics represent a new generation of geosynthetic materials, which have a wide range of new applications. The key innovation with these materials is that they are electrically conductive and have the ability to initiate electrokinetic processes as well as to retain the established geosynthetic functions. The electrokinetic phenomena used are electro-osmosis and electrophoresis (electro-osmosis causes water movement through low-permeability materials and electrophoresis relates to the movement of particles in materials with very high water contents).

Designing with active geosynthetics involves an understanding of electrokinetic phenomena and consideration of soil properties not usually considered in design.

This chapter identifies these and illustrates their relevance as well as providing information on case histories of the use of electrically conductive geosynthetics.

5.2 Composite geosynthetics

5.2.1 Combined filtration and drainage

Vertical sand drains were proposed as a means of deep soil improvement in 1925 by the American engineer Moran. The first practical sand drain installation was constructed in California. Later the Swedish engineer Kjellman introduced the first prototype prefabricated vertical drain made from cardboard, which were called wick drains. The main features of the prefabricated vertical drain are the combination of an outside filter surrounding an inner drainage core, which can be installed rapidly in the field to reduce the drainage path of poorly draining soils. In 1971, the Kjellman wick drain was improved by the introduction of a grooved plastic polyethylene core as a replacement for the cardboard centre. The use of prefabricated vertical drains has increased significantly and is now established construction practice. Many types have been developed, rapid and simple installation procedures have been introduced and installation depths of about 60 m at a rate of up to 1 m/s are possible.


5.2.2 Combined reinforcement and drainage

The design of reinforced slopes is concerned with the provision of an adequate factor of safety on strength and the control of settlements to acceptable limits. Conventional design and construction methods have used granular materials because of their high shear strength and good drainage properties. Research and long-term case histories have indicated that cohesive soils can be used in the construction of reinforced slopes if an adequate drainage system is provided.

When low-permeability fills are loaded, excess pore water pressures can be generated. This can result in a reduction in the available shear strength of the cohesive fill and also a reduction in the soil–reinforcement bond, requiring more reinforcement to provide an adequate bond length. The dissipation of excess pore water pressures results in consolidation and settlement of the reinforced structure, which can result in unacceptable face deflections.

The magnitude of excess pore water pressure present in a slope is a function both of the applied load and of the ability of the drainage system to dissipate the excess pore water pressure. At the base of a slope, with no drainage, large excess pore water pressures can develop. If drainage is provided and complete dissipation of excess pore water pressure occurs before construction of the next layer, the excess pore water pressure in the completed structure would be only a fraction of that otherwise present.

The ideal reinforcing material for cohesive soils requires the drainage charact-

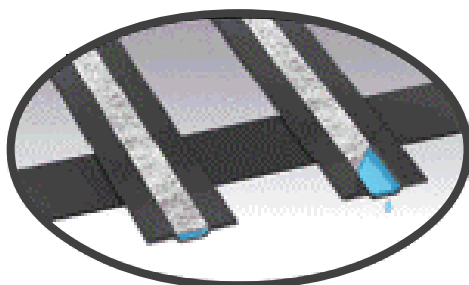


5.1 Integral drainage and reinforcement.

eristics of a non-woven geotextile and the strength of stiffer or stronger reinforcing geosynthetics. Alternatively, it is possible to combine existing materials (e.g. using a non-woven drainage geotextile together with geogrid reinforcement).

Heshmati (1993) studied the effects of combining a drainage material with grid reinforcement in clay soil. He concluded that the drainage and the reinforcement function were equally important in producing a stable and efficient structure. An important observation was that the method used to combine the drainage and reinforcing functions is critical. Simply placing a geotextile drain in conjunction with geogrid reinforcement can result in a reduction in strength as the presence of the drainage layer can lubricate the surface of the reinforcement. An essential requirement is that the combined functions of reinforcement and drainage have to be made integral.

An innovative geosynthetic material has been developed, which conforms with Heshmati's findings relating to a reinforcing material, also providing drainage. The multifunctional geosynthetic material consists of high-tenacity polyester encased in a polyethylene sheath. The sheath both protects the load-carrying elements and maintains the shape of the product which is profiled to provide a drainage channel on one side. The profiled strap has a thermally bonded non-woven geotextile strip bonded on the shoulders of the drainage channel action as a filter. The geotextile allows excess pore water pressure to dissipate while retaining the cohesive soil (Fig. 5.1). Confirmation of the performance of the combined geogrid reinforcement and drainage material has been provided by Kempton *et al.* (2000) who identified the following.

- 1 The effectiveness in dissipating excess pore water pressures under various confining stresses.
- 2 The pull-out resistance of the multifunctional material compared with a conventional geogrid of similar construction but with no drainage component.
- 3 The horizontal flow characteristics of the material under various hydraulic gradients and confining pressures.
- 4 Suitable parameters for use in design for constructing steep slopes using cohesive fills.

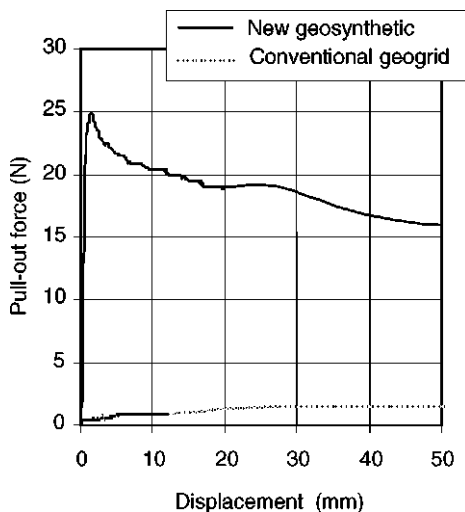

5.2 Pull-out results for a new geosynthetic and conventional geogrid with no drainage component after dissipation of excess pore water pressure for 12 h (after Kempton *et al.*, 2000).

The test results show that the pore water pressure reduces to 20% of the applied pressure in a 36–42 h period at confining pressures of both 50 and 100 kPa. No noticeable difference was observed in pore water pressure values measured above and below the test specimen even though the drainage channel was only on one side of the combined reinforcement and drainage material.

Pull-out testing on the combined material and on conventional geogrid with no drainage component was conducted after partial and full dissipation of excess pore water pressure (Fig. 5.2). The improvement in pull-out resistance is explained by the rapid dissipation of the excess pore water pressure in the immediate vicinity of the composite material, thus allowing early development of bond between the reinforcement and the soil. Full dissipation of excess pore water pressure is assumed when the pore water pressure reaches 10% of the applied overburden pressure in the immediate vicinity of the composite material.

5.3 Smart geosynthetics

The collapse of subsurface voids is a major problem in some counties in Europe, North America and parts of Africa and Asia. These voids are the result of geological conditions associated with the solution of soluble rocks (karst) or the result of underground mining. A feature of the development of surface voids caused by the collapse of old mine workings or evaporite solution of underlying strata is that the time of occurrence and location of any void are unknown. Prediction of void formation can only be made based upon historical evidence or probability theory. From an engineering perspective, the development of

randomly occurring voids is a major potential hazard which poses particular structural problems to transport systems.

The logical approach to the development of surface voids is to avoid the problem by relocating the particular structure to an area not affected. This may be possible with some building structures but it is usually impossible to use this strategy with basic infrastructure such as transportation systems. In these cases, design precautions are required. The basic design approach is to consider two limit states, covering ultimate and serviceability conditions. The *ultimate limit state* considers collapse conditions whilst the *serviceability limit state* governs deformation modes of failure, which do not lead to collapse but which render the structure or any system supported by the structure unserviceable.

For small voids it is possible, using engineering techniques, to ensure serviceability although the serviceability limits are sensitive to the engineering problem. High-speed rail systems are the most sensitive to differential settlements and voids of 2–4 m in diameter may be the limiting size for design.

In the case of voids in excess of 10–20 m it may not be possible to design against the ultimate limit case even for highways. With very large voids, collapse of the structure is inevitable and any structural precautions are restricted to providing warning of the collapse in order that loss of life may be avoided and if necessary to permit the mobilization of emergency measures. The design objective in this case is to provide a safe period of 24 h from loss of serviceability to total collapse. In the case of small voids (less than 3–10 m), the design objective is to provide long-term serviceability.

5.3.1 Design solutions

The use of basal reinforcement to prevent collapse of fill following the formation of a void or to support embankments over piles are accepted foundation engineering techniques, as described in BS 8006 (British Standards Institution, 1995). The development of basal reinforcement is an example of the technical and economic benefits which have been provided by the introduction of high-strength polymeric materials for use in reinforced soil (Jones, 1996). The technique was used successfully in the reconstruction of the East Coast Main Railway line between London and Edinburgh in 2002–2003 and on the new rail track at Stansted Airport, UK.

A weakness of the use of basal reinforcement is that it can mask the movement of the subsoil, and monitoring is required. To overcome the difficulties inherent in monitoring potential settlement, a smart geosynthetic material has been developed named 'Geodetect'. Geodetect is a system that combines the reinforcing function with a monitoring system based upon optical technology which can be used over extensive areas.

5.3.2 Conventional monitoring systems

Conventional monitoring systems can be classed in three groups.

- 1 Usual sensors.
- 2 Electrical warning system.
- 3 Ground-penetrating radar.

Usual sensors

Two kinds of usual sensor can be used: sensors fixed to the geosynthetic material (to measure the strain) and sensors positioned in the soil (to measure the settlement). Various kinds of sensor can be used including strain gauges, rod extensometers and inclinometers. These sensors can only be used for discrete measurement during a full-scale test. They cannot be used in a warning system because their lifetime in soil is short and they are difficult to fix to geosynthetic materials. Sensors in soil cannot be used in a general warning system. The use of settlement gauges require great care during installation and can only detect large localized sinkholes.

Electrical warning system

The electrical warning system consists of two non-woven geotextiles fitted together with electric wires at the inner side to form a detection layer. Deformation below the warning layer is indicated by an increase in electrical resistance. The method is effective for the detection of collapsing subsurface cavities and has been used in Germany (Ast and Haberland, 2002; Leitner *et al.*, 2002). However, the electrical aspect of the method may be a disadvantage for railway line application owing to electrical interference with signal systems.

Ground-penetrating radar

Ground-penetrating radar is a non-invasive electromagnetic geophysical technique for subsurface exploration, characterization and monitoring. It is widely used in locating lost utilities, environmental site characterization and monitoring, unexploded ordnance and land mine detection, groundwater, pavement and infrastructure characterization, mining, voids, and cave and tunnel detection. The application of the technique to sinkhole surveys has not proved effective in the case of railways. The method requires daily monitoring and can be expensive.

5.3.3 Geodetect system

The Geodetect system is formed as a composite material from a geosynthetic reinforcement material containing optical fibres. The optical fibres are inserted

into the geotextile during manufacture in a flexible sheath. The reinforcement geosynthetic is formed as a non-woven geotextile containing polyester reinforcement strands. The strands are needle punched to the non-woven geotextile in the production (machine) direction.

The optical fibres use the fibre Bragg grating (FBG) technique. FBGs are diffracting elements printed in the photosensitive core of a single-mode optical fibre. The grating reflects a spectral peak based on the grating spacing; thus changes in the length of the fibre due to tension or compression alter the grating spacing and the wavelength of light that is reflected back. Quantitative strain measurements can be made by measuring the centre wavelength of the reflected spectral peak. By using different wavelengths on which the mirrors are reflecting, signals of various FBG sensors can be identified. The wavelengths and wavelength shifts of these so-called mirrors can be measured with a fibre optic unit, allowing them to undergo demultiplexing in the wavelength domain. In this way, the space-distributed sensors are identified and distinguished. As each sensor has its own characteristic wavelength, the sensors can be connected in series on one optical line or a star configuration can be made. Using an optical switch, several hundreds of sensors can be measured with a relatively small low-cost interrogation unit. The Geodetect system has the following features.

- 1 Corrosion resistant.
- 2 Free from electromagnetic interference.
- 3 Radiation resistant.
- 4 Explosion proof (no risk of sparks).
- 5 Immune to lightning strikes.

The Geodetect system has been tested in the laboratory and on a full scale (Briancon *et al.*, 2004). Two simulated sinkholes were formed by deflating balloons located under a railway containing the Geodetect membrane. During deflating, the Bragg gratings located the cavities, indicating an instantaneous increase in strain as deflation commenced. Additional strain was recorded during the passage of vehicles above the voids.

The Geodetect system has been used by French Railways over an identified fault located perpendicular to the track. The length of the area treated was 50 m and the width of the track 5 m. The embankment under the track consisted of 250 mm ballast and a base of 500 mm and the Geodetect membrane was located below the base course (Nancy *et al.*, 2004). The design criteria required of the system were set as follows.

- 1 'Warning' level, surface settlement $s_w = 6$ mm.
- 2 'Slowdown' level, surface settlement $s_s = 9$ mm.
- 3 'Intervention' level, surface settlement $s_i = 21$ mm.

The geosynthetic reinforcement layer was designed as basal reinforcement using the following parameters (Villard *et al.*, 2000).

- 1 Embankment expansion coefficient $C_c = 1.1$.
- 2 Dead loading applied to the base (formation + ballast) $q_0 = 6$ kPa.
- 3 Live loading, 25.5 t per axle distributed over three rail sleepers.
- 4 Assumption of circular cavity 1.2 m in diameter.

With these parameters, the maximum stress q_{\max} applied to the reinforcement is 45 kPa. The stiffness J of the reinforcement is 3400 kN/m.

5.4 Active geosynthetics


The main applications of geosynthetics are primarily related to the civil engineering and environmental industries and are well established as providing filtration, separation, reinforcement and drainage and acting as barriers. In use, conventional geosynthetic materials have a *passive* role, e.g. as barriers stopping the passage of liquids, and as reinforcement providing tensile resistance but only after an initial strain has occurred and as drains providing a passage for water but not causing water to flow. New applications for geosynthetics can be identified if the geosynthetic can provide an *active* role, initiating chemical or physical change to the soil matrix in which it is installed as well as providing the established functions. This can be achieved by creating electrically conducting geosynthetics and combining electrokinetic phenomena with established geosynthetic functions to give electrokinetic geosynthesis (EKGs).

5.4.1 Electrokinetic phenomena in soils

Electrokinetic techniques have been developed for treatment of clay soils, since their introduction as a construction technique by Casagrande in 1939. Electrokinetics, for these applications, may be defined as the application, or induction, of an electrical potential difference across a soil mass containing fluid, or a high-fluid content slurry or suspension, causing or caused by the motion of electricity, charged soil and/or fluid particles.

Electrokinetic phenomena are the result of the coupling between hydraulic and electrical potential gradients in fine-grained soils (Yeung and Mitchell, 1993; Acar and Alshawabkeh, 1994). These phenomena occur due to the presence of a diffuse double layer around grained soil particles and involve the movement of electricity, charged particles and fluids (Mitchell, 1993). Electrokinetic phenomena may be defined in terms of five categories. Of these, the three most relevant are defined below and illustrated in Fig. 5.3.

- 1 *Electromigration or ion migration*. The applied electrical potential difference induces ion migration within the fluid phase of a charged-particle matrix.
- 2 *Electrophoresis*. The applied electrical potential difference induces movement of suspended colloidal particles within a fluid medium.
- 3 *Electro-osmosis*. The applied electrical potential difference induces fluid flow in a charged-particle matrix.

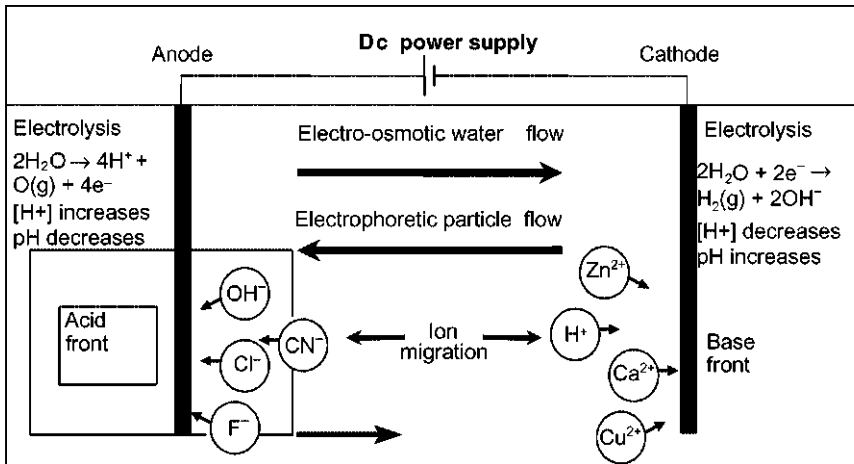

5.3 Electrokinetic effects (after Glendinning *et al.*, 2005).

Typically electro-osmotic dewatering of clay soils is of the order of one to four orders of magnitude faster than hydraulic dewatering, with a typical value of electro-osmotic permeability k_e for a clay soil being 10^{-5} $\text{cm}^2/\text{V s}$, as opposed to hydraulic permeability which ranges from 10^{-9} to 10^{-5} m/s for silts and clays. Actual values of k_e and k_h for a range of soils are shown in Table 5.1. The greatest advantage to be gained from electrokinetic dewatering over hydraulic dewatering is when the ratio of k_e to k_h is high.

5.4.2 Electro-osmosis


Several theories have been developed to explain electro-osmotic transport of water in clay soils. Of these, the Helmholtz–Smoluchowski theory is one of the earliest and one of the most widely used (Mitchell, 1993). It is based on an electrical condenser analogy that assumes that the soil capillaries have charges of one sign on or near the surface of the wall and countercharges concentrated in a layer in the liquid a small distance from the wall (Fig. 5.4). The mobile shell of counterions is assumed to drag water through the capillary by plug flow, resulting in a high-velocity gradient between the two plates of the condenser. The balance between the electrical force causing water movement and friction between the liquid and the wall controls the rate of water flow.

If v is the flow velocity and δ is the distance between the wall and the centre of the plane of mobile charges, then the velocity gradient between the wall and the centre of the positive charges is v/δ ; thus, the drag force per unit area is $\eta dv/dx = \eta v/\delta$ where η is the viscosity. The force per unit area from the electric field is $\sigma \Delta E/\Delta L$, where σ is the surface charge density and $\Delta E/\Delta L$ is the electrical potential gradient. At equilibrium,

Table 5.1 Coefficients of electro-osmotic permeability and other parameters (after Mitchell, 1993)

Material	Water content (%)	K_e ($10^{-5} \text{ cm}^2/\text{s V}$)	Conductivity σ (S/m)	Approximate k_h (cm/s)	K_i water per unit charge ^a ($\text{m}^3/\text{s A}$)
London clay	52.3	5.8	N/A	10^{-8}	N/A
Boston blue clay	50.8	5.1	N/A	10^{-8}	N/A
Kaolin	67.7	5.7	N/A	10^{-7}	N/A
Clayey silt	31.7	5.0	N/A	10^{-6}	N/A
Rock flour	27.2	4.5	N/A	10^{-7}	N/A
Na-montmorillonite	170	2.0	N/A	10^{-9}	N/A
Na-montmorillonite	2000	12.0	N/A	10^{-8}	N/A
Mica powder	49.7	6.9	N/A	10^{-5}	N/A
Fine sand	26.0	4.1	N/A	10^{-4}	N/A
Quartz powder	23.5	4.3	N/A	10^{-4}	N/A
Ås quick clay	31.0	2.0	N/A	2.0×10^{-8}	N/A
Bootlegger Cove clay	30.0	2.4–5.0	0.02	2.0×10^{-8}	1×10^{-7}
Silty clay, West Branch Dam	32.0	3.0–6.0	0.25	$(1.2–6.5) \times 10^{-8}$	$9.6 \times 10^{-9}–2 \times 10^{-8}$
Clayey silt, Little Pic River, Ontario	26.0	1.5		2×10^{-5}	
Decomposed granite, Silty clay	N/A	30	0.17	$10^{-4}–10^{-5}$	1.8×10^{-7}
Silty clay	23	5.0	0.08–0.12	$(0.5–8) \times 10^{-5}$	$(6.3–4.2) \times 10^{-9}$
Silty clay	10	9.0	0.02	1×10^{-5}	4.5×10^{-8}
Marine silty clay	37	6–9	0.024–0.033	10^{-7}	$(1.8–3.8) \times 10^{-7}$

^aN/A, not applicable.

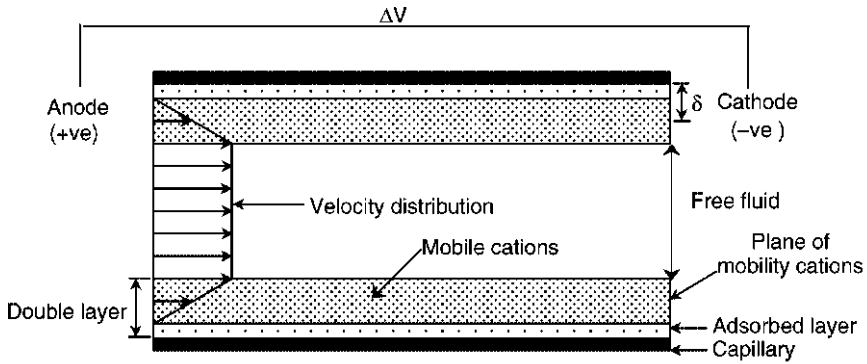

5.4 Helmholtz –Smoluchowski model (after Mitchell, 1993).

$$\eta \frac{v}{\delta} = \sigma \frac{\Delta E}{\Delta L} \quad [5.1]$$

or

$$\sigma \delta = \eta v \frac{\Delta L}{\Delta E} \quad [5.2]$$

From electrostatics, the potential gradient ζ across a condenser is given by:

$$\zeta = \frac{\sigma \delta}{D} \quad [5.3]$$

where

D = relative permittivity or dielectric constant of the pore fluid

Substitution of σ and δ into Equation 5.3 gives

$$v = \left(\frac{\zeta D}{\eta} \right) \frac{\Delta E}{\Delta L} \quad [5.4]$$

The potential ζ is the zeta potential, which is not equal to the surface potential of the double layer. For a single capillary of area a , the flow rate is

$$q_a = va = \frac{\zeta D}{\eta} \frac{\Delta E}{\Delta L} a \quad [5.5]$$

and for a group of N capillaries with a total cross-sectional area A normal to the flow direction,

$$q_A = Nq_a = \frac{\zeta D}{\eta} \frac{\Delta E}{\Delta L} Na \quad [5.6]$$

If the porosity is n , then the cross-sectional area of the voids is nA , which must equal Na . Thus,

$$q_A = \frac{\zeta D}{\eta} n \frac{\Delta E}{\Delta L} A \quad [5.7]$$

By analogy with the Darcy law, this may be rewritten as

$$q_A = k_e i_e A \quad [5.8]$$

where

$$i_e = \frac{\Delta V}{\Delta L} = \text{electrical potential gradient (V/m)} \quad [5.9]$$

$$k_e = \frac{\zeta D}{\eta} n = \text{coefficient of electro-osmotic permeability} \quad [5.10]$$

This is the equation that describes the flow of water under an electrical potential gradient.

5.4.3 Electro-osmotic permeability

Unlike hydraulic permeability, k_e is relatively independent of pore size (Table 5.1). Casagrande (1952) suggested that for most practical applications a value for $k_e = 5 \times 10^{-5} \text{ cm}^2/\text{s V}$ can be accepted. Therefore, it can be seen that electro-osmosis can be effective for water movement in fine-grained soils compared with water flow under hydraulic gradients.

5.4.4 Electro-osmotic efficiency

The efficiency of electro-osmosis relates to the quantity of water moved per unit charge passed (Grey and Mitchell, 1967). According to Mitchell (1993), this factor may vary by several orders of magnitude depending upon the soil type.

The efficiency of electro-osmosis depends upon the electrical conductivity of the soil mass. The electrical conductivity is in turn controlled by the water content, the cation exchange capacity and the free electrolyte concentration of the pore fluid, as indicated by Grey and Mitchell (1967) and validated by Lockheart (1983). The mineralogy of the soil itself also has a major implication upon the soil conductivity.

5.4.5 Energy requirements

The quantity of water moved per unit charge passed ($l/h \text{ A}$ or mol/F) is a measure of the viability of using electro-osmosis on a particular site. If this quantity is expressed as k_i then

$$q = k_i I \quad [5.11]$$

where k_i can vary over a wide range. The power consumption is defined by

$$P = \Delta E I = \frac{\Delta E q h}{k_i} \quad [5.12]$$

where ΔE is in volts and I in amperes.

The power consumption per unit volume of flow is

$$\frac{P}{qh} = \frac{\Delta E}{k_i} \times 10^{-3} \text{ KW h} \quad [5.13]$$

5.4.6 Relationship between k_e and k_i

The electro-osmotic flow rate is given by

$$q_h = k_i I = k_e \frac{\Delta E}{\Delta L} A \quad [5.14]$$

However, $\Delta E/I$ is the resistance and $\Delta L/(\text{resistance} \times A)$ is the specific conductivity σ , hence

$$k_i = \frac{C k_e}{\sigma} \quad [5.15]$$

where

k_e = electro-osmotic permeability (cm/s V cm)

k_i = electro-osmotic efficiency (gal/A h)

σ = specific conductivity (S/m)

C = constant = 1.0 using the stated units

Equation [5.15] is useful in that k_e varies within narrow limits as shown in Table 5.1. Hence, the electro-osmotic efficiency measured by k_i is dependent upon the electrical specific conductivity σ of the soil.

5.4.7 Applied voltage

Electro-osmosis may be carried out by applying a constant current or constant voltage. During treatment, the resistivity of the soil changes owing to electrochemical changes and desiccation. When a constant voltage is applied, the magnitude of the current decreases corresponding to the increase in the resistance of the soil mass being treated. Similarly, if a constant current is applied, the corresponding applied voltage will increase. Hamir (1997) carried out a series of basic tests to assess the difference between constant-voltage and constant-current tests. The findings of his investigation were that, in terms of the properties of the treated soil, no distinction between the two methods could be found.

Polarity reversal (the reversal of electrodes or current direction) has a marked effect on the effectiveness of dewatering in producing more uniform conditions. In addition, current intermittence has been shown to increase the efficiency of electro-osmotic dewatering. The principles of the improvement are quantitatively interpreted in terms of the depolarization of the double layer associated with current intermittence. It has been shown that electro-osmotic strengthening of marine sediments is enhanced by the use of current intermittence with optimum conditions being obtained with intermittence intervals as 2 min on and 1 min off (Mohamedelhassan and Shang, 2001). Another benefit is the reduction in anode corrosion (Micic *et al.*, 2001).

5.4.8 Pore water pressures

For certain applications such as soil consolidation, the generation of negative pore water pressure is the principle operator in the strengthening process, and negative pore pressure is proportional to the applied voltage.

Esrig (1968) has presented solutions for the development of pore water pressures under an applied electrical potential field. The solution is based upon the following assumptions.

- 1 The soil is homogeneous and in a fully saturated state.
- 2 The physical and physiochemical properties of the soil are uniform throughout and are constant with time.
- 3 Electrophoresis of fine-grained soil particles does not occur.
- 4 There is proportionality between the electrically induced velocity v of water flow through the soil and the voltage gradient V . The proportionality factor is the coefficient of electro-osmotic permeability i.e. the Helmholtz–Smoluchowski equation is applicable.

$$v = k_e \frac{\partial V}{\partial x}$$

- 5 All applied voltages are effective in moving water.
- 6 The electric field produced throughout the soil mass is constant with time.
- 7 No reactions occur at the electrodes (e.g. electrolysis).
- 8 Fluid flows due to an electric field and due to a hydraulic gradient may be superimposed to find the total fluid flow.

Some of these assumptions are inherently incorrect.

- 1 A natural material is very rarely, if ever, homogeneous.
- 2 The resistivity of the soil undergoing electro-osmosis has been shown to vary with both position and time because of both desiccation and electrochemical changes.
- 3 Separation of the electrodes from the soil may also occur owing to gas formation caused by electrolysis.

- 4 The physical and physiochemical properties of the soil vary with time, as does the electric field.
- 5 Electrolysis occurs during all electro-osmotic treatments.

The assumption that fluid flow caused by an electric field may be superimposed on the flow caused by a hydraulic gradient is important. Grey and Mitchell (1967) demonstrated the validity of the theory indirectly through the measurement of streaming potentials resulting from hydraulic flows. Wan and Mitchell (1976) showed that the superposition of pore water pressures generated by surcharge loading and electro-osmosis was valid. Accepting the validity of superposition of electrical and hydraulically driven flows through an incompressible soil mass and limiting consideration to one dimensional flow gives

$$\frac{\partial v}{\partial x} + \frac{\partial V_h}{\partial x} = 0 \quad [5.16]$$

where

v = velocity of flow due to the electrical potential gradient $\partial V/\partial x$ (i.e. the Helmholtz–Smoluchowski)

V_h = the velocity of flow due to the hydraulic gradient (i.e. Darcy's equation)

Differentiation of Equation [5.16] with respect to x and inserting the Helmholtz–Smoluchowski and the Darcy equations give

$$k_e \frac{\partial^2 V}{\partial x^2} + \frac{k}{\gamma_w} \frac{\partial^2 u}{\partial x^2} = 0 \quad [5.17]$$

Rearranging gives

$$\frac{\partial^2 u}{\partial x^2} + \frac{k_e \gamma_w}{k} \frac{\partial^2 V}{\partial x^2} = 0 \quad [5.18]$$

and substitution of the variable ξ , where

$$\xi = \frac{k_e \gamma_w}{k} V + u \quad [5.19]$$

gives

$$\frac{\partial^2 \xi}{\partial x^2} = 0 \quad [5.20]$$

which is the Laplace equation in a one-dimensional system. Integrating once gives

$$\frac{\partial \xi}{\partial x} = C_1 \quad [5.21]$$

and integrating again gives

$$\xi = xC_1 + C_2 \quad [5.22]$$

where

C_1, C_2 = constants of integration dependent upon the boundary conditions.

The possible drainage conditions that may exist at the electrodes, which govern these boundary conditions, are discussed in the following section.

5.4.9 Electrode drainage conditions and pore water pressures

The drainage conditions applied to either the anode or the cathode have one of the following two conditions.





- 1 *Open.* This condition exists when the electrode is open to the atmosphere, such that no excess pore pressure can exist at the electrode, i.e. $u = 0$. This condition will occur where an EKG electrode is utilized with an external filter in place, or where a more conventional metallic-type electrode is used together with an associated drainage path, e.g. sand drain or hollow perforated electrode. An open electrode may also be pumped, recharged or simply allowed to overflow.
- 2 *Closed.* This condition exists when the electrode is sealed such that no passage of gas or fluid can take place along the length of the electrode.

The configurations used for consolidation and/or dewatering in practice are as follows.

- 1 Open, anode not recharged; open, cathode with overflow.
- 2 Closed, anode; open, cathode with overflow.
- 3 Closed, anode; open, cathode pumped.

5.4.10 Electrolysis effects associated with electro-osmosis

During electro-osmotic treatment of a soil mass, the whole system acts as an electrochemical cell in which cations migrate to the cathode and anions migrate to the anode. Reduction reactions take place at the cathode, with the principal reaction being the reduction of water to hydrogen gas. At the anode, there is the possibility of two distinct oxidation reactions: the oxidation of the anode material itself into its oxide or the oxidation of water to yield oxygen. Hence, the anode will degrade, with the rate of degradation being dependent upon the material from which the anode is manufactured. It is the degradation of the anode that has caused the most problems with the application of electro-osmotic treatment on an industrial scale. Corrosion of the anode is accompanied by a build-up of corrosion products, which degrade the electrical efficiency of the process. The process is also influenced by the production of gas at the electrodes, which must be vented for the process to continue. A schematic diagram of the movement of current and the electrolytic reactions that may occur during electro-osmotic treatment are



The liberation of hydrogen ions at the anode causes a reduction in pH, and an increase in hydroxide ions at the cathode causes an increase in pH. If these ions are not removed or neutralized from the anode and cathode, electromigration and/or ion migration will occur with hydrogen ions moving towards the cathode (acid front) and hydroxide ions moving towards the anode (base front). The advance of acid and base fronts is governed by ion migration as well as by electro-osmotic flow, diffusion and the buffering capacity of the soil medium. Owing to a higher ratio of charge to ionic size, H^+ ions move more rapidly than OH^- ions during electromigration. Additionally, electro-osmotic flow occurs in the same direction as H^+ migration, but it opposes the direction of OH^- migration. As a consequence, the acid front from the anode moves more quickly than the base front from the cathode, so that acidic conditions prevail throughout most of the soil mass.

5.4.11 Evolution of active geosynthetics

The problems relating to the degradation of the electrodes and gas and water production can be overcome by forming them of materials not susceptible to corrosion and also providing inbuilt drainage facilities for the gases produced and the water collecting at the cathode. This can be achieved by using electrically conducting geosynthetic materials to form the electrodes. The resultant materials differ from conventional geosynthetics in that they are active in the sense that they cause change in soils rather than acting in a passive manner as is the case with conventional materials (Jones *et al.*, 2005).

Jones *et al.* (1996) introduced the concept of EKG materials, defining them as a range of geosynthetics, which, in addition to providing filtration, drainage and reinforcement can be enhanced by electrokinetic techniques for the transport of water and chemical species within fine-grained low-permeability soils, which are otherwise difficult or impossible to deal with. In addition, transivity, sorption, wicking and hydrophobic tendencies may also be incorporated in the geosynthetic to enhance other properties. The EKG can take the form of a single material which is electrically conductive, or a composite material, in which at least one element is electrically conductive. They can be of the same basic form as present-day filter, drainage, separator and reinforcement materials but offer sufficient electrical conduction to allow the application of electrokinetic techniques.

Jones *et al.* (1996) undertook a series of laboratory studies to evaluate the use of conductive geotextiles as electrodes in electro-osmotic consolidation and reinforced

soil. The types of geosynthetic used included needle-punched geotextiles with copper wire of 1 mm diameter inserted into the geotextile to make it electrically conductive, conductive fibre (carbon) needle-punched material and modified polyester reinforcing tape. The latter was made electrically conductive by the addition of metal stringers aligned parallel to the polyester reinforcing elements. The results of the tests were favourable and indicated that the EKG behaved as well as a conventional copper electrode.

In the reinforced soil tests, the EKG reinforcement was used as an anode, with the cathode formed from a needle-punched EKG fabric. The results of pull-out tests showed an increase in reinforcement bond of up to 211% and increases in shear strength of up to 200% compared with the values obtained when the geosynthetics were not electrically conductive, (Hamir, 1997). Nettleton *et al.* (1998) continued the work presented by Jones *et al.* (1996) and suggested that a band-drain-type electrode would be the most suitable configuration to fulfil all the electrode requirements associated with consolidation, bioremediation and moisture control in embankments.

Current EKG materials are formed using special conductive elements woven knitted or needle punched into conventional geosynthetic products to form drains, tubes, bags, grid or sheet elements (Hamir *et al.*, 2001; Electrokinetic, 2005).

5.4.12 Development of soil acceptability criteria for electrokinetic treatment

Acceptability criteria for the electrokinetic treatment of soils have been developed on the basis of standard and non-standard soil mechanics tests. The basis for advancing these criteria is to permit a relatively rapid assessment of the suitability of a soil for treatment by electro-osmosis based upon standard soil mechanics laboratory tests. This does not mean that electro-osmosis specific tests are not required in order to predict the performance of a particular site installation, but it permits an informed decision to be made at an early stage as to whether to proceed with the more specialized testing.

General classification tests

The liquid and plastic limits of a soil define the range within which a cohesive soil behaves in a plastic state. The value of the Atterberg limits of a cohesive soil depends upon several factors, including the quantity and type of clay mineral and type of absorbed cation. Typical values for the Atterberg limits for different clay mineral types are given in Table 5.2. It can be seen that the different clay mineralogies have a direct bearing upon the values of the Atterberg limits. It has also been shown that the electrical conductivity of a soil is influenced, to some extent, by the surface charge density A_0 and is dependent upon the clay mineralogy. Hence, the relationship between the Atterberg limits and the electrical


Table 5.2 Atterberg limits and associated parameters for different clay minerals (after Lambe and Whitman, 1969 and Mitchell, 1993)

Clay mineral type	Liquid limit (%)	Plastic limit (%)	Activity	Shrinkage limit (%)
Montmorillonite	100–900	50–100		8.5–1.5
Nontronite	37–72	19–27		
Illite	60–120	35–60	0.5–1.0	15–17
Kaolinite	30–110	24–40	0.5	25–29
Hydrated halloysite	50–70	47–60		
Dehydrated Halloysite	33–55	30–45		
Attapulgite	160–230	100–120	0.5–1.2	7.6
Chlorite	200–250	130–140		

conductivity of the soil can be linked to soil mineralogy. In addition to the mineralogy, the electrical conductivity of the soil *in situ* is partially governed by the electrical conductivity of the pore fluid and the water content.

The chemistry of the pore water, which is also reflected in the exchangeable cations present within the clay minerals, influences the range of results for the Atterberg limits presented in Table 5.2. The monovalent cations (e.g. Na^+ and K^+) give higher values of liquid and plastic limits whereas the presence of divalent and trivalent cations (e.g. Mg^{2+} , Fe^{2+} and Al^{3+}) give lower values. If the soil is tested repetitively, the exchangeable cations can be flushed from the clay, and a change in the Atterberg limits takes place. Thus, for samples that are to be tested with a view to utilizing the results for prediction of the viability of electro-osmosis, it is important that the tests are undertaken in accordance with BS 1377: Part 2 (British Standards Institution, 1990) and not repetitively wetted and dried.

The validity of the correlation proposed for the acceptability of soils based upon the Atterberg limits and conductivity is demonstrated in Fig. 5.5. The results

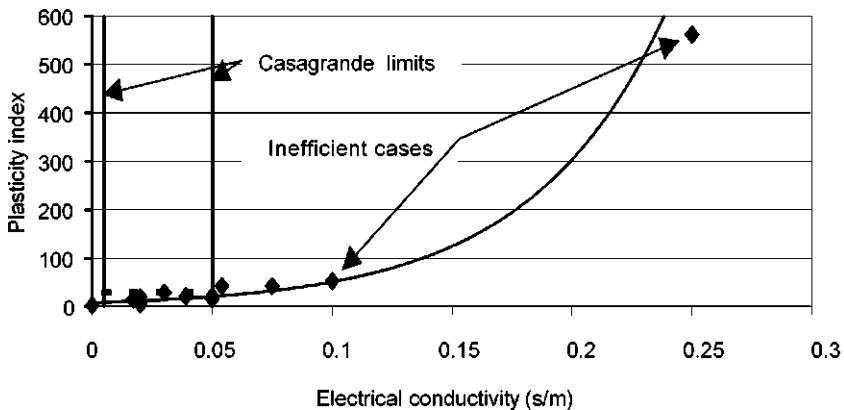

5.5 Conductivity against plasticity index for a range of natural soils (after Pugh, 2002).

presented in Fig. 5.5 relate to a review of published electro-osmotic case studies where both the plasticity indices and the electrical conductivities have been given (Bjerrum *et al.*, 1967; Casagrande, 1952; Casagrande *et al.*, 1961; Hamir, 1997; Pugh, 2002).

The delineation of acceptable electrical conductivities (σ) and, hence, plasticity indices is based upon the limits proposed by Casagrande (1952) that an acceptable and economic range for the electrical conductivity is 0.05 – 0.005 S/m. This range gives an associated acceptable range of plasticity index in the range from 5 to 30%. This criterion is adopted for the assessment of soils.

Chemical and electrochemical tests

The standard chemical and electrochemical tests may be carried out in accordance with BS 1377: Part 3 (British Standards Institution, 1990) with the soil samples being taken and prepared in accordance with BS 1377: Part 1 (British Standards Institution, 1990).

Organic content

The presence of organic matter in a soil can have a significant effect upon the cation exchange capacity, especially in high-pH conditions and can therefore have an effect upon the electro-osmotic efficiency of the soil to treatment. Therefore, if the soil may be described as an organic clay or silt, it is recommended that specific electro-osmotic testing be carried out to ascertain the soil's suitability.

Electrical resistivity

The electrical resistivity ρ of the soil may be determined in accordance with BS 1377: Part 3:1990 Part10 (British Standards Institution, 1990). The disc electrode method is the most appropriate. Electrical resistivity may be related to conductivity σ by

$$\sigma = \frac{1}{\rho} \quad [5.27]$$

The range of acceptable and economic values of electrical conductivities σ within the range 0.05–0.005 S/m are acceptable. Values in excess of this range do not indicate that the soil is not susceptible to treatment by electro-osmosis, but that the electro-osmosis installation will draw a high current and may not be economic.

Compressibility and permeability tests

The standard compressibility and permeability tests may be carried out in accordance with BS 1377: Part 5 (British Standards Institution, 1990). The falling-head permeability test, which is the most appropriate for fine-grained soils, is not

covered by current British or ASTM standards and the method given by Head (1982) is recommended.

One-dimensional consolidation parameters

Electro-osmotic consolidation is normally two dimensional, in that the electric field and the flow of water and development of pore water pressures are in the same direction, whereas the surface settlements induced are in an orthogonal direction. BS 1377: Part 5 (British Standards Institution, 1990) recommends that the soil specimen should be oriented such that the soil will be loaded in the same direction relative to the stratum as the applied stress *in situ*. Electro-osmotic consolidation via vertical drains or electrodes is equivalent to consolidation using surcharging and vertical sand drains, in the sense that the applied pressure and drainage occur in two dimensions, therefore, the coefficients of radial drainage are appropriate (Johnson, 1970; Das, 1997).

Shear strength–total stress


A review of the available literature for the range of c_u for soils that have been successfully treated by electrokinetic techniques indicates a range 0.7–81 kPa (Casagrande *et al.*, 1961; Bjerrum *et al.*, 1967; Wan and Mitchell, 1976; Lo *et al.*, 1991; Milligan, 1994; Abiera *et al.*, 1999). Comparison of the liquidity index criteria with the undrained shear strength criteria indicates that preferable soils (i.e. with a liquidity index greater than 0.6) will have a c_u of less than 20 kPa whereas soils that may still be acceptable (i.e. with a liquidity index greater than 0.2) will have a c_u of less than 55 kPa.

Shear strength–effective stress

Table 5.3 presents typical values for the range of ϕ' for silts and clays that are amenable to treatment by electro-osmosis. Electro-osmosis may be expected to increase the value of ϕ' for treated soils as Pugh (2002) and Casagrande (1952) have demonstrated for London clay and fine quartz sand, respectively, in that the

Table 5.3 Typical ϕ' values for compacted clays (after Carter and Bentley, 1991)

Soil type	Unified classification system designation	ϕ' (deg)
Silty clays	SM	34
Silts and clayey silts	ML	32
Clays of low plasticity	CL	28
Clayey silts, elastic silts	MH	25
Clays of high plasticity	CH	18

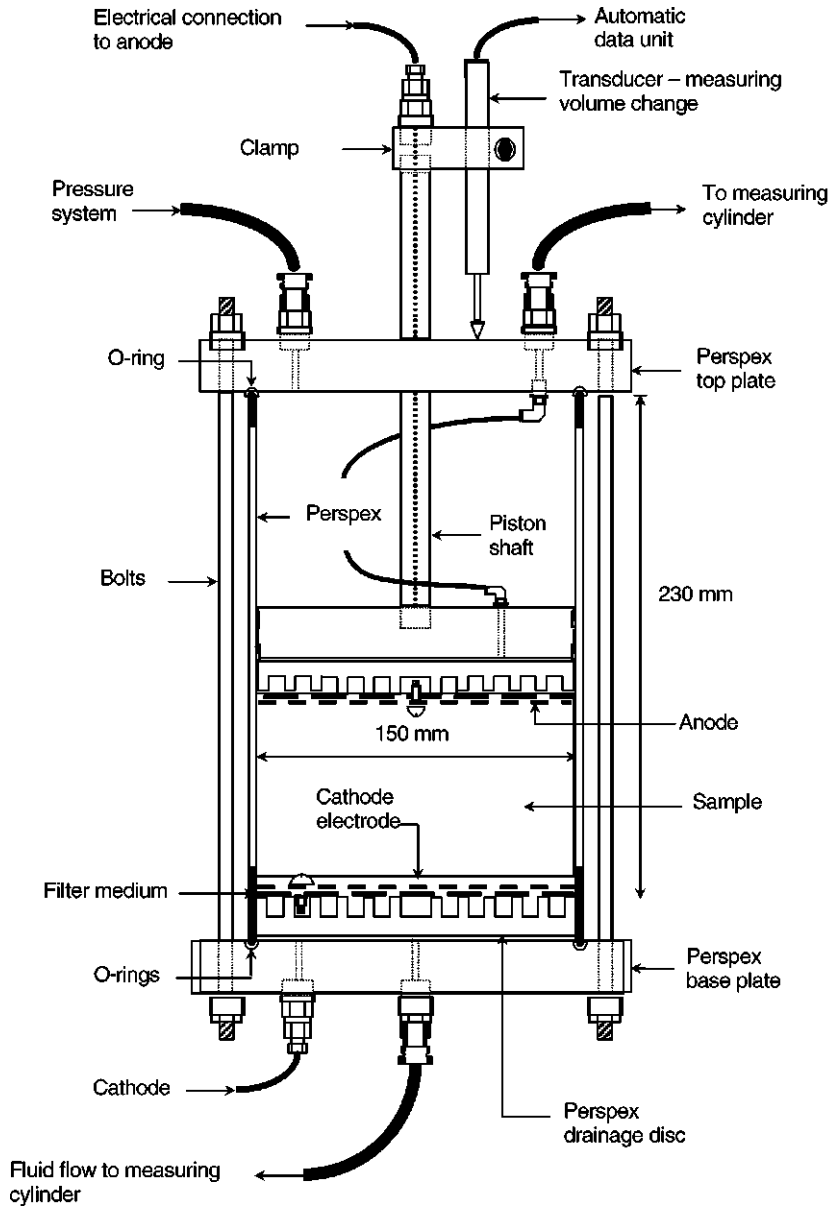

5.6 Electro-osmotic cell (not to scale) (after Hamir, 1997).

electro-osmotic process causes a shift in the particle size distribution to a coarser grain size.

Specialist electro-osmotic testing

The suitability of a material for electrokinetic treatment is best determined using an electro-osmotic cell. The cell used with EKG materials was originally developed by Banerjee and Vitayasupakorn (1985) and later modified by Hamir (1997). The cell is shown schematically in Fig. 5.6 and consists of a Perspex cylinder with a fixed base plate and an internal moveable piston whose movement may be monitored by means of a linear variable-displacement transducer. Provision is made for the location of disc-type electrodes both on the piston and on the fixed base plate by means of cable glands that permit the passage of an electrical cable into the cell, without the loss of pressure. Additionally, the cell incorporates side ports through which the water pressure and voltage gradient of pores may be measured if required by means of a hypodermic needle tipped with porous ceramic. The chamber behind the moveable piston may be pressurized to apply a consolidation pressure to the soil sample. Back pressure may also be applied to the soil sample through tubing which passes through the piston and the base plate; this tubing also acts as a drain for any excess pore water pressure. An alternative to the electro-osmotic cell is the use of an electro-osmosis box described by Nettleton (1996) and Adali (1999).

The usefulness and relevance of the various tests, which can be undertaken to assess the suitability of materials suitable for electrokinetic treatment, are shown in Table 5.4.

Table 5.4 Usefulness of soil tests for assessing acceptability for electro-osmosis (after Pugh, 2002)

Test	Usefulness ^a	Acceptability range
Atterberg limits	✓✓✓	Plasticity index, 5–30%
Water content	✓✓✓	Liquidity index, 0.6–1.0
Particles size distribution (sieve/sedimentation)	✓✓✓✓	See British Standards Institution (1986)
Particle density	✓	Not applicable
Organic content	✓✓	Up to organic
One-dimensional consolidation parameters	✓✓✓	$mv = 0.3\text{--}1.5 \text{ MN/m}^2$
Disc electrode	✓✓✓	0.5–0.005 S/m
Hydraulic permeability	✓✓✓	< 1–8 m/s
Undrained shear strength	✓✓	< 55 kPa
Drained shear strength	✓	$\phi' < 30^\circ$
Electro-osmosis cell	✓✓✓✓	Not applicable
Electro-osmosis box	✓✓✓✓	Not applicable

^a✓✓✓✓, excellent; ✓✓✓, good; ✓✓, reasonable; ✓, poor.

5.4.13 Civil and environmental applications of active geosynthetics

It has been established that conductive geosynthetics, acting as electrodes, can be used to effect the movement of contaminants through soil to the electrodes and then to adsorb them. Using electrophoresis it is possible to dewater industrial wastes, which are currently untreatable and can only be disposed of in tailing lagoons.

Conductive geosynthetics can be used to consolidate soil or to reduce the volume of industrial wastes by electro-osmosis, thus significantly lowering the cost of disposal. The use of conductive reinforcement can permit the use of fine, very wet material as fill for reinforced structures. Initial studies have shown that the use of electrically conductive band drains could prevent liquefaction of susceptible soils during earthquakes.

Other applications can be seen in different fields such as sport and horticulture. The use of conductive geosynthetics can resolve some of the problems inherent in many large sports stadia, such as the detrimental effect of shade on growing surfaces. An electrically conductive geosynthetic laid as a continuous porous membrane at root level provides oxygen directly to the root system as well as offering a method to control drainage, aeration and ball bounce (Lamont-Black *et al.*, 2003). A working model of this technology was exhibited in the Science Museum in London during the 2002 Football World Cup.

Three basic applications areas can be identified for active geosynthetics.

- 1 Accelerated settlement of solids from liquids (electrophoresis).
- 2 Dewatering to reduce volume alone (electro-osmosis).
- 3 Consolidation to improve strength by consolidation (electro-osmosis).

The application areas of active geosynthetics can be further identified by consideration of the electrical conductivity and the water content of the material to be treated (Table 5.4). The use of EKG reinforcement represents an extension of current reinforced soil technology which has important implications with respect to the type of fill that can be used with these structures.

The application of EKGs for the construction of reinforced soil, consolidation of weak soil and sports applications has been reported by Pugh *et al.* (2000), Jones and Pugh (2001), Lamont-Black *et al.* (2003), Glendinning *et al.* (2005) and Jones *et al.* (2005). The results presented demonstrate that EKGs can lead to improvements and forms of construction beyond those that can be achieved by conventional methods. The use of active geosynthetics to stabilize mine tailings has been reported by Fourie *et al.* (2002).

5.5 Future trends

5.5.1 Novel applications of active geosynthetics

A number of novel applications for active geosynthetics have been proposed including those by Jones *et al.* (2005).

Trenching and excavation

It would be possible to combine EKG dewatering with conventional well pointing technology in low-permeability soils to achieve a more rapid drawdown of the phreatic surface than that currently possible. An additional benefit of electro-osmotic dewatering is that the soil properties may be improved which will make excavation easier and more stable.

Earth pressure balance machine or mining methods could be enhanced using EKG technology to improve the soil conditions in the vicinity of the tunnel or to reduce post-construction settlements associated with the tunnel. If access to the surface was also available, the EKG could be installed at the surface to assist the process. In addition, electrokinetics could be used in very soft soils to reduce the possibility of chimney formation.

Piling

Electrokinetic phenomena can assist with piling in two principal ways. If EKGs are installed in close proximity to the piling area and steel piles are made into the cathodes the result would be to soften the soil locally in the vicinity of the piles and to facilitate driving. Once the desired piling depth has been achieved, the electrokinetic process can be shut down and the soil will then gradually regain its equilibrium and the soil properties return to their former state around the piles. Preferentially, the polarity could be reversed, making the piles anodic and therefore improving the soil properties in the vicinity of the piles. The latter process has been successfully employed in Canada (Milligan, 1994).

Enhanced lime migration

EKGs also have a potential application in improving existing lime pile techniques. In this case, the EKG could be used as a conductive element to establish electro-osmotic flow to induce the migration of calcium ions through the soil, thereby increasing the zone of influence of the pile by causing lime migration to a greater radius than occurs by conventional diffusion.

Slope stability

The stability of slopes may be improved through the use of an EKG to achieve a

more rapid dewatering of the soil and to act as drains to reduce pore water pressures within an unstable cohesive slope. The application of a potential difference generates negative pore water pressures at the anode and increase the soil strength and an increase in bond between the EKG nail or anchor and the soil, resulting in an overall increase in the stability of the slope.

Shrinkage and swelling prevention of shallow foundations and pipelines

EKG technology may be able to offer a remedy to the problem associated with low-rise structures built with shallow foundations, which are constructed on soils prone to shrinkage and swelling. In this case, the EKG would allow moisture control of the susceptible strata and either add or remove water as necessary to prevent the volume change of the founding stratum.

Remediation of contaminated sites

The use of electrokinetic techniques to provide *in situ* treatment of contaminated soils is a developing technology. Active geosynthetics in the form of EKG materials have been shown to facilitate this form of treatment including the application of *in situ* bioremediation (Nettleton, 1996).

Electrokinetic dewatering of geotubes

Geotubes used to contain and dewater difficult waste materials can be enhanced using electrokinetic techniques. In this application the geotube is formed as a cathode with an anode installed within the waste material.

Improvement in process dewatering

The treatment and disposal of sewage sludge are one of the most problematical issues affecting waste water treatment in the developed world. It has been shown that electrokinetic dewatering of sludge is more efficient than conventional hydraulic-driven methods and this is anticipated to be a major application of electroconductive geosynthetics.

Improvement in horticultural processes

Conductive geosynthetics have been shown to provide technical benefits to the sports turf industry; the same principles can be transferred to horticulture.

Production of fertilizer from sewage waste

One method of treating humic sludge is by thickening, pressing or centrifuging and then drying in the open air in elongated stockpiles or windrows. Wood waste is

added to the sludge to improve the mechanical handling characteristics; this has a cost implication and results in a significant increase in volume to be finally disposed of. Electrokinetic treatment of the windrows has shown that the drying process can be accelerated and that there is the potential for the use of green waste in place of wood waste which has major economic potential. In addition, the product of the electrokinetic treatment could be used as fertilizer.

5.6 Sources of further information

General information relating to geosynthetics and related products can be obtained from the web site of the International Geosynthetics Society (IGS) (2006).

The conferences run under the auspices of the IGS cover the latest developments of the technology and all major manufacturers of geosynthetics are members of the IGS.

There are two official journals of the International Geosynthetics Society: *Geotextiles and Geomembranes* published by Elsevier, and *Geosynthetics International* published by Thomas Telford. Both are available online.

Information on electrically conductive geosynthetics is available from Electrokinetic Ltd (2006)

5.7 References

- Abiera, H. O., Miura, N., Bergado, D. T. and Nomura, T. (1999), 'Effects of using electro-conductive PVD in the consolidation of reconstituted Ariake clay,' *Journal of Southeast Asian Geotechnical Society*, **30**(2), 67–83.
- Acar, Y. B. and Alshawabkeh, A. K. (1994), 'Modelling conduction phenomena in soils under an electric current', *Proceedings of the 13th International Conference on Soil Mechanics and Foundation Engineering*, Vol. 2, New Delhi, India, 1994, A. A. Balkema, Rotterdam, pp. 669–672.
- Adali, E. (1999), 'Study of electro-osmosis in multi-layered soils', *MSc Dissertation*, Geotechnical Group, Department of Civil Engineering, University of Newcastle upon Tyne, Newcastle upon Tyne, UK.
- Ast, W. and Haberland, J. (2002), 'Reinforced embankment combined with a new developed warning system for high-speed trains over areas of previous mining', *Proceedings of the 7th International Conference on Geosynthetics*, Nice, France, 2002, A. A. Balkema, Rotterdam, pp. 335–340.
- Banerjee, S. and Vitayasupakorn, V. (1984), 'Oedometer tests', *Journal of Geotechnical Engineering*, **110**(8), 1007–1023.
- Bjerrum, L., Moum, J. and Eide, O. (1967), 'Application of electro-osmosis to a foundation problem in Norwegian quick clay', *Géotechnique*, **17**, 214–235.
- Briançon, L., Nancey, A., Caquel, F. and Villard, P. (2004), 'New technology for strain measurements in soil and the survey of reinforced earth constructions', in *Proceedings of the 3rd European Geosynthetics Conference*, Munich, Germany, 2004, A. A. Balkema, Rotterdam, pp. 471–476.
- British Standards Institution (1986), *BS 8004 Code of Practice for Foundations*, British Standards Institution, London.

- British Standards Institution (1990), *BS1377 Methods of Test for Soils for Civil Engineering Purposes*, British Standards Institution, London.
- British Standards Institution (1995), *BS8006 Code of Practice for Strengthened/Reinforced Soil and other Fills*, British Standards Institution, London.
- Carter, M. and Bentley, S. P. (1991), *Correlations of Soil Properties*, Pentech Press, London.
- Casagrande, L. (1952), 'Electro-osmotic stabilisation of soils', *Journal of the Boston Society of the Civil Engineers Section, American Society of Civil Engineers*, **39**, 51–83.
- Casagrande, L., Loughney, R. and Matich, M. A. J. (1961), 'Electro-osmotic stabilization of a high slope in loose saturated silt', *Proceedings of the 5th International Conference on Soil Mechanics and Foundation Engineering*, Vol. 2, Paris, France, 1961, A. A. Balkema, Rotterdam, pp. 555–561.
- Das, B. M. (1997), *Advanced Soil Mechanics.*, 2nd edition, Taylor & Francis, London,
- Electrokinetic (2006), <http://www.electrokinetic.co.uk>
- Esrig, M. I. (1968), 'Pore pressures, consolidation and electrokinetics', *Journal of the Soil Mechanics Division, American Society of Civil Engineers*, **94**(SM4), 899–921.
- Fourie, A. B., Johns, D. and Jones, C. J. F. P. (2002), 'In-situ dewatering of mine tailings using electrokinetic geosynthetics', in *Proceeding of the International Conference on Tailings and Mine Waste*, London, UK, 2002, Thomas Telford, London, pp. 341–345.
- Glendinning, S., Jones, C. J. F. P. and Pugh, R. C. (2005), 'Reinforced soil using cohesive fill and electrokinetic geosynthetics', *International Journal of Geomechanics*, **5**(2), 138–146.
- Grey, D. H. and Mitchell, J. K. (1967), 'Fundamental aspects of electro-osmosis in soils', *Journal of the Soil Mechanics and Foundation Division, American Society of Civil Engineers*, **93**(SM6), 209–136 (closure discussion in (1969), *Journal of the Soil Mechanics and Foundation Division, American Society of Civil Engineers*, **95**(SM3), 875–879).
- Hamir, R. (1997), 'Some aspects and applications of electrically conductive geosynthetic materials', *PhD Thesis*, Geotechnical Group, Department of Civil Engineering, University of Newcastle upon Tyne, Newcastle upon Tyne, UK.
- Hamir, R., Jones C. J. F. P. and Clarke, B. G. (2001), 'Electrically conductive geosynthetics for consolidation and reinforced soil', *Geotextiles and Geomembranes*, **19**(8), 455–483.
- Head, K. H. (1982), *Manual of Soil Laboratory Testing*; Vol. 2, *Permeability, Shear Strength and Compressibility Tests*, Pentech Press, London.
- Heshmati, S. (1993), 'The action of geotextiles in providing combined drainage and reinforcement to cohesive soil,' *PhD Thesis*, University of Newcastle upon Tyne, Newcastle upon Tyne, UK.
- International Geosynthesis Society (2006), <http://www.geosynthetic.society.org>.
- Johnson, S. J. (1970), 'Foundation precompression with vertical sand drains', *Journal of the Soil Mechanics and Foundation Division, American Society of Civil Engineers*, **96**(SM1) 145–175
- Jones, C. J. F. P. (1996), *Earth Reinforcement and Soil Structures*, Thomas Telford, London.
- Jones, C. J. F. P., Fakher, A., Hamir, R. and Nettleton, I. M. (1996), 'Geosynthetic materials with improved reinforcement capabilities', *Proceedings of the International Symposium on Earth Reinforcement*, Vol. 2, Fukuoka Kyushu, Japan, 1996, A. A. Balkema, Rotterdam, pp. 865–883.
- Jones, C. J. F. P. and Pugh, R. C. (2001), 'A full-scale field trial of electrokinetically enhanced cohesive reinforced soil using electrically conductive geosynthetics', in *Landmarks in Earth Reinforcement* (Eds H. Ochiai, J. Otani and K. Omine), Swets & Zeitlinger, Lisse, pp. 219–223.

- Jones, C. J. F. P., Pugh, R. C., Lamont-Black, J. and Glendinning, S. (2005), 'New applications for smart geosynthetics', in *Proceedings of Geo-Frontiers 2005, ASCE Special Publications 130-142* (Ed. E. M. Rathje), Austin, Texas, USA, 24-26 January, 2005, American Society of Civil Engineers, New York: H:\pdffiles\papers\GSP142\40769-6719.pdf.
- Kempton, G. T., Jones, C. J. F. P., Jewell, R. A. and Naughton, P. J. (2000), 'Construction of slopes using cohesive fills and a new innovative geosynthetic material', in *Proceedings of the 2nd European Geosynthetics Conference*, Vol. 2, Bologna, Italy, 2000, Patron Editore, Bologna, pp. 825-828.
- Lambe, T. W. and Whitman, R. V. (1969), *Soil Mechanics*, Wiley, New York.
- Lamont-Black, J., Glendinning, S., Jones, C. J. F. P. and Huntley, D. T. (2003), 'Electrokinetic processes for the management of natural sports turf', in *Proceedings of the National Turfgrass Foundation Annual Conference*, Harrogate, North Yorkshire, UK, National Turfgrass Association, London, p. 4.
- Leitner, B., Sobolewski, J., Ast, W. and Hangen, H. (2002), 'A geosynthetic over bridging system in the base of a railway embankment located on an area prone to subsidence at Groebers: construction experience', in *Proceedings of the 7th International Conference on Geosynthetics*, Nice, France, 2002, A. A. Balkema, Rotterdam, pp. 349-354.
- Lockheart, N. C. (1983), 'Electro-osmotic dewatering of clays: II influence of salt, acid and flocculants', *Colloids and Surfaces*, **6**, 239-251.
- Lo, K. Y., Ho, K. S. and Incullet, I. I. (1991), 'Field test of electroosmotic strengthening of soft sensitive clay', *Canadian Geotechnical Journal*, **28**, 74-83.
- Micic, S., Shang, J. Q., Lo, K. Y., Lee, N. Y. and Lee, S. W. (2001), 'Electrokinetic strengthening of a marine sediment using intermittent current', *Canadian Geotechnical Journal*, **38**(2), 287-302.
- Milligan, V. (1994), 'First application of electro-osmosis to improve friction pile capacity - three decades later', *Proceedings of the 13th International Conference on Soil Mechanics and Foundation Engineering*, Vol. 5, New Delhi, India, 1994, A. A. Balkema, Rotterdam, pp. 1-5.
- Mitchell, J. K. (1993), *Fundamentals of Soil Behaviour*, 2nd edition, Wiley, New York.
- Mohamedelhassan, E. and Shang, J. Q. (2001), 'Effects of electro materials and current intermittence in electro-osmosis', *Ground Improvement*, **5**(3), 3-11.
- Nancy, A., Briangon, L., and Villard, P. (2004), 'Geodetect: the first "intelligent" earth construction', Private communication.
- Nettleton, I. M. (1996), 'Electro-bioremediation', *Internal Report*, Geotechnical Group, University of Newcastle upon Tyne, Newcastle upon Tyne, UK.
- Nettleton, I. M., Jones, C. J. F. P., Clarke, B. G. and Hamir, R. (1998), 'Electrokinetic geosynthetics and their applications', in *Proceedings of the 6th International Conference on Geosynthetics*, Vol. 2, Atlanta, Georgia, USA, 1998, Industrial Fabrics Association, Roseville, Minnesota, pp. 871-876.
- Pugh, R. C. (2002), 'The application of electrokinetic geosynthetic materials in the construction industry', *PhD Thesis*, University of Newcastle upon Tyne, Newcastle upon Tyne, UK.
- Pugh, R. C., Clarke, B. G., and Jones, C. J. F. P. (2000), 'An electro-osmotic consolidation trial using electrokinetic geosynthetics', in *Proceedings of the 4th International Conference on Ground Improvement Geosystems*, Vol. 2, Helsinki, Finland, 2000, Finnish Geotechnical Society, Helsinki, pp. 533-540.
- Villard, P., Gourc, J. P. and Giraud, H. (2000), 'A geosynthetic reinforcement solution to

prevent the formation of localized sinkholes', *Canadian Geotechnical Journal*, **37**(5), 987–999.

Wan, T. Y. and Mitchell, J. K. (1976), 'Electro-osmotic consolidation of soils', *Journal of the Geotechnical Engineering Division, American Society of Civil Engineers*, **102**(GT5), 473–491.

Yeung, A. T. and Mitchell, J. K. (1993), 'Coupled fluid, electrical and chemical flows in soil', *Géotechnique*, **43**(1), 121–134.

The use of geosynthetics as filters in civil engineering

J. FANNIN

University of British Columbia, Canada

Filters are typically constructed as part of a drainage system and have a wide range of applications in civil engineering works. The primary objective of the filter is to protect against soil erosion in applications where groundwater flow has the potential to cause a seepage-induced movement of particles while, at the same time, to provide for adequate discharge capacity and therefore unimpeded drainage of the soil. Accordingly, properly designed filters are integral to the performance of construction works, both with respect to the economic concerns governing serviceability and also for safety concerns governing stability at the ultimate limit state.

6.1 Introduction

Applications in which filters are commonly specified include drainage systems behind retaining walls, adjacent to roads and foundations, within slopes, and under hydraulic structures, landfills and sports fields. Consider, for example, placement of a geotextile filter for stabilization of the cut slope illustrated in Fig. 6.1; where groundwater exits the lower portion of the slope, the geotextile provides for retention of erodible soils and permits seepage flow to exit freely into an overlying blanket of rock. In many construction applications, the design life of the filter and companion drainage system is typically the same as that of the constructed works. However, this is not always the case. Consider the use of prefabricated vertical drains to accelerate consolidation of compressible soils under an embankment, a case of ground improvement for which the design life of the filter is considerably shorter than that of the related engineering works.

The principle of using a filter zone to control groundwater seepage and to protect against erosion was studied by Karl Terzaghi, with application to foundation design of small weirs, for which he was first granted a patent in 1922. Further studies led directly to applications in large-zoned earthfill dams, and the development of empirical rules for specifying the grain size distribution of the filter layer. The filter medium consisted of one or more select gradations of cohesionless soil,



6.1 Cut-slope stabilization: geotextile filter and rock blanket.

for which the characteristic grain sizes D_n are reported from laboratory testing. In effect, for a granular filter, by specifying directly the size distribution of grains, the corresponding size distribution of openings in the porous medium is determined indirectly. Hence, the opening size distribution is governed by soil type and may be influenced by its method of field placement and any potential for segregation during placement. In contrast, the opening size distribution of a geotextile is controlled by the process of manufacturing, for which one or more characteristic values of opening size O_n in the fabric are established directly by means of laboratory testing and reported by the manufacturer with reference to a statistical database for purposes of quality control.

6.1.1 Geotextiles

The manufacturing process yields several styles of geotextile, two of which, a non-woven and a woven fabric, are typically used in filtration applications. The styles are inherently different. A non-woven geotextile consists of a layer of many randomly oriented polymer strands that are bonded to obtain a planar fabric. The individual strands are usually a short fibre or a continuous filament, generally made of polypropylene and occasionally of polyester or polyethylene. The common methods of bonding are either physical entanglement of the strands, yielding a needle-punched non-woven geotextile, or thermal fusing of contact points between the strands during a calendering operation, which produces a heat-bonded non-woven geotextile. In contrast, a woven geotextile is made from individual

polymer strands that are aligned and interweaved on an industrial loom, again yielding a planar fabric. The strand itself is usually a tape, a monofilament or a multifilament yarn. A fibrillated strand is one that has been intentionally split along portions of its length, as a part of the manufacturing process, to condition its properties. Geotextiles are supplied on a roll, with the machine direction being perpendicular to the roll, and the cross-machine direction being parallel to the roll.


Inherent differences between each of these manufacturing processes, and the resulting style of a geotextile, impart subtle differences to the characteristic opening size and opening size distribution of the fabric and, by association, to the capacity for flow of water across the plane of the fabric. It also imparts variations in tensile strength and stiffness. Accordingly, in the design approach, assessment of a candidate geotextile for a proposed filtration application must account for a series of compatibility requirements.

6.2 Compatibility requirements

Filtration compatibility requires that there is no unacceptable erosion as a consequence of soil loss through the geotextile while, at the same time, provision is made for unimpeded flow of water seeping from that soil. Therefore, the principal requirements for compatibility are those of, firstly, soil retention and, secondly, cross-plane permeability. They represent competing interests, insomuch as soil retention is assured by relatively small pore-size openings in the geotextile whereas cross-plane permeability is assured by many relatively large pore-size openings. In addition to these geometric and hydraulic provisions, there is also a requirement for, thirdly, provision of adequate strength to ensure that the geotextile is not damaged in the process of installation and can accommodate, thereafter, any loads that are imposed on it over the service life of the installation.

Consider the first requirement, for soil retention. Filtration compatibility is contingent on the fact that the geotextile has a distribution of pore-size openings that prevents any significant movement of soil particles through those openings. The expectation, as with granular filters, is that retention of coarser particles in the soil then promotes the development of a stable interface or 'bridging zone' in a thin zone of soil adjacent to geotextile (Fig. 6.2). Given this expectation, the design approach is predicated on matching a characteristic pore size opening of the geotextile (O_n , e.g. O_{95}) to a characteristic particle size of the soil (D_n , e.g. D_{85}). The approach is very similar to that adopted in granular filters, where a characteristic particle size of the filter (e.g. D_{15}) is used as a default measure of opening size (e.g. D_{15}) and matched to a characteristic particle size of the soil.

With respect to the second requirement, for cross-plane permeability, filtration compatibility is contingent on the fact that the geotextile has a capacity for discharge flow significantly greater than that of the soil against which it is placed. The expectation, as for granular filters, is that, if each successive layer in the direction of seepage flow exhibits a greater permeability, there is no potential to

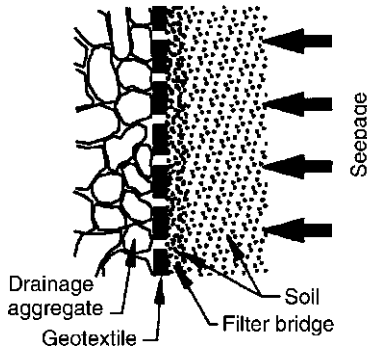


6.2 Soil retention by means of a bridging zone (after Holtz *et al.*, 1997).

impede discharge flow through those layers. The design approach is commonly based on matching an index value of cross-plane permeability (k_n) for the geotextile to the permeability (k_s) of the soil. The approach differs from that adopted for granular filters, where the permeability of both filter and soil are characterized, indirectly, by a characteristic particle size (e.g. D_{15}).

In considering the third requirement for strength, filtration compatibility is contingent on the fact that the geotextile exhibits adequate capacity to resist loads mobilized in the polymer strands as a consequence of localized deformation, without any loss of integrity in the fabric. The greatest demand on the geotextile is typically that encountered during the installation process. Thereafter, it must also be sufficiently durable to ensure that those loads can be sustained over the service life of the installation. The design approach is usually based on one or more index values of strength that are used to categorize the geotextile according to a classification system (e.g. a three-class system of high, moderate or low strength). A required strength class is then established for the application, with reference to the anticipated severity of the installation process. Durability over the service life of the structure is often addressed with reference to the polymer from which the geotextile is manufactured, and appropriate provisions for ultraviolet (UV) protection, taking into account the nature of the soil and groundwater chemistry. Although the approach again differs substantially from that used for granular filters, which do not exhibit any tensile strength, it is similar with regard to the need to ensure durability of the filter medium itself.

6.3 Material properties for design

Geotextile properties are established from laboratory testing of specimens taken from a sample of the fabric that is cut from the manufactured roll. The sample is deemed representative of the roll and chosen accordingly; the number of specimens is specified in the methodology of the laboratory test itself. Material

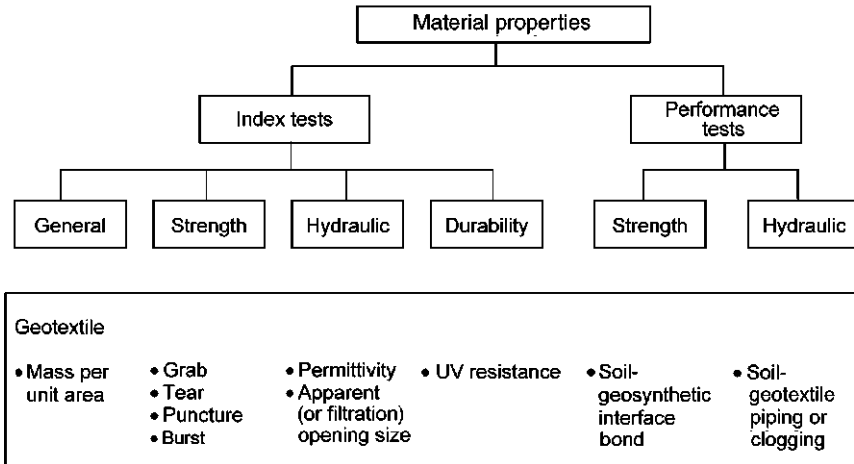

6.3 Material properties of geotextiles (adapted from Fannin, 2000).


properties are commonly established with reference to a standard test method. The development and publication of such test methods are usually coordinated by governmental or intra-governmental standards agencies, following experimental studies in specialist laboratories. Standard test methods developed at the national level often vary between countries. The work of the International Organization for Standardization (ISO) and the European Committee for Standardization (Comité Européen de Normalisation (CEN)) seeks to harmonize those differences at the international level.

In considering the intent of a laboratory test, it is convenient to distinguish between an index test and a performance test (Fig. 6.3). Index tests are used to establish material properties that are specific to the geotextile alone, with little or no direct consideration given to the relevance of the laboratory test conditions to those of the field application. Examples include the characteristic pore size opening, cross-plane permeability, strength and UV resistance of the geotextile. In contrast, performance tests are used to establish material properties of the geotextile that do take into consideration aspects of the field application, often with reference to soil–geotextile interaction. Examples include that of permeameter testing of soil and geotextile to examine the potential for piping or clogging under the influence of seepage over a designated range of hydraulic gradient, and that of direct shearbox testing to determine the interface strength between a geotextile and soil over a designated range of vertical effective stress.

6.3.1 Index tests


Pore size opening

Geotextiles exhibit a distribution of pore size openings, with the variation in size

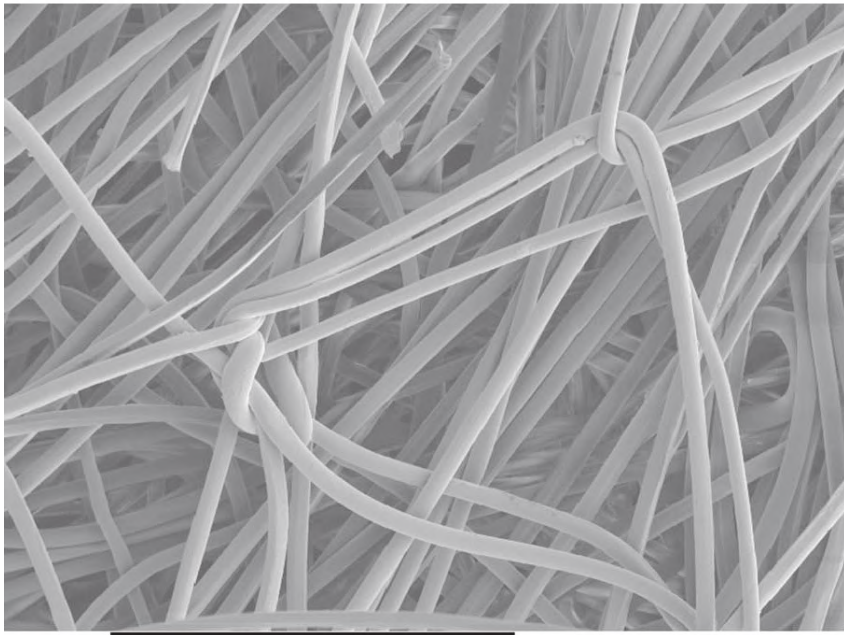

700 μm

(a)

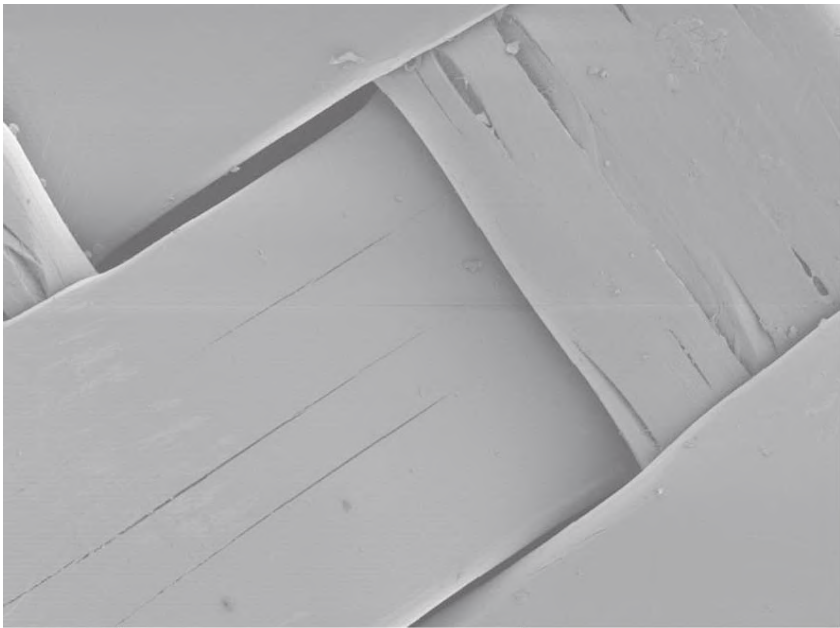

700 μm

(b)

6.4 Pore-size openings of (a) a needle-punched non-woven geotextile: (b) a woven geotextile.

being largely determined by attributes of the polymer strand and the manufacturing process. In contrast to a non-woven geotextile, see Fig. 6.4(a), which has a wide range of opening sizes, a woven geotextile tends to have narrow range of relatively larger openings, see Fig. 6.4(b). A characteristic opening size of the fabric is established through indirect means, typically by sieving a gradation of glass ballotini or sand through a specimen of the geotextile, and subsequent determination of the grain size distribution curve of the fraction that passes through the fabric under a prescribed disturbance. The disturbing action typically involves either dry shaking or hydrodynamic flushing. A characteristic opening size, e.g. O_{95} (μm), is taken to be the equivalent grain size of the fraction passing, in this case D_{95} , with the implicit understanding that 95% of the pore openings are less than or equal to this value.

Cross-plane permeability

Geotextiles exhibit a relatively wide range of volumetric flow rate per unit area across the plane of the fabric, with discharge capacity again being largely determined by attributes of the polymer strand and the manufacturing process. The geotextile is mounted in a permeameter, and subject to flow under the influence of either a constant differential head or a falling head. A calculation is typically made of the normal permeability k_n (cm/s), which may also be reported as a value of permittivity ψ (s^{-1}) if divided by the thickness of the fabric.

Strength

Geotextiles are thermoviscoelastic materials, which cause the relation between load (or stress) and deformation (or strain) to be governed by ambient temperature and imposed rate of displacement. Accordingly, geotextiles do not exhibit a unique strength in testing. Strength is generally established from testing of a specimen that is subject to either axisymmetric loading, or a loading condition that approximates plane strain. The imposed rate of displacement can vary significantly between types of test. Examples of axisymmetric loading include a burst or puncture test, while an example of the latter is tensile loading of a relatively wide specimen in either the machine or the cross-machine direction. Axisymmetric loading yields a value of strength (N), and plane strain loading a value of strength per unit width (kN/m).

Ultraviolet resistance

Geotextiles are made from polymers, all of which degrade in the presence of sustained exposure to UV light, yielding a loss of strength. The impact of UV exposure is mitigated through the addition, during manufacture, of stabilizing agents to the polymer of the geotextile. Resistance is characterized in laboratory

testing by a measurement of percentage strength loss that occurs in the geotextile following a prescribed period of exposure to a UV light source. The loss (%) is reported over the duration of exposure time.

6.3.2 Performance tests

Piping or clogging behaviour

Filtration compatibility is predicated on the geotextile satisfying a requirement for soil retention. Incompatibility may take the form of unacceptable piping or clogging. Piping refers to particle migration through the geotextile, whereas clogging is a result of entrapment of particles within the geotextile. With reference to the permeability of the soil that is retained, piping yields a zone of relatively high permeability adjacent to the geotextile while, in contrast, clogging generates a zone of relatively low permeability. Compatibility may therefore be evaluated by placing the soil and geotextile in a permeameter, imposing a prescribed seepage regime, and monitoring any change in the permeability of the soil–geotextile interface relative to that of the undisturbed soil. Interpretation of the results involves comparison of observed change against a threshold value of acceptability.

Interface strength

A geotextile invokes strength at the interface with a soil through mobilization of a shear resistance that is largely controlled by friction. The available strength is therefore governed both by the type of soil and by attributes of the fabric that are dependent on the type of polymer, strand and manufacturing process. Interface strength is commonly established in direct shearbox testing, for a prescribed range of vertical effective stress. In cohesionless soils, the efficiency of the bond with the geotextile is expressed as a ratio of interface strength, $\tan \delta$, to the angle of shearing resistance of the soil, $\tan \varphi$.

6.4 Design criteria

Compatibility of a geotextile filter and the soil against which it is placed is governed by the three principal requirements of soil retention, cross-plane permeability and strength. Many generalized design criteria have been proposed for each these requirements, all of which have a common basis.

6.4.1 Soil retention

For retention of the soil, the maximum value of the characteristic opening size of

the geotextile is limited by the larger grains of soil against which it is placed, where

$$O_n \leq C_1 D_n \quad [6.1]$$

and C_1 is a dimensionless constant that may be used to differentiate between soil type and style of geotextile. Given the empirical basis of the relation, it is important to account for the test method used to establish the characteristic pore size opening since different test methods have been noted to yield a variation in opening size for the same geotextile (Bhatia *et al.*, 1996). Many design criteria have been proposed for soil retention, most of which relate to unidirectional flow in coarse-grained soils, and some of which are appropriate to fine-grained soils (Table 6.1). The geotextile is typically characterized by a relatively coarse opening size O_{90} or O_{95} and the soil by a relatively large grain size D_{50} or D_{85} , with distinction frequently made between a woven and non-woven geotextile, and recognition occasionally given to the shape of the grain size distribution of the soil. A comprehensive framework has been proposed by Mylnarek (2000), which considers both coarse- and fine-grained soils, the phenomena of dispersion and internal instability in those soils, and the concept of both a minimum and a maximum opening size for the geotextile. Further, it recommends performance testing of some geotextile–soil combinations in order to evaluate filtration compatibility (Fig. 6.5).

6.4.2 Cross-plane permeability

For cross-plane permeability, the capacity of the geotextile must meet or exceed the cross-plane permeability (k_s) of the soil, where

$$k_n \geq C_2 k_s \quad [6.2]$$

C_2 is a constant that may be used to differentiate between soil type and severity of the seepage condition, and k_n is established from index testing of the geotextile. Typical hydraulic gradients may vary from about 1.0 in a trench drain to more than 10 in shoreline protection works (Giroud, 1996) leading to suggested values for the constant that vary between 10 and 100. If a performance test, such as the ASTM D5101-01 gradient ratio test (ASTM International, 2005) is conducted for filtration compatibility it will yield, in addition to a qualitative measure of soil retention, a quantitative measure of relative soil–geotextile permeability which is independent of that based on index testing of material properties.

6.4.3 Strength

For strength, it is customary to ensure that the available strength, established from one or more index tests, exceeds required values that may be either established from a site-specific analysis of anticipated loading or, as more usually occurs, defined by minimum values that are believed appropriate to the field application

Table 6.1 Soil retention criteria for geotextiles^a (modified from Palmeira and Fannin, 2002)

Source	Criterion	Remarks
Calhoun (1972)	$O_{95}/D_{85} \leq 1$ no. 200 sieve	Woven geotextiles, soils with $\leq 50\%$ passing through sieve
	$O_{95} \leq 0.2 \text{ mm}$	Woven geotextiles, cohesive soils
Ragutzki (1973) (from Faure, 1988)	$O_f \leq 0.5D_{50} - 0.7D_{50}$	Woven geotextiles and non-woven geotextiles, dynamic or reversing flow, unconfined soil
	$O_f \leq 0.5D_{50} - 1.3D_{50}$	Woven geotextiles, dynamic or reversing flow, confined soil
	$O_f \leq 0.5D_{50} - 1.5D_{50}$	Non-woven geotextiles, dynamic or reversing flow, confined soil
Zitscher (1974) (from Rankilor, 1981)	$O_{50}/D_{50} \leq 1.7-2.7$	Woven geotextiles, soils with $C_u \leq 2$, $D_{50} = 0.1-0.2 \text{ mm}$
	$O_{50}/D_{50} \leq 2.5-3.7$	Non-woven geotextiles, cohesive soils
Ogink (1975)	$O_{90}/D_{90} \leq 1$	Woven geotextiles
	$O_{95}/D_{85} \leq 1.8$	Non-woven geotextiles
	$O_f \leq D_{85}$ (from Faure, 1988)	Dynamic or reversing flow, woven geotextiles and non-woven geotextiles, with formation of a natural filter
	$O_f \leq D_{15}$ (from Faure, 1988)	Dynamic/reversing flow, woven geotextiles and non-woven geotextiles, without the formation of a natural filter
US Army Corps of Engineers (1977)	$0.149 \text{ mm} \leq O_{95} \leq 0.211 \text{ mm}$	$D_{50} > 0.074 \text{ mm}$
	$0.149 \text{ mm} \leq O_{95} \leq D_{85}$	$D_{50} \leq 0.074 \text{ mm}$ Geotextiles should not be used if $D_{85} < 0.074 \text{ mm}$
Schober and Teindl (1979)	$O_{90}/D_{50} \leq 2.5-4.5$	Woven and thin non-woven geotextiles, dependent on C_u
	$O_{90}/D_{50} \leq 4.5-7.5$	Thick non-woven geotextiles, dependent on C_u , silts and sands
Millar <i>et al.</i> (1980)	$O_{50}/D_{85} \leq 1$	Woven geotextiles and non-woven geotextiles


Rankilor (1981)	$O_{50}/D_{85} \leq 1$ $O_{15}/D_{15} \leq 1$	Nonwoven geotextiles, soils with $0.02 \text{ mm} \leq D_{85} \leq 0.25 \text{ mm}$ Nonwoven geotextiles, soils with $D_{85} > 0.25 \text{ mm}$
Giroud (1982)	$O_{95}/D_{50} < C'_U$ $O_{95}/D_{50} < 9/C'_U$ $O_{95}/D_{50} < 1.5C'_U$ $O_{95}/D_{50} < 13.5/C'_U$ $O_{95}/D_{50} < 2C'_U$ $O_{95}/D_{50} < 18/C'_U$	$I_D < 35\%$, $1 < C'_U < 3$ $I_D < 35\%$, $C'_U > 3$ $35\% < I_D < 65\%$, $1 < C'_U < 3$ $35\% < I_D < 65\%$, $C'_U > 3$ $I_D > 65\%$, $1 < C'_U < 3$ $I_D > 65\%$, $C'_U > 3$ Assumes fines in soil migrating for large C_U
Heerten (1982)	$O_{90} < 10D_{50}$ and $O_{90} \leq D_{90}$ $O_{90} < 2.5D_{50}$ and $O_{90} \leq D_{90}$ $O_{90} < 10D_{50}$ and $O_{90} \leq D_{50}$ and $O_{90} \leq 0.1 \text{ mm}$	Cohesionless soils, with $C_U > 5$ and static load conditions Cohesionless soils, with $C_U < 5$ and static load conditions Cohesionless soils, dynamic load conditions Cohesive soils and all load conditions
Carroll (1983)	$O_{95}/D_{85} < 2-3$	Woven and non-woven geotextiles
Christopher and Holtz (1985)	$O_{95}/D_{85} \leq 1-2$ $O_{95}/D_{15} \leq 1$ or $O_{50}/D_{85} \leq 0.5$	Dependent on soil type and C_U Dynamic, pulsating and cyclic flow, if soil can move beneath geotextile
Mlynarek (1985), Mlynarek <i>et al.</i> (1990)	$2D_{15} < O_{95} < 2D_{85}$	Non-woven geotextiles
Comité Français Géosynthétiques (1986)	$O_f/D_{85} \leq 0.38-1.25$	Dependent on soil type, compaction, hydraulic and application conditions
	$O_f \leq 0.5D_{85}$ (from Faure, 1988)	Reversing flow, woven geotextiles and non-woven geotextiles, loose soil
	$O_f \leq 0.75D_{85}$ from Faure, 1988)	Reversing flow, woven geotextiles and non-woven geotextiles, dense soil
Lawson (1986)	$O_{90}/D_n = C$	Developed for residual soils from Hong Kong Values of n and C are obtained by a chart defining regions of acceptable filter performance

Table 6.1 (cont.)

Source	Criterion	Remarks
Lawson (1987) (from Geotechnical Engineering Office, 1993)	$O_{90}/D_{85} \leq 1$	For predominantly granular soils with $D > 0.1$ mm, e.g. residual soils which are granular in nature and alluvial sandy soils
	$0.08 \text{ mm} \leq O_{90} < 0.12 \text{ mm}$	For non-cohesive soils, e.g. silts of alluvial or other origin, and for non-dispersive cohesive soils
	$0.03 \text{ mm} \leq O_{90} \leq D_{85}$	For dispersive cohesive soils
John (1987)	$O_{95}/D_{50} \leq (C'_U)^a$	a is dependent on the size of the particle to be restrained ($a = 0.7$ for D_{85})
Fischer <i>et al.</i> (1990)	$O_{50}/D_{85} \leq 0.8$	Based on geotextile pore size distribution, dependent on C_U of soil
	$O_{95}/D_{15} \leq 1.8-7.0$	
	$O_{50}/D_{50} \leq 0.8-2.0$	
Rollin <i>et al.</i> (1988)	$O_{95} < 1D_{85} - 1.5D_{85}$	Tests with a fine sandy soil and three non-woven needle-punched geotextiles using an upflow filtration apparatus
Luettich <i>et al.</i> (1992)	Design charts	Based on geotextile void size and type, hydraulic conditions and other factors
Ontario Ministry of Transportation (1992)	$O_f/D_{85} < 1.0$ and $O_f > 0.5D_{85}$ or $40 \mu\text{m}$	Non-woven geotextiles preferred, $t_{GT} > 1$ mm; avoid thermally bonded geotextiles
Murray and McGown (1992) (from Corbet, 1993)	$O_{90}/D_{90} = 1-3$	Soils with $1 \leq C_U < 5$, woven and non-woven geotextiles
	$O_{90}/D_{90} < 1-3$	Soils with $5 < C_U < 10$, woven and thin non-woven geotextiles ($t_{GT} \leq 2$ mm); alternative criterion
	$O_{90}/D_{50} < 1.8-6$	Soils with $5 < C_U < 10$, thick non-woven geotextiles ($t_{GT} > 2$ mm); alternative criterion

Bhatia and Huang (1995)	$O_{95}/D_{85} < 0.65 - (0.05 C_c)$ $O_{95}/D_{85} < 2.71 - (0.36 C_c)$ $O_{95} < D_{85}$	$n < 60\%$ and $C_c > 7$ $n < 60\%$ and $C_c < 7$ $n < 60\%$
Lafleur (1999)	$O_f/D_1 < 1$ $1 < O_f/D_1 < 5$	Stable soils ($C_U \leq 6$ and $D_1 = D_{85}$ in this case), soils with $C_U > 6$ but linearly graded ($D_1 = D_{50}$ in this case), gap-graded ($C_U > 6$) internally stable soils ($D_1 = D_G$) and soils with $C_U > 6$ with gradation curve concave upwards and internally stable ($D_1 = D_{30}$) Unstable soils with $D_1 = D_{30}$ for gap graded internally unstable soils and for internally unstable soils with gradation curves concave upwards (risk of piping of fines) Criteria developed for cohesionless soils
Mylnarek (2000)	$A < O_f < B$ (from charts)	Values of A and B established with reference to grain size, coefficient of uniformity, plasticity index and dispersion potential of the soil, and for seepage flow that is either unidirectional or bi-directional (dynamic)

^a C_c , coefficient of curvature of the soil equal to $D_{30}^2/(D_{60}D_{10})$; C_U , coefficient of uniformity of the soil equal to D_{60}/D_{10} ; C'_U , linear coefficient of uniformity of the soil equal to $(D'_{100}/D'_0)^{0.5}$; D_{Gr} , minimum soil gap size; D_1 , indicative size of the protected base soil; D_{50Gr} , mean particle size of the soil fraction smaller than the value of O_f for the geotextile; D_{Yr} , soil particle size corresponding to $Y\%$ passing; D'_{Yr} , soil particle size corresponding to $Y\%$ passing obtained from a straight line fitting of the central part of the soil gradation curve; I_D , density index (relative density); n , geotextile porosity, O_r , filtration opening size based on hydrodynamic sieving; O_{Xr} , geotextile opening size corresponding to X particle size based on dry glass bead sieving; t_{GT} , geotextile thickness.

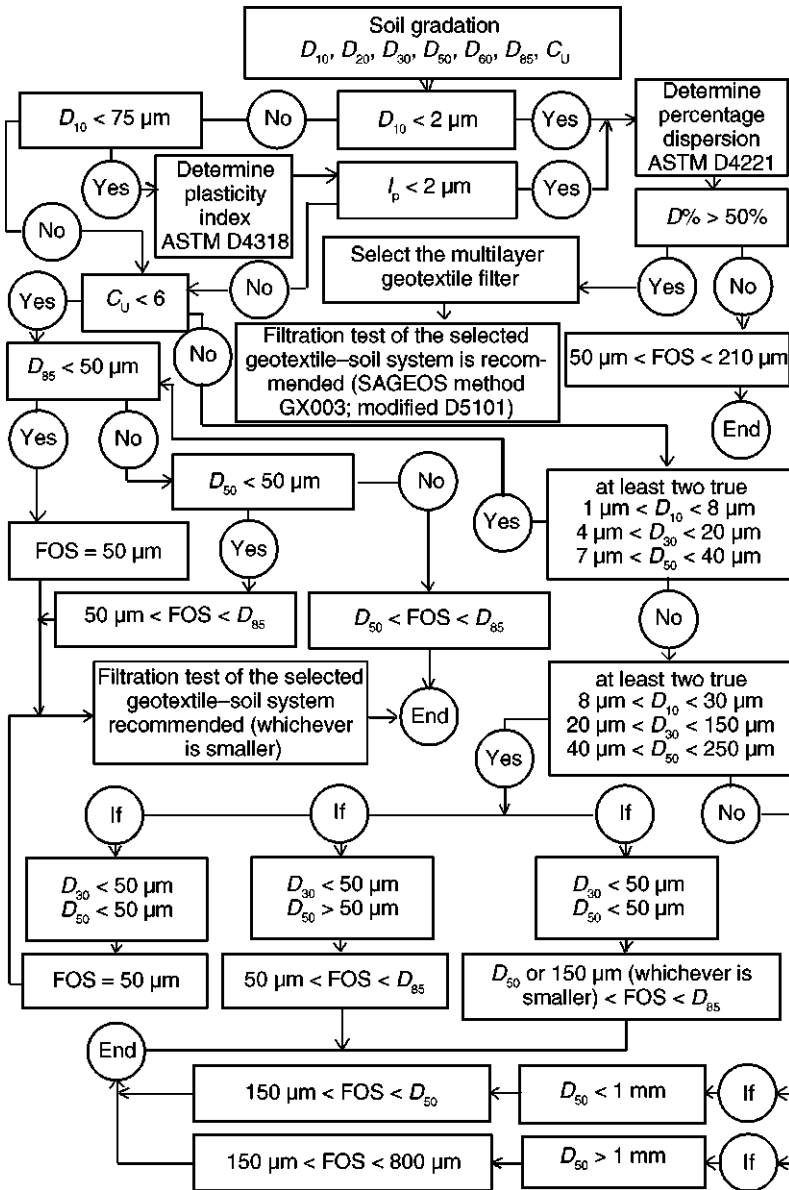

6.5 Design criteria for soil retention in unidirectional flow (after Mylnarek, 2000): FOS, filtration opening size.

based on experience rather than analysis. Additionally, it is usual to ensure that the UV resistance of the geotextile from index testing is greater than a minimum value which again is based entirely on experience, rather than analysis.

6.4.4 Commentary

The design criteria for soil retention, cross-plane permeability and strength are empirical in origin and, unless specifically noted, are considered appropriate to filtration applications where the following hold.

- 1 Seepage flow across the geotextile is predominantly low and unidirectional.
- 2 Confining stress on the geotextile is essentially constant and subject to little change.
- 3 There is consideration given to quality assurance, through site supervision, during placement of the geotextile.

These conditions are commonly encountered in earthworks associated with slopes, retaining walls, shallow foundations and sports fields. Confidence in the design criteria is founded on a considerable body of laboratory experience from testing that simulates these relatively simple field conditions. In contrast, the occurrence of reversing or pulsating flow and cyclic or vibration loading of the ground produce more complex conditions that are not easily reproduced in simple laboratory tests. Accordingly, in these more severe applications, it is recommended that design criteria for soil retention and cross-plane permeability (see for example Holtz *et al.*, 1997 and Mylnarek, 2000) be applied with caution rather than confidence, and with recourse to performance tests to support a site-specific evaluation of filtration compatibility (Fannin and Pishe, 2001).

6.5 Specification of materials

Design criteria are used to identify suitable material properties of a geotextile. More specifically, they are used to establish a maximum opening size, a minimum value for cross-plane permeability, and minimum values for strength of the material. They are required values of material properties for design, based on index tests, and are commonly reported in a construction specification document, together with additional guidance on required provisions for placement of the geotextile on site. On occasion it may be necessary to include additional reference to performance tests, to ensure that a comprehensive statement is provided on the compatibility requirements of a proposed filtration application.

The specification document enables comparison of required material properties, established from the design process, with available material properties, based on the range of geotextile products that can be delivered to site through contact with commercial suppliers. Accordingly, one intended use of the specification document is to identify a candidate product that satisfies design criteria for the application, in the expectation that this will provide for compatibility over the service life of the geotextile filter.

Two approaches may be adopted in the writing of a specification document, with the choice of approach being largely determined by the scope of the construction application. Consider an application that involves, for example, challenging

soils or an unusual flow regime, for which project-specific design criteria have been established. The criteria are typically established with reference to data from a site investigation and may account for special features of the proposed construction. Required material properties are therefore specific to that site, yielding the need for a specification document that is unique to the proposed application, and one that should enable selection of a candidate geotextile that is expected to be fully compatible with the project requirements.

In contrast, consider an application that is, in all respects, a small and routine example of filtration practice for which no detailed site investigation is warranted. From a cost–benefit perspective there is no compelling need to develop a project-specific or unique specification document and, therefore, recourse can legitimately be made to a standard specification. Filtration applications in subsurface drainage and permanent erosion control, as a part of earthworks for road construction, represent good examples of such relatively small and routine provisions. The standard specification document may be used to establish default values for the opening size, cross-plane permeability and strength of the geotextile (see for example AASHTO M 288-00 (American Association of State Highway and Transportation Officials, 2000)). The standard specification therefore acts as a guide to the selection of a candidate geotextile that is expected to be compatible with the project requirements.

Accordingly, the choice in specifying material properties of a geotextile lies between that of a site-specific or unique specification document and that of a generic or standard specification document. The merits of each approach are largely determined by the scope of the construction project, and the nature of the soils and groundwater flow regime.

6.6 Construction considerations

Geotextiles are products manufactured to designated ranges of specific material properties, with commensurate attention given to quality assurance on the rolls that are supplied to site. Each roll identification tag, with product name and roll number, should allow for a direct cross-reference to quality control testing of the production lot by the manufacturer. Where appropriate, e.g. in permanent earthworks associated with significant capital costs or potential for loss of life in the event of failure, the specification document may be written to require submission of a manufacturer's certificate of compliance: the certificate declares the date and location of manufacture and affirms both product style and relevant material properties. The specification document may also be written to allow for independent testing of samples taken from geotextile rolls supplied to site, at the discretion of the engineer, in order to verify the material properties claimed by the manufacturer.

6.6.1 Site delivery and field inspection

The geotextile roll is covered with an outer wrapping. It is important that the roll is protected during shipping and storage, and that there is no prolonged exposure at the time of installation on site. During placement, rolls should not be dragged, and construction equipment should not operate directly on the surface of the geotextile, as this may result in material damage. Placement procedures should be reviewed, including provisions for ground clearing and grading, subgrade preparation, overlaps or seams between rolls, cover soils and construction equipment.

6.6.2 Placement of the geotextile

A check should be made to ensure that the direction in which the roll is deployed is consistent with that specified for installation and to confirm that the method of placement on site complies with that approved for construction. Filtration compatibility between soil and geotextile relies on an intimate contact between each material, which thereby limits the potential for development of preferential flow and localized erosion. Accordingly, ground protrusions and depressions should be trimmed to yield a smooth and flat surface. Where adjacent rolls overlap, a lap distance of 0.3 to 0.5 m should be provided for, or more if the ground is likely to deform, and about 0.1 m if the overlap is to be sewn. Sewn seams should exhibit strengths that are similar to those of the geotextile itself. Provisions for repair of any damage, including patching or replacement, should be described in the specification document.

6.7 Sources of further information

Additional reading on the use of geotextiles in filtration applications may, for purposes of convenience, be considered in two general categories: firstly, construction guidance that is focused on basic requirements governing routine design practice and, secondly, a series of specialist conference proceedings on applied research to improve upon knowledge of filtration compatibility and on case study reports of performance monitoring in construction projects.

Routine design issues have been addressed in several documents, of which two deserve specific mention. The US Federal Highway Administration (Christopher and Holtz, 1985) first published a comprehensive review of filtration principles with reference to supporting research studies. The Geotechnical Engineering Office of Hong Kong (1993) subsequently prepared a review of principles and practices related to the design of filters for use in earthworks, with additional commentary on construction methods: Part III of this publication addresses geotextile filters, with reference to types of geotextile, durability issues, hydraulic properties, long-term behaviour, a review of design criteria and specific guidance

for the soils of Hong Kong. It provides a very useful contribution to design practice.

A series of international conferences has been organized on the use of geofilters, with specific emphasis on applications of filters and drainage in geotechnical and geoenvironmental engineering. It commenced with Geofilters '92 (Karlsruhe, Germany) and continued with Geofilters '96 (Montreal, Canada), Geofilters 2000 (Warsaw, Poland) and Geofilters '04 (Stellenbosch, South Africa). The intent of the conference series is to disseminate the findings of advanced studies on both granular and geotextile filters, thereby defining the state of the art in analysis and design. The technical sessions address topics that include theoretical developments, laboratory testing, design criteria, long-term behaviour, waste disposal, landfill drainage, and hydraulic structures. The conference proceedings contain special or keynote lectures on a comparison of granular and geotextiles (Giroud, 1996), analytical modeling and experimental verification of filter behaviour (Indraratna and Locke, 2000), design criteria (Mylmarek, 2000), and filtering and drainage of contaminated water (Rowe and VanGulck, 2004).

6.8 Future trends

At the time of writing, it is reasonable to conclude that the behaviour of geotextile filters in earthworks subject to unidirectional flow of groundwater seepage through soils is reasonably well understood and, consequently, the companion design criteria may be used with confidence. The confidence is predicated on a thorough understanding of the physical processes that govern compatibility. The design criteria are wholly empirical and, importantly, assume that the soils are internally stable.

In contrast, there is limited experience with soils that may be problematic, such as internally unstable gradations (including gap-graded soils). Internal instability refers to a potential for seepage-induced migration of the finer fraction of a soil gradation, where the grain size distribution curve exceeds a limiting geometric constraint and the seepage flow exceeds a limiting hydromechanical constraint. It is likely that, with an improved understanding of such problematic soils, the use of geotextile filters will grow to include design recommendations for these soils that can be used with equal confidence.

Likewise, a good understanding is currently emerging of the operating conditions in filters in landfills that are subject to unidirectional seepage of leachate flow. The challenge, in this application, is one of accounting for the elevated temperatures that are present in the filter, which may approach 50–60 °C, and the ongoing chemical and biological processes, which tend to promote the growth of biomass and precipitation of deposits on the surface of the filter medium. These influences also combine to generate a significant amount of suspended soils in the seepage flow, with a commensurate potential for clogging of the filter openings. Although laboratory studies have sought to replicate the behaviour of these

systems, performance monitoring and forensic observations from waste containment facilities suggest that the spatial and temporal variations in seepage flow are often considerable. Accordingly, with the trend toward more reporting of experience gained in the operation of such facilities, it is expected that tentative design recommendations will be refined and used with increasing confidence.

In contrast with unidirectional seepage flow in routine filter applications, where there is a long-standing body of knowledge on use of geotextiles that is based on considerable field experience and many laboratory studies, the issue of bidirectional or reversing flow is one for which our current understanding is very much limited. This may be attributed to several factors, including the nature and occurrence of reversing flow in routine engineering works, and corresponding lack of good documented field experience, coupled with a paucity of laboratory studies that address the specifics of such flow regimes. Yet considerable challenges exist in the confident provision of filters for protection of civil infrastructure in estuarine and coastal environments, where a subtle distinction can be made between slow reversing flow, such as that of tidal environments, and the relatively faster reversing flow that occurs in the presence of wave action. Future trends will probably include a greater emphasis on building upon the existing confidence in use of geotextiles for routine applications of unidirectional flow, in order to develop a similar confidence in seepage applications that include reversals in the direction of flow.

6.9 References

- American Association of State Highway and Transportation Officials (2000), *AASHTO M288-00 Standard Specifications for Transportation Materials and Methods of Sampling and Testing*, American Association of State Highway and Transportation Officials, Washington, DC.
- ASTM International (2005), *D5101-01 Standard Test Method for Measuring the Soil-Geotextile Clogging Potential by the Gradient Ratio*, ASTM International, West Conshohocken, Pennsylvania.
- Bhatia, S. K. and Huang Q. (1995), 'Geotextile filters for internally stable/unstable soils', *Geosynthetics International*, **2**, 537–565.
- Bhatia, S. K., Smith, J. L. and Christopher, B. R. (1996), 'Geotextile characterisation and pore-size distribution: Part III, Comparison of methods and application to design', *Geosynthetics International*, **3**, 301–328.
- Calhoun, C. C. Jr (1972), 'Development of design criteria and acceptance specifications for plastic filter cloths', *Technical Report S-72-7*, US Army Engineer Waterways Experiment Station, Vicksburg, Mississippi, 83 pp.
- Carroll, R. G. (1983), 'Geotextile filter criteria', in *Engineering Fabrics in Transportation Construction, Transportation Research Record 916*, Transportation Research Board, Washington, DC, pp. 46–53.
- Comité Français Géosynthétiques (1986), *Geotextile Manual* (in French), *AFNOR G38017*, Comité Français Géosynthétiques Association Française de Normalisation, Saint-Denis-La-Plaine.

- Christopher, B. R. and Holtz, R. D. (1985), 'Geotextile engineering manual', *Report FHWA-TS-86/203*, US Federal Highway Administration, National Highway Institute, Washington, DC, 917 pp.
- Corbet, S. P. (1993), 'The design and specification of geotextiles and geocomposites for filtration and drainage', in *Geotextile in Filtration and Drainage* (Eds S. Corbet and J. King), Thomas Telford, London, pp. 29–40.
- Fannin, R. J. (2000), *Basic Geosynthetics – a Guide to Best Practices*, BiTech Publishers, Richmond, British Columbia, 86 pp.
- Fannin, R. J. and Pishé, R. (2001), 'Testing and specifications for geotextile filters in cyclic flow applications', in *Proceedings of Geosynthetics Conference 2001*, Portland, Oregon, USA, 12–14 February 2001, pp. 423–435.
- Fauré, Y. (1988), *Approche structurale du comportement filtrant-drainant des geotextiles*, Ph.D. thesis, Université Joseph Fourier, Grenoble, France, 352 pp.
- Fischer, G. R., Christopher, B. R. and Holtz, R. D. (1990), 'Filter criteria based on pore size distribution', in *Proceedings of the 4th International Conference on Geotextiles, Geomembranes and Related Products*, Vol. 1, The Hague, The Netherlands, 1990, A. A. Balkema, Rotterdam, pp. 289–294.
- Geotechnical Engineering Office (1993), 'Review of granular and geotextile filters', *GEO Publication 1/93*, Civil Engineering Department, Hong Kong, 141 pp.
- Giroud, J. P. (1982), 'Filter criteria for geotextiles', in *Proceedings of the 2nd International Conference on Geotextiles*, Vol. 1, Las Vegas, Nevada, USA, 1–6 August, 1982, Industrial Fabrics Association International, St Paul, Minnesota, pp. 103–108.
- Giroud, J. P. (1996), 'Granular filters and geotextile filters', in *Proceedings of Geofilters '96, Proceedings of the 2nd Conference on Filters in Geotechnical and Environmental Engineering* (Eds J. Lafleur and A. L. Rollin), Montreal, Canada, 29–31 May 1996, BiTech Publishers, Richmond, British Columbia, pp. 565–680.
- Heerten, G. (1982), 'Dimensioning the filtration properties of geotextiles considering long-term conditions', in *Proceedings of the 2nd International Conference on Geotextiles*, Vol. 1, Las Vegas, Nevada, USA, 1–6 August, 1982, Industrial Fabrics Association International, St Paul, Minnesota, pp. 115–120.
- Holtz, R. D., Christopher, B. R. and Berg, R. R. (1997), *Geosynthetic Engineering*, BiTech Publishers, Richmond, British Columbia, 452 pp.
- Indraratna, B. N. and Locke, M. (2000), 'Analytical modeling and experimental verification of granular filter behaviour', in *Geofilters 2000, Proceedings of the 3rd International Conference on Filters and Drainage in Geotechnical and Environmental Engineering*, (Eds W. Wolski and J. Mylnarek), Warsaw, Poland, 5–7 June 2000, A. A. Balkema, Rotterdam, pp. 3–26.
- John, N. W. M. (1987), *Geotextiles*, Blackie, Glasgow, 347 pp.
- Lafleur, J. (1999), 'Selection of geotextiles to filter broadly graded cohesionless soils', *Geotextiles and Geomembranes*, **17**(5/6), 299–312.
- Lawson, C. R. (1986), 'Geotextile filter criteria for tropical residual soils', in *Proceedings of the 3rd International Conference on Geotextiles*, Vol. 2, Vienna, Austria, 1986, A. A. Balkema, Rotterdam, pp. 557–562.
- Lawson, C. R. (1987), 'Use of geotextiles for subsurface drainage in South East Asia context', in *Proceedings of the International Symposium on Geosynthetics*, Kyoto, Japan, 1987, pp. 145–165.
- Luettich, S. M., Giroud, J. P. and Bachus, R. C. (1992), 'Geotextile filter design guide', *Geotextiles and Geomembranes*, **11**, 355–370.
- Millar, P. J., Ho, K. W. and Turnbull, H. R. (1980), 'A study of filter fabrics for geotechnical

- applications in New Zealand', *Central Laboratories Report 2-80/5*, Ministry of Works and Development, New Zealand.
- Murray, R. T. and McGown, A. (1992), 'Ground engineering applications of fin drains for highways', *TRL Application Guide 20*, Transport Research Laboratory, Wokingham, Berkshire.
- Mylnarek, J. (1985), 'Designing geotextiles as protective filters', in *Proceedings of the 21st IAHR Congress*, Melbourne, Australia, 1985, International Association of Hydraulic Engineering and Research, Miadna Pty, NSW, Australia, pp.154–158.
- Mylnarek, J. (2000), 'Geodrains and geofilters – retrospective and future trends', in *Geofilters 2000, Proceedings of the 3rd International Conference on Filters and Drainage in Geotechnical and Environmental Engineering* (Eds W. Wolski and J. Mylnarek), Warsaw, Poland, 5–7 June 2000, A. A. Balkema, Rotterdam, pp. 27–47.
- Mylnarek, J., Laflleur, J. and Lewandowski, J. B. (1990), 'Field study on long term geotextile filter performance', in *Proceedings of the 4th International Conference on Geotextiles, Geomembranes and Related Products*, Vol. 1, The Hague, The Netherlands, 1990, A. A. Balkema, Rotterdam, pp. 259–262.
- Ogink, M. J. M. (1975), 'Investigations on the hydraulic characteristics of synthetic fabrics', *Publication 146*, Delft Hydraulics Laboratory, Delft.
- Ontario Ministry of Transportation (1992), 'Guidelines for the design and quality control of geotextiles', *Draft Engineering Material Report*, Engineering Materials Office, Soils and Aggregate Section, Ontario Ministry of Transportation, Downsview, Ontario, 44 pp.
- Palmeria, E. M. and Fannin, R. J. (2002), 'Soil–geotextile compatibility in filtration', in *Proceedings of the 7th International Conference on Geosynthetics*, (Eds P. Delmas and J. P. Gourc), Nice, France, 22–27 September 2002, A. A. Balkema, Rotterdam, pp. 853–870.
- Ragutzki, G. (1973), 'Beitrag zur ermittlung der filterwirksamkeit durch-lassiger kunststoffe', *Jahresbericht der Forschungsstelle für Insel und Küstenschutz*, Band XXV, Nordeney.
- Rankilor, P. R. (1981), *Membranes in Ground Engineering*, Wiley, New York, 377 pp.
- Rollin, A. L., Mylnarek, J. and Bolduc, G. (1990), 'Study of significance of physical and hydraulic properties of geotextiles used as envelopes in subsurface drainage systems', in *Proceedings of the 4th International Conference on Geotextiles, Geomembranes and Related Products*, Vol 1, The Hague, The Netherlands, 1990, A. A. Balkema, Rotterdam, pp. 363.
- Rowe, R. K. and VanGulck, J. F. (2004), 'Filtering and drainage of contaminated water', in *Geofilters 2004, Proceedings of the 4th International Conference on Filters and Drainage in Geotechnical and Environmental Engineering*, (Ed. A. Fourie), Stellenbosch, South Africa, 19–21 October 2004, University of Witswatersrand, Wits, Gauteng, pp. 1–63.
- Schober, W. and Teindl, H. (1979), 'Filter criteria for geotextiles', in *Proceedings of the 7th European Conference on Soil Mechanics and Foundation Engineering*, Vol. 2, Brighton, UK, 123–129, British Geotechnical Society, Thomas Telford, London.
- US Army Corp of Engineers (1977), 'Plastic filter cloth', *Civil Works Construction Guide Specification CW-02215*, US Army Corps of Engineers, Office, Chief of Engineers, Washington, DC.
- Zitscher, F. F. (1974), 'Recommendations for the use of plastics in soil and hydraulic engineering', *Die Bautechnik*, **52**(12), 397–402.

The use of geosynthetics as separators in civil engineering

W. WILMERS
Germany

7.1 Introduction

7.1.1 The separation layer between coarse granular soil and fine-grained soft soil

Separation is filtration under load. In the case of a granular layer over a fine-grained soft soil, the separator must prevent the fine particles of soft soil from entering the gaps between the particles of granular material above it, as well as preventing the larger grains of the granular layer from sinking into the soft soil below. The separator must also permit water to pass through to prevent pore water overpressure in the soft soil, and all this must function under load. The simplest example is shown in Fig. 7.1. The boot and the crushed stones do not penetrate the soft soil, but the water, pressed out under load, rises up.

The physical demands for a separator under an access road are more complex. When vehicles pass along the road, the granular layer is pressed down by the wheels and deformed in accordance with the shape and load of the wheels. This deformation widens the gaps between the granular particles, which permits the finer soil particles to penetrate the granular layer (Fig. 7.2). Successive transits by vehicles increase the amount of fine particles in the granular layer and the coarse aggregates start to sink into the fine soil. Eventually, the granular layer collapses and the road becomes impassable.


The separator must therefore have the following characteristics.

- 1 It must follow the deformation under rolling loads.
- 2 It must have a high elongation, to allow rutting without the layer rupturing.
- 3 It must possess sufficient strength to prevent a local collapse.
- 4 It must be robust enough to withstand mechanical stresses during installation and under traffic.


Separation is distinct from reinforcement as the latter aims to reduce the depth of ruts through tensile strength.



7.1 Non-woven geotextile over soft soil as a separator for crushed stones and a worker's boot.

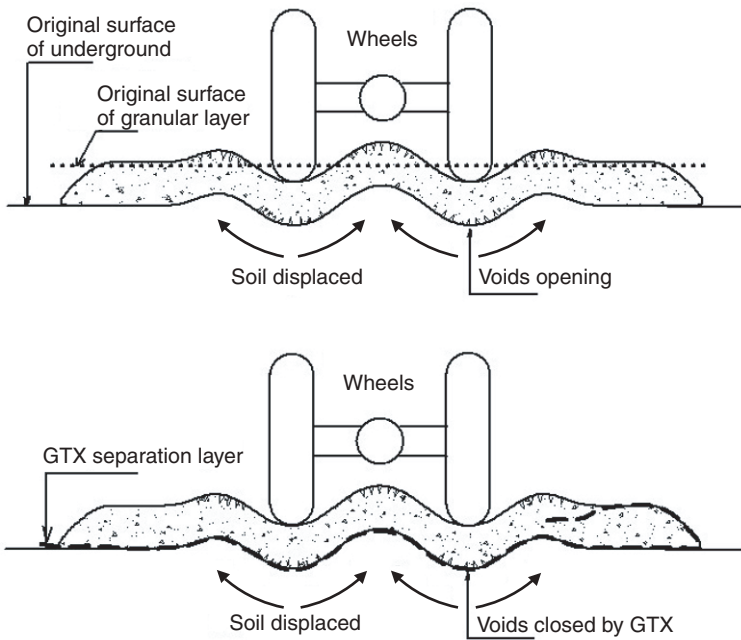

7.2 Granular layer under a wheel load, without and with a separation layer.

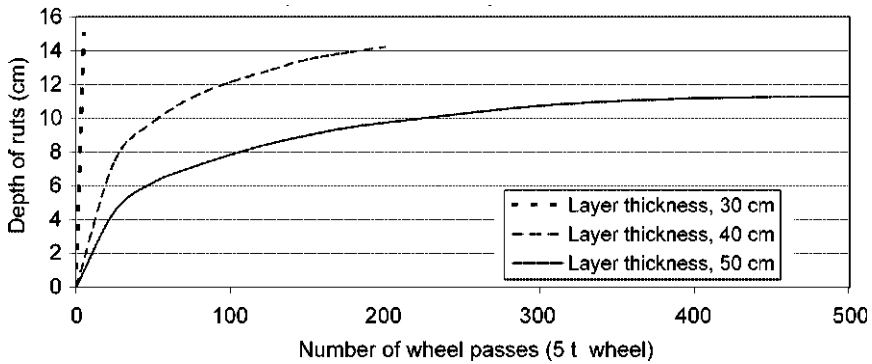

7.3 Development of ruts with a separation layer between the bearing layer and soft soil and with different thicknesses of bearing layer. Where the depth of the ruts (normalized for $I_c = 1$) is plotted against number of wheel passes over layers of crushed stone, 0–56 mm, over silt with $0.5 < I_c < 1.0$ (Brau *et al.*, 1987).


7.1.2 Bearing capacity

The bearing capacity in this situation relates to the number of wheel passes for a ‘layer–separator–soft soil’ system and depends on the thickness and inner friction of the granular layer and the deformability and inner friction of the underlying soft soil. The granular layer should be a well-graded granular material and should be strongly compacted, to obtain high friction between the grains and maximum stiffness. The only function of the separator is to preserve the inner friction of the granular layer, but it also helps to consolidate the underlying soft soil. Under wheel loads, the pores of the fine soil are subjected to pressure and overpressure can build up in the water that they contain. When the water is allowed to rise up through the separator into the granular layer, the fine layer consolidates and this improves the bearing capacity. This explains why separators often limit the development of deep ruts (Fig. 7.3). The first layer over a separation layer must therefore be water permeable and the grains must be resistant against weathering.

However, consolidation takes time and, when the soft soil cannot consolidate, e.g. when the water permeability is too low or when there is not enough time between vehicle passes, then rut development is faster. In this case, a separation layer with high elongation that can adjust to the ruts without rupturing is needed, or the depth of the ruts should be kept to a minimum through reinforcement.

7.1.3 Levelling of surfaces with ruts

Rutting not only deepens the surface of the bearing layer but also compresses the soil layer between and on the sides of the ruts, moving it vertically and horizontally (Fig. 7.2). When the ruts become too deep for vehicles to pass, the surface

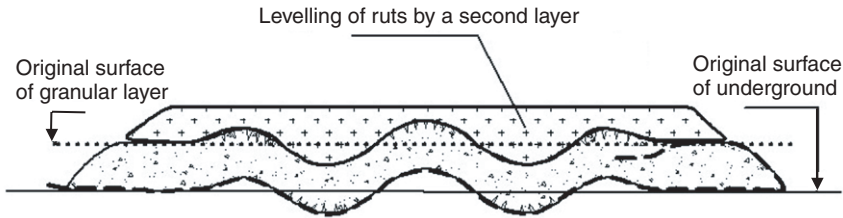

7.4 Levelling of ruts.

must be levelled. This is achieved by filling the ruts and compacting the fill (Fig. 7.4). If the levelling is achieved by grading, the layer is thinner at the higher parts between and beside the ruts and the bearing capacity of the system is partially reduced.

7.2 Applications

7.2.1 Unpaved roads and trafficked areas

Access roads

The main application is as a separation layer in access roads. In most cases, these are temporary roads, used by heavy and very heavy vehicles for a limited period. Usage can vary from heavy to none at all, and the road may be dismantled once it is no longer needed. Therefore it is important to minimize the quantity of material used, and so the thickness of the bearing layer is kept as thin as possible. Deformation is permitted, but not to the level of collapse. Access roads are typically narrow and vehicles use the same path in both directions, so rutting is inevitable (Fig. 7.2). To optimize the thickness of the layer for the given traffic load, site tests are needed because an estimation of the reaction of the subsoil and the influence of the friction characteristics of the fill is not realistically possible. Figure 7.6, shown later, gives an example for sandy gravel with round grains.

When the access road is to be used for only a short time and the materials are to be recovered, geotextiles made from natural fibres are preferable, because they rot in landfills. The separation layer is helpful in restoring the native soil beneath because, after aggregates are recovered, it can be removed together with any residual particles.

The choice of geotextile separation layer should take into consideration the grain size of the fill and the expected depth of ruts, and it must demonstrate the required filter characteristics (see Section 7.3).

Forest and agricultural roads

Forest roads or roads in agricultural areas are typically unpaved. Vehicles of

different sizes and wheel loads use them, but traffic is limited to certain periods and not as frequent as for access roads. Rutting is allowed, but not too much, because otherwise maintenance demands for the road become too high. Under these conditions, consolidation of the subsoil over time occurs more easily and helps to ameliorate the bearing capacity.

The choice of geotextile for this type of separation layer should take into account the grain size of the fill and the expected depth of ruts, as well as the required filter characteristics (see Section 7.3). Geotextiles with high durability should be chosen when the expected lifetime of the road is long; these will generally be those made from synthetic fibres with proven durability.

Work platforms

Work platforms are sometimes used temporarily, like access roads, and sometimes consist of the first layer of an embankment over compressible soils. However, there is an important difference here because work platforms must not deform or yield, especially when they are used for machines with high towers, such as pile boring machines. The separation layer in this case does not improve the bearing capacity of the system, but it does help to hinder deterioration. The strength is provided by the material and thickness of the fill, taking into account the stiffness and deformability of the subsoil.

7.2.2 Paved roads and trafficked areas


Geosynthetics in road bases

The permitted elastic deformation for subgrades under road bases and superstructures is less than 0.5 mm. If the soil is not strong enough, geosynthetics cannot guarantee a sufficient strength, because geosynthetics require deformation in their plane to develop a reaction force. The vertical deformation of a rut, necessary for an elongation of only 1.0% in a textile on the base of a layer of 300 mm thickness, is more than 50 mm for a wheel rut of 300 mm width (Fig. 7.5).


Separation layers cannot therefore improve the strength of a subgrade, but they are very helpful under a granular layer used to improve the bearing capacity of the subgrade (by excavating soft soil and installing granular soil of higher bearing capacity), because they guarantee that the granular material keeps its properties even when disturbed by construction traffic. The bearing capacity is given by the thickness of the bearing layer. Fig. 7.6 shows the effect of layer thickness for sandy gravel over soft soil with different strengths (see also Fig. 7.3).

Textiles under cement concrete pavements

Concrete pavements are often laid on a bound base. This can be a coarse base of

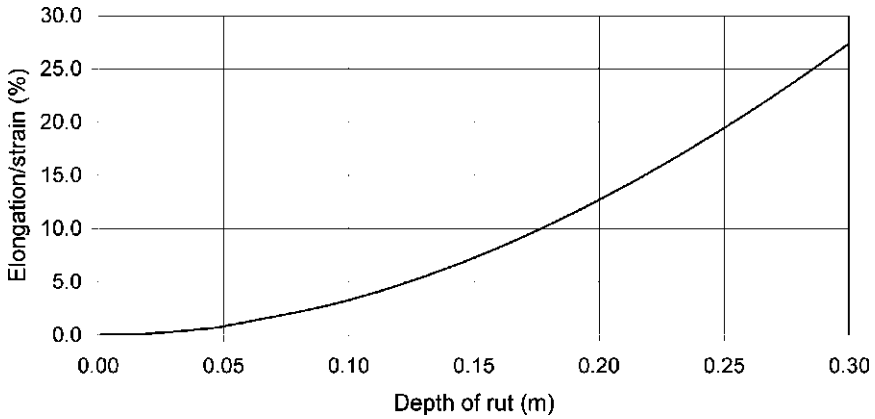

7.5 Depth of ruts and elongation of fabric under a layer of 300 mm thickness for ruts of size 300 mm.

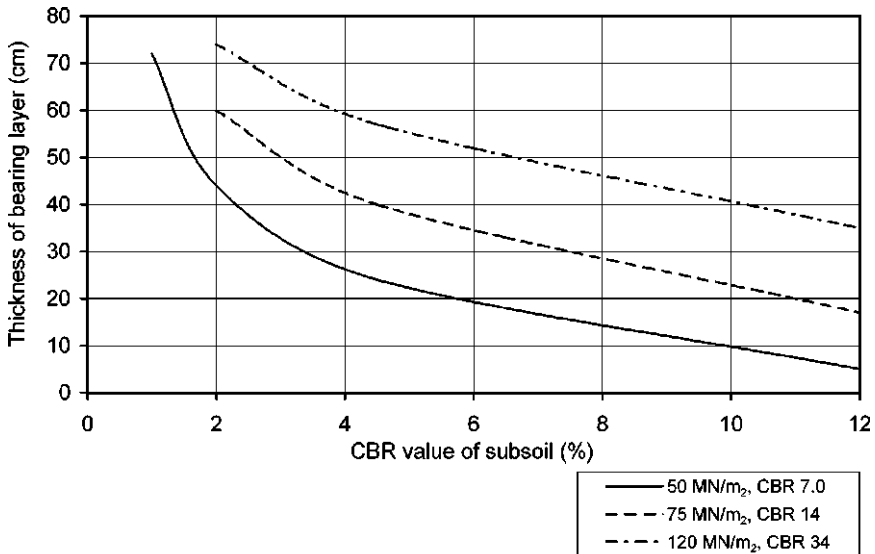

7.6 Thickness of a layer of sandy gravel over soft soil to reach a stiffness E_{v2} (MN/m^2), measured by a static plate bearing test, in relation to the stiffness of subsoil measured as the CBR value (Voss, 1961).

cement concrete or of asphalt concrete. Water can enter into the horizontal crack between the base and the pavement from the side or through joints. The impact of wheel loads squeezes the water aside and the thin water layer can reach very high velocities, sufficient to corrode the upper surface of the bound base, and in some cases also the lower surface of the pavement. This corrosion begins near the

transverse joints, because under the arris the vertical movement is higher than in the middle, and also when there are dowels. After partial corrosion of the bedding, the concrete pavement can rise and break; therefore nowadays, in Germany, non-woven textiles are usually placed under new concrete pavements.

The functions of the textile layer are as follows (Sulten and Wilmers, 2000).

- 1 *Separation.* The fabric creates a clear division by separating the concrete pavement from the base; secondary bending strains are avoided and internal strains are reduced.
- 2 *Drainage.* Water is discharged to the sides.
- 3 *Bedding.* The fabric creates even bearing conditions for the concrete surface and functions similarly to elastic bedding; dynamic traffic loads are cushioned and absorbed.

German regulations for concrete pavements include the following requirements, according to ZTV Beton-StB (Forschungsgesellschaft für Strassen- und Verkehrswesen, 2001).

- 1 Non-woven textile, alkali resistant (polypropylene or polyethylene).
- 2 Thickness d , measured under 20 kPa load: $d > 2$ mm.
- 3 Mass ma per unit area: $450 \text{ g/m}^2 < ma < 550 \text{ g/m}^2$.
- 4 Tensile strength T_f in the machine direction and cross machine direction: $T_f > 10 \text{ kN/m}$.
- 5 Elongation ε_t at tensile strength in the machine direction and cross machine direction: $\varepsilon_t < 130\%$.
- 6 Water permeability k_H in the plane under 20 kPa load and hydraulic gradient $i = 1$: $k_H > 5 \times 10^{-4} \text{ m/s}$.
- 7 Water permeability k_V vertical to the plane under 20 kPa load and hydraulic gradient $i = 1$: $k_V > 1 \times 10^{-4} \text{ m/s}$.

Asphalt interlayers

Asphalt interlayers are mostly used in the rehabilitation of roads and pavements subjected to thermal fatigue and reflective cracking, and to reduce the amount of cracking in a new pavement or an asphalt overlay according to prEN 15382 (European Committee for Standardization, 2005). They can have different functions.

- 1 *Stress relief.* Separation between a structure which is jointed or fissured (concrete pavement, cement bound base, old fissured asphalt) and a new asphalt pavement.
- 2 *Barrier.* Waterproofing of a fissured layer over a water- or a frost-susceptible base, to be covered by asphalt.
- 3 *Reinforcement.* Reinforcement of the new asphalt layer over a jointed or fissured structure.

Table 7.1 Asphalt interlayers: function-related characteristics and test methods to be used as condition for CE marking (extract from EN 15382, Table 1)

Characteristic	Test method	Function ^a		
		Reinforcement	Stress relief	Barrier
Tensile strength ^b	EN ISO 10319	H	H	H
Elongation at maximum load	EN ISO 10319	H	H	H
Dynamic perforation resistance ^c	EN 918	H	–	H
Static puncture (CBR) ^c	EN ISO 12236	H	H	H
Resistance to weathering	EN 12224	S	S	S
Bitumen retention	EN 15382, Annex C	–	H	A
Melting point	EN ISO 3146	S	S	S
Alkaline resistance	EN 14030	S	S	S

^aH, required by the mandate; A, relevant for all conditions of use

S: relevant for some conditions of use.

^bThe wide-width tensile test may not be suitable for specific purposes such as durability assessment or behaviour under cyclic loading. In these cases, more appropriate methods such as EN ISO 13934-1 or ASTM D 6337-01 shall be used.

^cIt should be considered that this test may not be applicable for some types of product, e.g. geogrids. If tensile strength and static puncture are coded H, the producer shall give data for both.

There are different types of product for these tasks, e.g. non-woven geosynthetics, grids and combinations of grids with non-woven geosynthetics. prEN 15382 defines functions and function-related characteristics (see Table 7.1). The fabrics are placed on the surface to be covered and pasted with bitumen enriched with polymers either spread as hot bitumen or as bitumen emulsion. Hot-mixed asphalt pavement is then placed on top. The heat of the asphalt melts the bitumen, which permeates the layer and thus pastes the interlayer to the asphalt pavement.

Particular problems occur in roads over shrinking soils with very low traffic, e.g. roads in arid or semi-arid environments, or paved agricultural roads. The asphalt overlay may be placed as surface dressing over a non-woven interlayer impregnated with bitumen emulsion.

Parking lots

Parking lots are stressed under low-velocity circulation and by vehicles that rest in the same place for a long period of time. Parking lots mostly have bound pavements (asphalt or cement concrete) or concrete stone set paving. In all cases, the construction must be stiff enough to hinder local deformations under load, which can be followed by settling. The separation layer between subsoil and first fill aids during construction, because it prevents deformation and mixing of the

Table 7.2 Separation layer in railroad construction: requirements for geotextiles as filter- and separation elements under bearing layers: German Rails (from EBA, 2003)

Characteristic	Test method	Requirement
Woven geotextiles: tensile strength	EN ISO 10319	> 45 kN/m
Non-woven geotextiles: static puncture	EN ISO 12236	> 2.5 kN
Water permeability normal to the plane	E-DIN 60500-4	$k_v > 1 \times 10^{-3}$ m/s
Characteristic opening size	EN ISO 12956	Related to design
Weather resistance	EN 13249	CE document
Durability	EN 13249	CE document
Compatibility to environment	M Geok E-StB 05	List of parameters

underlying soil. The bearing capacity is not influenced by the separation layer but only by the bearing capacity of the subsoil and the properties and thickness of the fill.

Stone-set paving

In some constructions, a geotextile separates a sandy bed of concrete stones from an open-graded gravel layer below, or a water-permeable bound layer with large pores. This is to stabilize the bedding of stone set paving.

7.2.3 Railroads

A separation layer between ballast and the underlying soil can be very efficient because, under a dynamic load, the coarse grains can be pressed or vibrated into the ground, making maintenance necessary. The very high erosion of coarse sharp-edged grains under the dynamic loads of railway circulation destroys even very thick geotextiles in a short time. Therefore, in railroad tracks with frequent circulation, it is better to install a layer of, for example, sandy gravel under the ballast. This layer is filter stable against the ballast under load and is known as the 'protection layer'. A geotextile separation layer should be placed between the fine-grained soil and the gravel. German Rail has developed special requirements for this purpose (Table 7.2).

7.3 Requirements for geotextiles

7.3.1 Values required by EN 13249 ff

EN 13249 ff (European Committee for Standardization, 2000) defines a list of characteristics of geotextiles that describe the properties necessary for use as a separation layer in road construction and in other construction fields (Table 7.3). This table is identical with that in EN 13250 concerning railroad construction.

Table 7.3 Separation layers: function-related characteristics and test methods to be used as condition for CE marking (extract from EN 13249, Table 1)

Characteristic	Test method	Function, separation ^a
Tensile strength ^b	EN ISO 10319	H
Elongation at maximum load	EN ISO 10319	A
Tensile strength of seams and joints	EN ISO 10321	S
Static puncture (CBR) ^{b,c}	EN ISO 12236	H
Dynamic perforation resistance ^c	EN 918	A
Friction characteristics	EN ISO 12957-1/-2	S
Damage during installation	EN ISO 10722-1	A
Characteristic opening size	EN ISO 12956	A
Water permeability normal to the plane	EN ISO 11058	A
Durability	EN 13249 Annex B	H
Resistance to chemical ageing degradation	EN ISO 12960, EN ISO 13438, EN 12447	S
Resistance to microbiological	EN 12225	S
Resistance to weathering	EN 12224	A

^aH, required by the mandate; A, relevant for all conditions of use; S, relevant for some conditions of use.

^bThe mechanical properties of tensile strength and static puncture are coded H in this table; this requires the producer to provide data for both. The use of only one, either tensile strength or static puncture, is sufficient in the specification.

^cIt should be considered that this test may not be applicable for some types of product, e.g. geogrids.

There, the values with an H are harmonized, which means that they are obligatory for the CE label. For values labelled A, the CEN Technical Committee 189, which has developed the standard, states that these values must be given for all cases of use, and an S means that the values are necessary for some cases of use. However, only the values labelled H are given in the CE documentation; so the user must request the others from the producer.

7.3.2 Requirements for asphalt interlayers (prEN 15382)

prEN 15382 (European Committee for Standardization, 2005) defines a list of characteristics to describe the ability of textiles for a given purpose (see Table 7.1). For an explanation of H, A and S see Section 7.3.1.

7.3.3 Requirements for separation layers

Calculation of damaging influences is not realistically possible; therefore, in different countries, individual approaches are developed, on the basis of experiences with particular applications. The following are outlined.

France (AFNOR G 38-063)

According to AFNOR G 38-063 (Association Française de Normalisation, 1993), the subsoil is separated into three classes: soil 1, $c_u > 60$ kPa; soil 2, $20 \text{ kPa} < c_u < 60$ kPa; soil 3, $c_u < 20$ kPa.

The fill is defined by four properties.

- 1 Permeability in two classes: lower or higher $k_f = 1 \times 10^{-5}$ m/s or 100 times the permeability of subsoil.
- 2 Particle shape in two classes: sharp-edged or round.
- 3 Particle size in two classes: greatest particle size smaller or larger than 250 mm.
- 4 Thickness of first layer in two classes: middle, 0.30–0.50 m; thick, 0.50–1.00 m.

Geotextiles are characterized by the following properties.

- 1 Tensile strength and tensile strain.
- 2 Tear resistance.
- 3 Water permeability vertical to plane.
- 4 Water permeability in plane.
- 5 Opening size.

In a screen for different fill conditions, the required properties of geotextile separators are defined.

Germany

For separators in road construction, according to M Geok E-StB 05 (Forschungsgesellschaft für Strassen- und Verkehrswesen, 2005a) and TL Geok E-StB 05 (Forschungsgesellschaft für Strassen- und Verkehrswesen, 2005b) the fill is characterized by the following.

- 1 Angularity: sharp-edged or round
- 2 Particle size and grading in four classes
- 3 Stress during installation and use in five classes, defined by depth of ruts.

In a screen, these factors are combined to give five classes of requirements for the geotextiles. Corresponding to this the robustness of geotextiles is characterized in five classes depending on strength and mass per unit area. The strength of non-woven geotextiles is measured by the static puncture test CBR (EN ISO 12236), of woven geotextiles by the tensile test.

The hydraulic properties are as follows.

- 1 Permeability: $k_v > 1 \times 10^{-4}$ m/s and $k_v > k_{f \text{ soil}}$
- 2 Opening size O_{90} : for non-woven geotextiles, $0.06 \text{ mm} < O_{90} < 0.20 \text{ mm}$ and, for woven geotextiles, $0.06 \text{ mm} < O_{90} < 0.40 \text{ mm}$.

For separators between protection layers and fine-grained soils in railtracks,

German Rail has developed special requirements (Eisenbahn-Bundesamt, 2003) (see Table 7.2).

Scandinavian countries (NorGeoSpec, 2002)

According to NorGeoSpec, 2002 (Stiftelsen for Industriell og Teknisk Forskning, 2002), five specification profiles are based on the following.

- 1 Subsoil conditions (two classes), defined by shear strength c_u .
- 2 Construction conditions (two classes), based on construction traffic, angularity of fill material, particle or stone size and layer thickness.
- 3 Traffic in use (two classes), vehicles per day.
- 4 Maximum grain size and grading (four classes).

For five specification profiles, requirements for characteristics of geotextiles are given for the following.

- 1 Tensile strength and strain.
- 2 Cone drop diameter.
- 3 Energy index (product of maximum tensile strength multiplied by strain at maximum strength, divided by two).
- 4 Water flow velocity index.
- 5 Characteristic opening size O_{90} (0.15 mm or 0.20 mm).
- 6 Allowable tolerances for mass per unit area and static puncture strength (CBR).

Switzerland (SN 640 552a)

According to SN 640 552a (Vereinigung Schweizer Strassenfachleute, 1997), the fill is characterized by angularity and particle size, and particle grading in three classes. The bearing capacity of subsoil is separated into five classes by CBR value or plate-bearing test, and the traffic load into two classes by the addition of axel loads over the period of use. For three layer thicknesses of bearing layers, the requirements for geotextiles are defined according to tensile force and elongation.

The hydraulic properties are as follows.

- 1 Permeability: four classes of $k_G > 1 \times 10^{-4}$ m/s to $k_G > 1 \times 10^{-6}$ m/s in relation to the soil.
- 2 Opening size O_w for non-woven geotextiles: four classes, $0.05 \text{ mm} < O_w < 0.20 \text{ mm}$, up to $0.05 \text{ mm} < O_w < 0.50 \text{ mm}$ in relation to the soil.

UK

In road construction, the following requirements are given (Highways Agency, 2001a, 2001b). The tensile load is to be defined by the client. The water permeability at a right angle to its principle plane shall be not less than $10 \text{ l/m}^2 \text{ s}$ under a

constant water head of 100 mm, and the pore openings such that mean opening O_{90} is between 100 and 300 μm .

British Rail (1996) have the following requirements for separation layers. The minimum tensile breaking load shall be 10 kN/m and the CBR puncture resistance greater than 3000 N at a displacement of less than 60 mm. Water permeability shall be not less than 10 l/m² s under a constant water head of 100 mm and the pore openings such that mean opening O_{90} is between 30 and 85 μm .

7.3.4 Durability

For durability, all countries follow EN 13249 ff, Annex B (European Committee for Standardization, 2000).

Weathering resistance

All products are more or less susceptible to weathering. The best protection is by covering with fill. EN 13249, Annex B.1, gives the maximum exposure time after installation based on the results of an accelerated weathering test. According to EN 13249, the producer must define the time of covering in the CE-accompanying document: 'to be covered on the day of installation or to be covered within 2 weeks or within 1 month'.

Resistance against chemical and/or biological damage

The polymers are susceptible to chemical degradation in different ways. EN 13249, Annex B.2 to Annex B.4, defines test procedures for this. Based on these tests, the producer must define in the CE-accompanying document predicted to be durable for a minimum of 25 (or 5) years in natural soils with $4 < \text{pH} < 9$ and soil temperatures $< 25\text{ }^{\circ}\text{C}$. For separation layers, these periods are normally sufficient.

7.4 Requirements for fill material

The fill material must be resistant against weathering for the length of time that it will be used, the grain size distribution must guarantee good water permeability, and the angularity and grain size distribution must provide a good inner friction. When recycled construction material with a higher content of cement concrete or cement mortar is used, then only polymers not susceptible to alkaline degradation (e.g. the polyolefins polypropylene and polyethylene) should be used, unless the fill is required only for a short period and the product is proven to be sufficiently durable.


7.5 Construction

7.5.1 Placing of the separation layer

The product should always be placed evenly and smoothly. There must be sufficient overlapping that the soft soil under pressure beneath cannot erupt through any gaps. The requirements under various national specifications range from an overlap of 30–50 cm. Normally, the web should be placed across the direction of the work because, when unrolled lengthwise there is a high risk that the webs will drift apart when distributing the fill. However, when the overlaps are fixed, e.g. by sewing, glueing or clamping on subsoil with soil nails, the layer can be unrolled lengthwise. Overlapping should be in the direction of the work, like tiles on a roof.

7.5.2 Placing of fill

Driving directly on the fabric is not allowed, because of the vulnerability of the products and the risk that the web will drift apart. The transport vehicles delivering the fill should not drive on the geotextile. The fill should be unloaded where fill has already been put down and then distributed by pushing (Fig. 7.7). Only fill transport vehicles should be allowed to drive on the fill before compaction, because the fill layer does not reach full bearing capacity until after compaction.

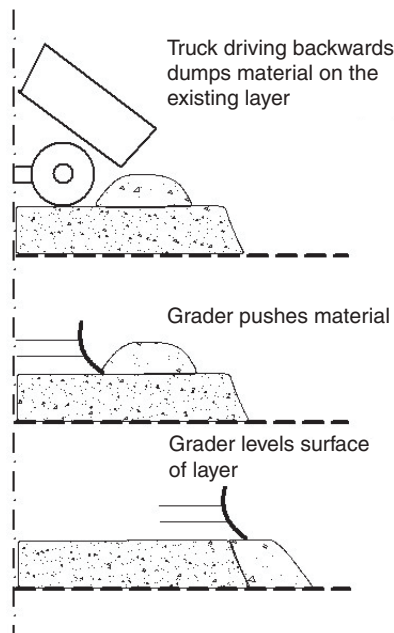

7.7 Placing of the separation layer and of the fill.

7.6 References

- Bräu, G., Laier, H. and Floss, R. (1987), *Wirkungsweise von Geotextilien unter intensiver dynamischer Beanspruchung*, Prüfamts Grundbau Technische Universität, München.
- Sulten, P. and Wilmers, W. (2000), 'Use of geotextiles in concrete pavement construction', in *Proceedings of the 2nd European Geosynthetics Conference*, Vol. 1, Bologna, Italy, 15–18 October 2000, International Geosynthetics Society, Paris, pp. 437–441, Fig.1–Fig. 9.
- Voss, R. (1961), *Lagerungsdichte und Tragwerte von Böden bei Straßenbauten*, Strasse u. Autobahn, H. 4, Kirschbaum, Bad Godesberg.

7.7 Regulations

- Association Française de Normalisation (1993), AFNOR G 38-063 Articles à Usages Industriels: Recommandations pour l'Emploi des Geotextiles et Produits Apparentés – Utilisation des Géotextiles et Produit Apparentés sous Remblais sur Sols Compressibles, Association Française de Normalisation, Paris.
- British Rail (1996), *Railtrack Line – Specifications – Geotextiles*, British Rail, London.
- Eisenbahn-Bundesamt (2003), *EBA 2003 Prüfungsbedingungen für Geokunststoffe in Zulassungsverfahren des Eisenbahnbundesamtes*, Eisenbahn-Bundesamt, Bonn.
- European Committee for Standardization (2000), EN 13249, *Geotextiles and Geotextile-related Products – Characteristics Required for Use in the Construction of Roads and other Trafficked Areas (excluding Railways and Asphalt Inclusions)* European Committee for Standardization, Brussels.
- European Committee for Standardization (2005), prEN 15382 *Geotextiles and Geotextile-related Products – Requirements for Use in Pavements and Asphalt Overlays*, European Committee for Standardization, Brussels, CEN.
- Forschungsgesellschaft für Strassen- und Verkehrswesen (2001), *ZTV Beton-StB 01 Zusätzliche Technische Vertragsbedingungen und Richtlinien für den Bau von Fahrbahndecken aus Beton*, Forschungsgesellschaft für Strassen- und Verkehrswesen, Köln.
- Forschungsgesellschaft für Strassen- und Verkehrswesen (2005a), *M Geok E-StB 05 Merkblatt über die Anwendung von Geokunststoffen im Erdbau des Straßenbaues*, Forschungsgesellschaft für Strassen- und Verkehrswesen, Köln.
- Forschungsgesellschaft für Strassen- und Verkehrswesen (2005b), *TL Geok E-StB 05 Technische Lieferbedingungen für Geokunststoffe im Erdbau des Straßenbaues*, Forschungsgesellschaft für Strassen- und Verkehrswesen, Köln.
- Highways Agency (2001a), *Manual of Contract Documents for Highway Works*, Vol. 1, *Specification for Highway Works* (amendment 2005), HMSO, London.
- Highways Agency (2001b), *Manual of Contract Documents for Highway Works*, Vol. 2, *Notes for Guidance on the Specification for Highway Works* (amendment 2004), HMSO, London.
- Stiftelsen for Industriell og Teknisk Forskning, (2002), *NorGeoSpec 2002 A Nordic System of Specification and Control of Geotextiles in Roads and Other Trafficked Areas*, Stiftelsen for Industriell og Teknisk Forskning, Trondheim.
- Vereinigung Schweizer Strassenfachleute (1997), SN 640 552a *Geotextiles, Exigences pour les Fonctions de Séparation, de Filtration et de Drainage*, Vereinigung Schweizer Strassenfachleute, Zürich.

T. MEGGYES

Bundesanstalt für Materialforschung und -prüfung, Germany

Before the passage of environmental regulations, wastes were dumped indiscriminately in open areas with no care for the environment. Many countries have developed stringent regulations on waste disposal and landfills in the last few decades. Today, landfills are engineered structures that are aimed at containing the wastes effectively. Upon stabilization of municipal solid waste, the landfill sites may be used for a beneficial purpose such as golf course, recreational park, industrial park and other such uses.

Stief (1986) proposed the concept of a multibarrier system for landfills based on the following.

- 1 The subsoil (the geological barrier).
- 2 A basal liner and capping (the technical barrier).
- 3 The waste body itself.
- 4 The control of landfill performance.
- 5 Aftercare or post-closure plan.

The most important element for containment is the technical barrier, the standard for which is a composite liner throughout most of Germany. Landfill technology has evolved with well-defined design and construction procedures. This chapter presents the salient features of landfill technology: waste separation and pretreatment, landfill concepts, standard composite and alternative liner systems, design considerations for earthen and geomembrane liners, safety analysis of liners, leachate drainage systems, and gas generation and management. Finally, cut-off walls for the control of pollution at the landfill sites are briefly described.

8.1 Waste separation and pretreatment

The waste body is affected by waste collection. A separate collection is more favourable than an assortment of non-separated collected waste. Even more important is the pretreatment of waste which can serve several goals. It is advantageous if processes that convert the waste into a less reactive form proceed before landfilling. In an ideal situation, the aim is to obtain inert materials. Pretreatment reduces the amount of waste which is particularly beneficial because

landfill capacity is becoming increasingly scarce. Pretreated waste can often be used for new purposes, such as energy generation, or it can be recycled.

There are thermal, biological, chemical and physical pretreatment procedures; thermal pretreatment is quantitatively the most important. TI Municipal Waste (1993) requires municipal waste to be deposited with a maximum of 5% of organic components. To adhere to this limiting value, incineration is often the only possibility. The heat generated by incineration can be used for energy generation. The solid residues, namely slag and ash, may provide raw materials for building purposes.

Biological pretreatment can be aerobic (composting) or anaerobic (fermentation). Biological pretreatment exhibits great potential for waste reduction. The biological–mechanical pretreatment aims at the degradation of organic pollutants, a reduction in the quantity and better compactibility.

Landfill mining is a method of treating old landfills. After eliminating emission sources, the waste body is excavated, the remaining waste compacted and useful materials are separated and recycled. As a result, landfill void space is increased, pollution potential reduced and financial gains are achieved by material utilisation (Spillmann *et al.*, 2007).

8.2 Landfill concepts

Landfill classes are defined by the type and concentration of pollutants in the waste and, accordingly, different design standards are required. In Germany, the standards for hazardous waste are defined by TI Hazardous Waste (1991) and those for municipal waste by TI Municipal Waste (1993). These two documents set the limits for various waste strength parameters and for some 20 pollutants in the leachate. The landfill classes thus defined (characterized by for example the permitted nickel content in the leachate) are as follows in order of increasing potential risk.

Municipal solid-waste landfills.

Class I. Virtually inert waste, e.g. Ni content < 0.2 mg/l.

Class II. Waste with higher pollutant contents, e.g. Ni content < 1 mg/l.

Hazardous solid-waste landfills, e.g. Ni content < 2 mg/l.

If the waste fails to meet the requirements for hazardous solid-waste landfills, it must be incinerated or disposed of underground.

Landfills may also be classified based on the waste composition and operations as inert material landfill, containment landfill, reactor landfill and co-disposal landfills.

8.2.1 Inert material landfill

In an ideal case, the inert material landfill contains only wastes that are neutral concerning emission and do not change the natural background concentration.

8.2.2 Containment and reactor landfills

Landfill strategy can be of the 'containment' type and 'reactor' type. Containment means an isolation from environmental effects and, in particular, water. For this purpose, the waste body is generally provided with liners. The capping protects the waste body from precipitation, while the basal liner aids the collection of leachate which is then transported to treatment.

In contrast, the reactor landfill encourages the processes which, in an ideal case, produce an inert content, which is stable under environmental conditions and releases no pollutants to the environment. One will be able to reach such a state only in exceptional cases.

When landfilling untreated municipal waste, a certain quantity of water has to be added to enable biological degradation processes. Otherwise the organic components may become 'mummified'. When water is added, mummification can be interrupted or replaced by biological degradation processes. In old deposits, the biochemical processes may be interrupted if a (subsequent) containment obstructs the access of water. A leaky capping may entail an uncontrolled inflow of water and uncontrolled reactions. In such cases it may be reasonable to feed water purposefully into old dry deposits to accelerate the biochemical reactions to bring them to completion within the operational time of the landfill.

The biological processes go through an aerobic and an anaerobic phase. In these phases both gas develops, e.g. methane, and organic pollutants accumulate in the leachate. At the end of the processes, the landfill content is mineralized. The landfill operator is interested in encouraging the biological degradation so that it is finished within the active aftercare phase which is 50–100 years. If the waste body has reached the mineralized state, it still contains inorganic pollutants, e.g. heavy metals of which only a limited amount is supposed to be released.

For all these reasons 'containment' and 'reactor landfill' are not necessarily contradictory strategies since the bioreactor needs a liner to protect the environment and a capping and irrigation system to control the inflow of water and to minimize leachate production the treatment of which is very cost intensive. However, in bioreactor landfills, the question of repercussion of elevated temperatures on performance of technical barriers has to be considered carefully.

8.2.3 Co-disposal landfill

The UK Department of the Environment (1990) define co-disposal as a calculable and supervised treatment of industrial and commercial liquid and solid wastes in interaction with biologically degradable wastes in a controlled landfill (Campbell, 1994). If co-disposal is to have advantages, the basic materials must be exactly defined and mixed with one another in a controlled way. The mixing process must produce as homogeneous a product as possible.

Sewage sludge and industrial sludges often contain so much water that they are

not stable. The addition of municipal waste can yield a consistency which makes landfilling possible. Mixing harbour mud with clay, lime or cement may produce a stable material that can be landfilled. Mono landfills should be used to avoid inhibition of biological processes in municipal wastes by industrial pollutants. Co-disposal is outlawed in many countries today (Spillmann *et al.*, 2007).

8.3 Landfill phases

Landfill phases are important to distinguish for landfill construction and operation:

Phase 0 Basal liner construction.

Phase I Before filling wastes: the basal liner is fully or partially exposed.

Phase II Period of waste filling: this phase ends with the construction of the capping and the reclamation layer.

Phase IIIa Aftercare, part 1: it lasts 50–100 years. No more construction measures take place. Drainage and monitoring facilities are operated and maintained.


Phase IIIb Aftercare, part 2: unlimited in time, ageing of components of the liner systems occurs, impairing their effectiveness.

8.4 Landfill liners


Generally, landfills must be provided with a composite basal liner and a capping, both of which are composed of sealing, protective and drainage layers, although alternative liners with proven barrier equivalence can be used (August *et al.*, 1997; Müller, 2001). The capping system's main function is to prevent gaseous pollutant emission into the atmosphere and rainwater from percolating into the landfill so as to keep leachate generation to a minimum, while basal liners must protect the surrounding soil and groundwater from leachate pollution. Both the sealing layers are overlain by a drainage system which in the basal liner collects leachate and transports it to a treatment plant to be cleaned of pollutants and subsequently discharged in the nearby surface water. A capping drainage layer collects rainwater which requires no processing before being released.

8.4.1 Composite liners

Figure 8.1 illustrates the basal liner and capping systems for Class II of municipal waste according to TI Municipal Waste (1993). The most important element of these systems is the composite liner consisting of several lifts of earthen (mineral) material with a minimum thickness of 0.25 m of each lift and a minimum certified geomembrane 2.5 mm thick. The geomembrane is installed on top of the earthen layer in intimate contact with it and is protected by a protective layer against damage by gravel or aggregates in the drainage layer (Müller, 2001, 2006).

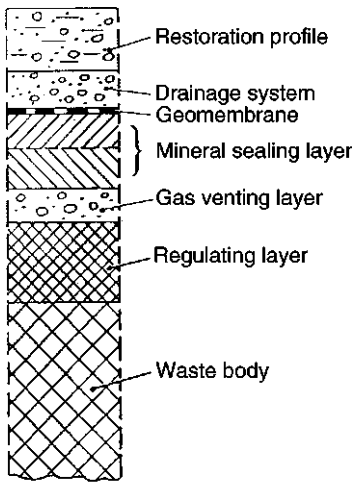

Capping system

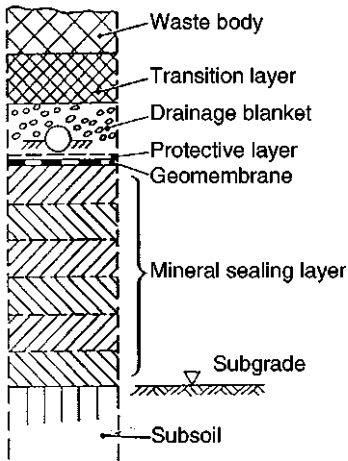

Composite basal lining system

8.1 Liner and capping system for Class II landfills.

Liners for Class I municipal solid-waste landfills differ inasmuch as no geomembrane is required and the minimum total thickness of the earthen layer is only 0.5 m while basal liners in hazardous waste landfills are similar to those for Class II, except that the earthen layer must be a minimum 1.5 m thick. The permeability of the earthen layer of basal liners for all classes and in the capping system of hazardous solid waste landfills must be $k < 5 \times 10^{-10}$ m/s, and for Class II capping systems $k < 5 \times 10^{-9}$ m/s.

Composite liners are required according to TI Hazardous Waste (1991) and TI Municipal Waste (1993). One of their most important properties is the synergistic effect whereby the combined effect of the earthen layer (also called mineral or clay layer) and geomembrane is greater than the sum of the effects of the individual components. The properly installed and welded geomembrane is an effective barrier against convection: pollutants can only permeate it by diffusion, the rate of diffusion for various chemicals varying widely. For heavy-metal ions and other inorganic materials, the geomembrane is virtually a perfect barrier, although water can diffuse through it to some small extent. Hydrocarbons and chlorohydrocarbons can slightly penetrate geomembranes and diffuse through them, however they will then sorb within the earthen layer. Any further transport is only then possible by diffusion. Based on conservative assumptions on organic pollutant concentrations at the landfill base, breakthrough times of 16–18 years were obtained, indicating that the first pollutant molecule only reaches the lower surface of the earthen layer after this period of time, assuming a steady ‘supply’ of pollutants.

The long-term durability of geomembranes cannot be quantified exactly since it strongly depends on the quality of the individual product chosen. The minimum period of time of full efficacy is often given as 50 years; however, geomembranes of well-stabilized and highly stress-crack-resistant high-density polyethylene (HDPE) resins are likely to remain intact for several hundred years. Most importantly, geomembranes exhibit their full protective function in the active aftercare period when pollutant concentrations in the leachate are highest. Earthen sealing layers are generally assumed to maintain their efficacy as basal liners over geological periods of time even under chemical attack. However, they are likely to fail as capping liners in the long run. Since earthen materials are never absolutely watertight, small amounts of pollutants will permeate over longer periods of time.

The construction of the composite liners to meet the prescribed strict standards, in particular ensuring high-quality intimate contact between the geomembrane and earthen layer, represents a great challenge to construction companies. In order to solve this complex problem, general quality management systems closely defining building procedures are required.

8.4.2 Alternative liners

Instead of composite liners, alternative liners can be used if they can prove to be equally effective as composite barriers. Some of the alternative liners currently in use are as follows.

Mineral liners

The statutory requirement for not less than 20% of fines (less than 2 μm) and not less than 10% of clay minerals in the earthen layer is very often difficult to meet; therefore, equivalent earthen materials of different compositions are also used.

Well-graded materials have grain size characteristics approximating Fuller's curve, i.e. there is a stable structure and only a small fines content is required to achieve low permeability. This type of liner exhibits less shrinkage on losing water, but they are not as flexible as earthen materials with a high clay content and this can be a disadvantage in the event of differential settlement. DYWIDAG dry liners consist of 8% bentonite and two well-graded sand and gravel fractions. They yield an extremely high dry density and, on the addition of water, they tend to swell (volume increase), thus cracks in the liner will not be expected.

Multiple liner with a sorption layer

A multiple liner is composed of two layers with principally different functions: one of these serves as containment, i.e. to prevent pollutants from leaving the landfill, and the other's function is to minimize the consequences of pollution, should containment measures fail.

Improved mineral liners

Silica glass, quaternary ammonium compounds, montan wax and other additives can provide high levels of imperviousness even in the absence of the clay fraction in the earthen material and flexibility can even be greater than that of pure mineral mixtures. Silica glass combined with silanes has been used successfully to improve cut-off materials. Silicone-carbon bonds in organosilane hydrogel modifiers are extremely resistant to biochemical degradation. Recently polymer-amended sand-bentonite mixtures have proven to be an alternative to compacted clay liners in capping systems.

Asphalt liners

Asphalt is composed of a well-graded grain skeleton, a filler (rock flour) and a bitumen. Based on experience in hydraulic engineering, liner systems incorporating asphalt are increasingly being used; in Switzerland, more than 20 landfills have been constructed with asphalt liners. In Germany, a combination of a mineral layer directly overlain by an asphalt liner is preferred. Short-term tests have shown asphalt liners to be a good barrier to the convective transport of aqueous solutions, while their stability and resistance to heat, weather and penetration are advantageous features. A liner made of asphalt concrete in accordance with the requirements is almost impermeable to water and gas. It is very robust against mechanical stresses and desiccation is irrelevant. However, it is susceptible to chemical attack by hydrocarbons and concentrated hydrocarbons can virtually destroy it.

Geosynthetic clay liners

Geosynthetic clay liners are also known as bentomats, and they generally consist

of bentonite sandwiched between two geotextile layers which are needled or sewn together to provide shear strength. Water-saturated bentonite exhibits extremely low permeability and, in principle, a bentomat with a few millimetres thickness is capable of producing the required barrier function. For practical reasons, thicknesses of a few centimetres are used. Bentomats can be manufactured industrially and installed in rolls, similar to laying techniques for geomembranes. They are light, easy and quick to lay, exhibit low susceptibility to settlement and are easy to repair; however, root penetration is a potential risk.

Capillary barriers

Capillary barriers consist of an upper fine-grained capillary layer and a lower coarse-grained capillary block. Capillary menisci are formed at the interface between the upper and lower layer by water percolating into the upper layer. Capillary force on these menisci and a very low unsaturated permeability in the capillary block prevent water from penetrating the coarse-grained layer. Capillary barriers are almost insusceptible to desiccation and subsidence. Both the sand used for the capillary layer and the gravel used for the capillary block must be well graded, their optimum layer thicknesses being 0.4 m and 0.3 m, respectively, and a minimum slope gradient of between 1:10 and 1:5 is advisable. Capillary barriers are most effective when used in combination with a gas-tight sealing layer (e.g. geomembrane or asphalt) and they are most often used on sloping areas of landfill caps.

8.5 Design considerations for earthen liners

8.5.1 Permeability

The imperviousness of an earthen material is characterized by the hydraulic conductivity (or permeability), the k value, defined by

$$v = kI$$

where

v = velocity, i.e. the flow rate per unit cross-sectional area

I = hydraulic gradient

The requirements with regard to imperviousness are much more exacting in landfill construction than in earthworks and hydraulic engineering. No other geotechnical parameter is as difficult to obtain reliably as permeability, as even small variations in water content and density may result in changes in permeability by up to two orders of magnitude. Three types of laboratory apparatus are used for permeability measurements: rigid-wall permeameters, triaxial cells and consolidometer permeameters. However, the latter produces a one-dimensional deformation state which corresponds most closely to that in a landfill basal liner and is therefore

best suited to investigate the influence of a load on permeability. In the field, permeability is measured by infiltration; a hollow cylinder is inserted or pressed into the liner from the surface and filled with water, and then losses due to infiltration measured. Large-area lysimeters are also used to catch all the percolated water. Field tests are considered necessary since it has repeatedly been found that permeability measured in the field is 10–1000 times higher than in the laboratory. Acceptably low permeability values can only be achieved if there are no macropores in the earthen liner, thus the homogeneity of the installed liner is by far its most important parameter.

8.5.2 Mechanical properties

Heavy landfill overburden pressures can result in subsoil subsidence, and the basal liners have to cope with differential subsidence without sustaining any damage, especially at the toe of slopes and on the slopes themselves. Collapses within the waste body and the subsidence of the subsoil are of particular importance for capping and interim liners. Radii of curvature of between 40 and 70 m were found as deformation limits in a large-scale test rig, as indicated by a sudden increase in permeability.

Deformation here is judged by the extent to which it impairs imperviousness and this impairment increases in the following order: homogeneously distributed distortion, limited shear zones or shear joints and, finally, gaping cracks. Unlike cracks, shear joints are capable of transferring compressive and shearing stresses. If the liner material contains a considerable amount of sand and gravel, shear zones form, leading to disturbance which can result in an increase in permeability. For liner materials, strain is a more important factor than stress.

Self-healing is the capacity of a clay material to close up again over time cracks which may be of mechanical or other origin, e.g. desiccation or pollutant influence. The most important factors of self-healing are plasticity, swelling and colmation. Bentonite addition and lateral pressure can increase self-healing capacity. Generally, the low surcharge in landfill caps is not sufficient to suppress cracks.

8.5.3 Moisture and pollutant transport

The moisture balance beneath landfills differs from that in undisturbed soil, as a containment landfill restricts or prevents moisture supply both to earthen layers and to the subsoil, and exothermic processes within the landfill may, over a long period of time, lead to desiccation in the earthen layer of the liner.

The tests carried out have shown that desiccation cracks are not expected to form if suction does not exceed the overburden pressure in absolute terms and this is shown to be in agreement with several theoretical considerations. Whether or not an earthen liner suffers desiccation must be decided for each individual case based on a coupled water transport and soil deformation analysis, analogous to static

calculations for engineering structures. This analysis consists of a description of the geometry, selection of appropriate physical and mathematical models, the determination of stresses, temperature and boundary conditions, evaluation of soil mechanical and transport parameters, calculation of heat and water transport and of soil deformation, assessment of the probability of cracking and, finally, a discussion of preventive measures. The most important aspect of this last point is that the suitability of earthen liners should be judged by virtue of their long-term properties rather than by those on placement. The efficacy of earthen liners is likely to be challenged after a period of 100 years or more, when it is predicted that the drainage system and the geomembrane may fail. Placement water content should not therefore be greater than that at long-term equilibrium. Placing the earthen layer in the form of small clods rather than in a highly homogenized form minimizes tensile stresses, thus preventing gaping cracks, should desiccation occur in the distant future (Holzlöhner, 1997).

8.6 Design considerations for geomembrane liners

A composite liner must be constructed so that the geomembrane (most commonly HDPE) will lie sufficiently flat on the flawless surface of the mineral liner and that subsequent surcharges such as the protective, drainage, waste and recultivation layers produce a complete contact, known as intimate contact, between them. This can only be achieved by means of a construction method which is well coordinated throughout the landfill construction industry. The geomembrane must be smoothed and ballasted after placement to prevent installation failures such as excessive waves and wrinkles, and sagging and damage to the mineral liner. Stability and the friction behaviour between the geomembrane and adjacent layers on slopes is critical and geomembranes with rough or textured surfaces are especially suited to inclined areas by virtue of their high coefficients of friction. To avoid any tensile overload of the geomembrane in basal liners, shear resistance between the geomembrane and protective layer must not exceed that beneath it, i.e. between the earthen layer and the geomembrane (Averesch and Schicketanz, 1998; Müller, 2006).

Load plate experiments into the effectiveness of geotextile and clay–synthetic protective layers showed that temperature, time and surcharge all have a considerable influence on strain in geomembranes. Overlapping and folds in protective layers should be avoided, and drainage gravel must not get beneath the protective layer. Heavier geotextiles and combined earthen–synthetic layers (geocontainers) have been shown to provide more effective protection for geomembranes.

Leaks from landfills can be monitored using grids of electrically conductive material installed directly above and below the geomembrane to measure local electrical resistance, changes in which can be attributed to leaks.

8.7 Drainage systems

The main functions of the drainage system at the base of the landfill are to remove leachate from the waste body and to collect it at defined points and to avoid leachate build-up on top of the basal liner. A basal drainage system consists of three elements.

- 1 Drainage layers (when laid flat these are also known as area filters).
- 2 Drainage pipes.
- 3 Leachate shafts.

The drainage layer should be installed as a blanket of mineral drainage material, specified as round grained with a particle size of 16–32 mm, or where necessary 8–16 mm. The pore volume content of 16–32 mm material is needed to counteract incrustation, i.e. microbiological deposition processes, which can drastically reduce the pore space in the drainage layer and the free cross-section of drainage pipes. Finer materials can become completely impermeable within a year and round grain is required to reduce the pressure from the individual grains on the underlying geomembrane and thus to avoid perforation. Requirements also demand a minimum thickness of 0.3 m and a long-term minimum permeability of 1×10^{-3} m/s, and fine particles must be prevented from being washed out of the waste into the drainage layer.

The clogging effect due to incrustation in drainage blankets and leachate collection pipes increases approximately proportionally to the concentration of organic matter in the leachate. While drainage pipes are quite easy to clean using mechanical methods, the rehabilitation of drainage blankets is somewhat difficult. Redissolving and disinfection measures combined with biological pretreatment of the waste have been suggested, hydrochloric, perethanoic, nitric and perchloric acids being effective redissolving agents, and perethanoic acid and hydrogen peroxide effective disinfectants, killing bacteria which cause incrustation. Biological pretreatment of the waste reduces the organic content of the leachate and, consequently, bacterial activity as well. It also prevents the development of the acidic phase in the landfill, thus calcium, magnesium, manganese and sulphate will be not precipitated from the leachate.

Drainage pipes are arranged herringbone fashion on both sides of a central longitudinal axis. Leachate should run freely off the landfill, the surface of the basal liner being pitched like a roof for this purpose. The lateral slope down to the pipes should be not less than 3% in the long term, and the gradient of the pipes greater than 1%. A lateral spacing between the drainage pipes should not be greater than 30 m. In Germany, the approved materials for landfill drainage pipes are HDPE (the most commonly used), polypropylene and plasticizer-free polyvinyl chloride. The chemical and biological resistance of all three materials is well established. The pipes should have a minimum nominal diameter of 0.25 m and the pipe walls of the upper 240° of the cross-section should be perforated with a

minimum water intake area of 0.01 m² per metre length of pipe. The geometry and manufacturing technology of apertures are important parameters which can influence the pipes' strength and durability under landfill conditions.

Leachate shafts are arranged at the deepest points of the drainage pipe network, preferably on the external slope edge of the landfill, allowing access to the drainage pipes and hence facilitating monitoring or maintenance work.

Geocomposite drains are a cost-effective and technically attractive alternative to mineral drainage layers. However, water flow capacity might be impaired in the long run by creep and degradation processes of the plastic material. Therefore, the long-term water flow capacity has to be carefully assessed by special test methods (long-term creep test and long-term shear strength test).

8.8 Landfill gas generation and management

Landfill gases are the result of microbial decomposition of solid waste. Gases produced include methane, carbon dioxide and lesser amounts of other gases (e.g. hydrogen, volatile organic compounds and hydrogen sulphide). Landfill gas production rates vary spatially within a landfill. Migration of landfill gases occurs owing to concentration gradients and pressure gradients. Generally, landfill gas moves through the path of least resistance. Uncontrolled migration of landfill gas can cause explosion hazards, undesirable odours, physical disruption and damage of caps, and toxic vapour emissions. Regulations require that landfill gas should be monitored to ensure that methane concentration does not exceed 25% of the lower explosion limit. Generally, gas collection systems that include passive and active gas collection are used. At large landfills, the collected gases are used for energy recovery. Thus, landfill gas recovery systems can reduce landfill gas odour and migration, and the danger of explosion and fire, and may be used as a source of revenue that may help to reduce the cost of closure (Sharma and Reddy, 2004).

8.9 Cut-off walls

Cut-off walls are used in order to prevent horizontal pollutant migration from landfills and contaminated sites, the most frequently used walls being slurry trench cut-offs and steel sheet pile walls. In the former case, trenches are excavated supported by fluids capable of solidifying and forming a diaphragm wall (single-phase diaphragm wall) or which are then displaced by another material which, in turn, is capable of solidifying (two-phase diaphragm wall). Cut-off slurries consist of clay (bentonite), cement, water and filler materials (rock flour). Cut-off walls are especially effective if they can be socketed into an impermeable layer. The most common construction principles include excavation of soil and placement of sealing material, displacement of soil, installation of sealing material and reducing permeability of soil in place (injection and freezing) (Holzlöhner *et al.*, 1995).

8.10 Safety analysis of landfill liners

Safety analysis is based on the assessment of the effects of an incident (e.g. leakage), assuming a worst-case scenario. It is aimed at estimating groundwater quality in the wake of leachate escape into the subsoil. The safety of a liner (sealing) system is measured by the extent of leachate containment. A liner (sealing) system is considered safe (suitable) if it provides a sufficiently strong barrier against certain pollutants or their mixtures in leachate over a long period of time. A barrier effect is considered suitable if the liner (sealing) system yields the same leakage behaviour as a standard liner system (e.g. a composite liner according to TI Hazardous Waste, 1991) (Heibrock and Jessberger, 1995).

Since landfill liners are expected to maintain their efficacy over periods of time several orders of magnitude greater than are conventional engineering structures, long-term behaviour and very slow physical processes are of special interest. Transport processes, desiccation in earthen layers and conditions which may endanger geomembranes, protective layers and drainage systems are fairly well understood. The mechanical properties of earthen materials can be improved and testing methods and apparatuses are available for the determination of critical values. Safety analysis shows that composite liners are extremely safe under the right conditions and, therefore, represent the standard by which the efficacy and equivalence of alternative liners should be measured (August *et al.*, 1997).

8.11 Acknowledgements

The author wishes to express his sincere gratitude to Professor K. Reddy (University of Illinois at Chicago, Illinois) and Dr W. Müller (Bundesanstalt für Materialforschung und -prüfung) for their helpful suggestions and advice and Professor H. August and Dr U. Holzlöhner (formerly Bundesanstalt für Materialforschung und -prüfung) for long-term cooperation. This chapter uses some of the results of the integrated research programme 'Advanced landfill liner systems' sponsored by the Bundesministerium für Bildung und Forschung under Projects 1440 569A and 1440 569I. The research achievements of the participants in the research programme are gratefully acknowledged.

8.12 References

- August, H., Holzlöhner, U., Meggyes, T. (Eds) (1997), *Advanced Landfill Liner Systems*, Thomas Telford, London, 380 pp.
- Aversch, U. B. and Schicketanz, R. T. (1998), 'Installation procedure and welding of geomembranes in the construction of composite landfill liner systems — focus on "Riegelbauweise"', in *Proceedings of the 6th International Conference on Geosynthetics* (Ed. R. K. Rowe), Industrial Fabrics Association International, Roseville, Minnesota, pp. 307–313.
- Campbell, D. J. V. (1994), 'Understanding co-disposal processes and practices', *Chemistry and Industry*, 6 June, pp. 407–409.

- Heibroek, G. and Jessberger, H. L. (1995), 'Safety analysis of a composite liner system', in *Proceedings of the 5th International Landfill Symposium*, Vol II, Santa Margherita di Pula, Cagliari, Sardinia, Italy, 1995, Centro di Ingegneria Sanitaria Ambientale, Università di Cagliari, Cagliari, pp.169–183.
- Holzlöhner, U. (1997), 'Water balance, the risk of desiccation in earthen liners', in *Advanced Landfill Liner Systems* (Eds H. August, U. Holzlöhner and T. Meggyes), Thomas Telford, London, pp. 19–30.
- Holzlöhner, U., August, H. and Meggyes, T. (1996), Building up the barriers for landfills. *Technology and Environment*. **2**(96), pp. 164–168.
- Holzlöhner, U., August, H., Meggyes, T. and Brune, M. (Eds) (1995), *Landfill Liner Systems. A State-of-the-Art Report*, Bundesanstalt für Materialforschung und -prüfung, Berlin.
- Solid and Hazardous Waste Research Unit, University of Newcastle upon Tyne, Newcastle upon Tyne, Penshaw Press, Sunderland, 304 pp.
- Müller, W. W. (Ed.) (2001), *Certification Guidelines for Plastic Geomembranes Used to Line Landfills and Contaminated Sites*, Laboratory of Landfill Engineering, Bundesanstalt für Materialforschung und -prüfung, Berlin.
- Müller, W. W. (2006), *HDPE Geomembranes in Geotechnics*, Springer, Berlin Heidelberg, p. 485.
- Sharma, H. D. and Reddy, K. R. (2004), *Geoenvironmental Engineering: Site Remediation, Waste Containment, and Emerging Waste Management Technologies*, Wiley, Hoboken, New Jersey.
- Spillmann, P., Dörrie, T. and Struve, M. (Eds) (2007) *Long-term Hazard for Drinking Water Resources by Landfills*, Thomas Telford, London (in press).
- Stief, K. (1986), 'Das Multibarrierenkonzept als Grundlage von Planung, Bau, Betrieb und Nachsorge von Deponien', *Müll und Abfall* **1**, pp. 15–20.
- 'TI hazardous waste: second general administrative provision to the Waste Avoidance and Waste Management Act, Part 1: technical instructions on the storage, chemical, physical and biological treatment, incineration and disposal of waste requiring particular supervision of 12.3.1991' (in German), in *Müll-Handbuch*, Vol. 1, 0670, Erich Schmidt Verlag, Berlin, pp. 1–136.
- 'TI municipal waste: third general administrative provision to the Waste Avoidance and Waste Management Act: technical instructions on recycling, treatment and storage of municipal waste of 14.5.1993' (in German), in *Müll-Handbuch*, Vol. 1, 0675, Erich Schmidt Verlag, Berlin, pp. 1–52.
- UK Department of the Environment (1993), *UK Landfill Practice – Co-disposal*, UK Department of the Environment, London.

8.13 Further reading

- Aubertin, M., Aachib, M. and Authier, K. (2000), 'Evaluation of diffusive gas flux through covers with a GCL', *Geotextiles and Geomembranes*, **18**, pp. 215–233.
- August, H., Tatzky-Gerth, R., Preuschmann, R. and Jakob, I. (1992), *Permeationsverhalten von Kombinationsdichtungen bei Deponien und Altlasten gegenüber wassergefährdenden Stoffen, F+E-Vorhaben 102 03 412*, Bundesanstalt für Materialforschung und -prüfung im Auftrag des Umweltbundesamtes, Berlin.
- Bagchi, A. (1990), *Design, Construction and Monitoring of Sanitary Landfill*, Wiley, New York, 284 pp.
- Barron, J. (1993), 'Landfill: liability and risk assessment', in *Discharge your Obligations – Cost Effective Application of New Technology in the Landfill Industry, Proceedings of a*

- Conference, Kenilworth, Warwickshire, UK, 2–4 November 1993, CPL Press, Newbury, Berkshire, pp. 13–22.
- Bergs, C. (1993), 'Grundzüge der TA Siedlungsabfall, Biologische Behandlung im Gesamtzusammenhang der TA Siedlungsabfall', in *Symposium Die neue TA-Siedlungsabfall und ihre Folgen, FIP Schriftenreihe*, Band 1, Verlag Mainz, Wissenschaftsverlag, Aachen, pp. 115–125, pp. 335–347.
- Boels, D. and Van der Wal, K. (1999), 'Trisoplast: new developments in soil protection', in *Proceedings Sardinia 1999, 8th International Waste Management and Landfill Symposium* (Eds R. Cossu, H. Christensen and R. Stegmann), Cagliari, Sardinia, Italy, 1999, Centro di Ingegneria Sanitaria Ambientale, Università di Cagliari, Cagliari, pp. III.77–84.
- Bräcker, W. (Ed.) (2002), *AbfallwirtschaftsFakten 6.1, Oberflächenabdeckungen und Abdichtungen*, Niedersächsisches Landesamt für Ökologie, Hildesheim.
- Bräcker, W. (2002), 'Einsatz von Abfällen als Deponiebaustoffe', *AbfallwirtschaftsFakten*, (7), pp. 1–6.
- Bundesregierung (2001), 'Abfallablagerungsverordnung', *Bundesgesetzblatt I(10)* 305.
- Bundesregierung (2002), 'Verordnung über Deponien und Langzeitlager', *Bundesgesetzblatt I(52)* 2807.
- Burkhardt, G. and Egloffstein, T. (1994), 'Vergleich von Abdichtungssystemen – Gleichwertigkeit?', in *Alternative Dichtungsmaterialien im Deponiebau und in der Altlastensicherung, Seminar des VDI-Bildungswerkes* (Eds K. A. Czurda, H. Hötzl, G. Burkhardt and T. Egloffstein), 17–18 March 1994, Lehrstuhl für Angewandte Geologie der Universität Karlsruhe, Karlsruhe, pp. 217–268.
- Burkhardt, G. and Egloffstein, T. (Eds) (1995), *Asphaltdichtungen im Deponiebau*, Expert-Verlag, Renningen-Malmsheim.
- Christophersen, M., Linderöd, L., Jensen, P.E. and Kjeldsen, P. (2000), 'Methane oxidation at low temperatures in soil exposed to landfill gas', *Journal of Environmental Quality*, **29**, pp. 1989–1997.
- Collins, H.-J. and Brammer, F. (1994), 'Bewässerung von Mülloberflächen', *Müll und Abfall*, **26**(5), pp. 260–278.
- Czurda, K. A. (1994), 'Multimineralische Abdichtung', in: *Alternative Dichtungsmaterialien im Deponiebau und in der Altlastensicherung. Seminar des VDI-Bildungswerkes* (eds K. A. Czurda, H. Hötzl, G. Burkhardt and T. Egloffstein) 17–18 March 1994, Lehrstuhl für Angewandte Geologie der Universität Karlsruhe, Karlsruhe, pp. 1–22.
- Dobson, M. C. and Moffat, A. J. (1993), 'The potential for woodland establishment on landfill sites', Research Report, Department of the Environment, HMSO, London.
- Dusseault, M. B. (1993), 'Solution cavern entombment of granular wastes'. in *Geology and Confinement of Toxic Wastes*, A. A. Balkema, Rotterdam, pp. 47–54.
- Egloffstein, T.A. (2002), 'Bentonite as sealing material in geosynthetic clay liners — influence of the electrolytic concentration, the ion exchange and ion exchange with simultaneous partial desiccation on permeability', in *Clay Geosynthetic Barriers*, (Eds H. Zanzinger, R. M. Koerner and E. Gartung), A. A. Balkema, Lisse, pp. 141–153.
- Ehrig, H.-J. and Krümpelbeck, I. (1999), *Abschätzung der Restemissionen von Deponien in der Betriebs- und Nachsorgephase auf der Basis realer Überwachungsdaten*, Umweltbundesamt, Berlin.
- Förstner, U., Kersten, M. and Wienberg, R. (1989), 'Geotechnical processes in landfills', in *The Landfill, Reactor and Final Storage* (Ed. P. Baccini), Springer, Berlin, pp. 39–81.
- German Geotechnical Society for the International Society of Soil Mechanics and Foundation Engineering (1991), *Geotechnics of Landfills and Contaminated Land, Technical Recommendations 'GLC'* (Ed. H. L. Jessberger), Ernst, Berlin.

- Gibb Environmental Sciences (1991), 'Capillary barrier landfill caps', in *Report of the Landfill Practices Review Meeting*, London, 6 November 1991, Wastes Technical Division, UK Department of the Environment, London.
- Hix, K. (1998), 'Leak detection for landfill liners, overview of tools for vadose zone monitoring', *Technical Status Report EPA-542-R-98-019*, US Environmental Protection Agency, Washington, DC.
- Holzlöhner, U. and Meggyes, T. (1995), 'Schutz vor Kontamination durch Deponien (Protection from contamination by landfills)', in *Handbuch der Bodenkunde* (Eds H.-P. Blume, P. Felix-Henningsen, R. Fischer, H.-G. Frede, R. Horn and K. Stahr), Ecomed, Landsberg/Lech, Chapter 7.6.7, pp. 1–19.
- Holzlöhner, U., Meggyes, T. and Seeger, S. (1999), 'Landfill technology in Germany', *Land Contamination and Reclamation*, **2**, pp. 109–119.
- Holzlöhner, U. and Ziegler, F. (1995), 'The effect of overburden pressure on desiccation cracking of earthen liners' in *Proceedings of the 5th International Landfill Symposium*, Vol II, Santa Margherita di Pula, Cagliari, Sardinia, Italy, 1995, Centro di Ingegneria Sanitaria Ambientale, Università di Cagliari, Cagliari, pp. 203–212.
- Hull, J. (1993), 'Recent developments in the use of waste-paper based daily cover systems in Europe', in *Discharge your Obligations — Cost Effective Application of New Technology in the Landfill Industry, Proceedings of a Conference*, Kenilworth, Warwickshire, UK, 2–4 November 1993, CPL Press, Newbury, Berkshire, pp. 89–94.
- Jessberger, H. L. (1992), *ITVA Arbeitspapier Dichtwände*.
- Kalbe, U., Berger, W. and Müller, W. (2000), 'Mineralogische und chemisch-physikalische Auswirkungen der Permeation von Kohlenwasserstoffen in Kombinationsdichtungen und -dichtwänden', *Bericht zum Forschungsvorhaben 1461027*, Bundesministerium für Bildung und Forschung, Bundesanstalt für Materialforschung und -prüfung, Labor Kontaminationsbewertung, Berlin.
- Koerner, R. M. and Daniel, E. D. (1994), 'A suggested methodology for assessing the technical equivalency of GCLs to CCLs', in *Geokunststoff-Ton-Dichtungen* (Ed. E. Gartung), Grundbauinstitute der Landesgewerbeanstalt, Nürnberg, pp. 59–85.
- Landesumweltamt Nordrhein-Westfalen (1993), 'Mineralische Deponieabdichtung', *Richtlinie 18*, Landesumweltamt Nordrhein-Westfalen, Essen.
- McDonald, C., Meggyes, T. and Simmons, E. (1997), 'Landfill capping: engineering and restoration. 1: structure and function of landfill capping systems', *Land Contamination and Reclamation*, **5**, pp. 89–97.
- Meggyes, T. and Holzlöhner, U. (1995a), 'Today's landfill liners protecting tomorrow's environment', *Environmental Technology*, **1**(95), pp. 84–92.
- Meggyes, T. and Holzlöhner, U. (1995b), 'Immissionsschutz bei Deponien', in *9. Internationales Kolloquium über Hydromechanisation, Publications of the University of Miskolc, Series A, Mining*, Vol. 50, *Process Engineering*, Fasc. 2, Miskolc, Hungary, 1995, University of Miskolc, Miskolc, pp. 173–187.
- Meggyes, T., Holzlöhner, U. and August, H. (1995), 'Improving the technical barrier for landfills', in *Proceedings of the 5th International Landfill Symposium*, Vol. II, Santa Margherita di Pula, Cagliari, Sardinia, Italy, 1995, Centro di Ingegneria Sanitaria Ambientale, Università di Cagliari, Cagliari, pp. 89–102.
- Meggyes, T., Holzlöhner, U. and August, H. (1997), 'A multidisciplinary approach to improving the safety and durability of landfill barriers', in *Contaminated and Derelict Land, Proceedings Related to the European Environment* (Ed. R. W. Sarsby), Thomas Telford, London, pp. 413–420.
- Meggyes, T., Simmons, E. and McDonald, C. (1998), 'Landfill capping: engineering and

- restoration: 2. engineering of landfill capping systems', *Land Contamination and Reclamation*, **1**, pp. 27–37.
- Melchior, S. (1993), 'Wasserhaushalt und Wirksamkeit mehrschichtiger Abdecksysteme für Deponien und Altlasten', *Hamburger Bodenkundliche Arbeiten* 22, Institut für Bodenkunde, Universität Hamburg, Hamburg, 330 pp.
- Melchior, S. and Steinert, B. (2001), 'Die Kapillarsperre – Stand der Technik, Leistungsfähigkeit und Kosten', in *Oberflächenabdichtungen für Deponien*, Vol. 29 (Ed. S. A. Savidis), Grundbauinstitut der Technischen Universität Berlin, Berlin, pp. 19–32.
- Melchior, S., Steinert, B. and Flöter, O. (2001), 'A comparison of traditional clay barriers and the polymer-modified material trisoplast in landfill covers', in *Proceedings of the Sardinia 2001 8th International Waste Management and Landfill Symposium* (Eds R. Cossu, H. Christensen and R. Stegmann), Cagliari, Sardinia, Italy, 2001, Centro di Ingegneria Sanitaria Ambientale, Università di Cagliari, Cagliari, pp. 55–64.
- Meyer, F., Bayersdorf, F. and Kasper, H. (1991), 'Daily cover of landfills with the on site foam system Plastsoil', *Proceedings of the Sardinia 91 3rd International Landfill Symposium*, Santa Margherita di Pula, Cagliari, Sardinia, Italy, 14–18 October 1991, Centro di Ingegneria Sanitaria Ambientale, Università di Cagliari, Cagliari, pp. 1087–1091.
- Mott MacDonald Environment (1991), *Welbeck Reclamation and Landfill Project*, City of Wakefield Metropolitan District Council, West Yorkshire Waste Management Joint Committee, Wakefield, West Yorkshire.
- Müller, W. W. (1996), 'Anforderungen an die Schutzschicht für die Dichtungsbahnen in der Kombinationsdichtung, Teil 2: Zulassungsanforderungen', *Müll und Abfall*, **28**(2), pp. 90–99.
- Müller, W. W. (1999), 'Stofftransport in Deponieabdichtungssystemen, Teil 3: Auswirkungen von Fehlstellen in der Dichtungsbahn, ein Überblick', *Bautechnik*, **76**(9), pp. 757–768.
- Müller, W. W. (2002a), 'Kunststoff-Dränmatten im Deponiebau Teil 1: Eigenschaften und Beurteilung', *Bautechnik*, **79**(3), pp. 178–192.
- Müller, W. W. (2002b), 'Kunststoff-Dränmatten im Deponiebau Teil 2: Zur Bemessung', *Bautechnik*, **79**(4), pp. 232–242.
- Müller, W. W., August, H., Jakob, I., Tatzky-Gerth, R. and Vater, E.-J. (1995), 'Die Wirkungsweise der Kombinationsdichtung – Immersionsversuche zur Schadstoffmigration in Deponieabdichtungssystemen', in *Asphaltdichtungen im Deponiebau – Eine Standortbestimmung* (Eds G. Burkhardt and T. Egloffstein), Expert Verlag, Renningen-Malmsheim.
- Müller, W. W., Büttgenbach, B., Tatzky-Gerth, R. and August, H. (1997), 'Stofftransport in Deponieabdichtungssystemen, Teil 2: Permeation in der Kombinationsdichtung', *Bautechnik*, **74**(5), pp. 331–344.
- Müller, W. W. and Jakob, I. (2003), 'Oxidative resistance of high-density polyethylene geomembranes', *Polymer Degradation and Stability*, **79**(1), pp. 161–171.
- Müller, W. W. and Seeger, S. (2002), 'Requirements for leak monitoring systems for HDPE geomembrane landfill liners', *Land Contamination and Reclamation*, **10**(2), pp. 91–99.
- Müller, W. W., Jakob, I., Tatzky-Gerth, R. and August, H. (1998), 'Solubilities, diffusion and partition coefficients of organic pollutants in HDPE geomembranes: experimental results and calculations', in *Proceedings of the 6th International Conference on Geosynthetics* (Ed. R. K. Rowe), Industrial Fabrics Association International, Roseville, Minnesota, pp. 239–248.
- Müller, W. W., Büttgenbach, B., Jakob, I. and Mann, H. (2003), 'Comparison of the oxidative resistance of various polyolefin geotextiles', *Geotextiles and Geomembranes*, **21**, pp. 289–315.

- Müller W. W., Seeger, S., Thies, M. and Gerloff, C. (2004), 'Long-term shear strength of multilayer geosynthetics' in *Geotechnical Engineering with Geosynthetics, Proceedings of the 3rd European Geosynthetics Conference* (Eds R. Floss, G. Bräu, M. Nussbaumer and K. Laackmann), Deutsche Gesellschaft für Geotechnik und Technische Universität München, Zentrum für Geotechnik, München, pp. 429–434.
- Palm, A. and Mähnz, K. (2001), 'Zum Einsatz von alternativen mineralischen Materialien in Oberflächenabdichtungen', in *Oberflächenabdichtungen für Deponien*, Vol. 29 (Ed. S. A. Savidis), Grundbauinstitut der Technischen Universität Berlin, Berlin, pp. 58–68.
- Sarsby, R. (2000), 'Environmental geotechnics', *Waste Disposal by Landfills*. Thomas Telford, London, Chapter 12.
- Sarsby, R. W. and Meggyes, T. (Eds.) (2001), *The Exploitation of Natural Resources and the Consequences, Proceedings of the 3rd International Symposium on Geotechnics Related to the European Environment*, 21–23 June, 2000, Thomas Telford, London, p. 580.
- Schellenberg, K. and Schellenberg, P. (2001), 'Oberflächenabdichtungen aus Asphalt', in *Oberflächenabdichtungen für Deponien*, Vol. 29, (Ed. S. A. Savidis), Grundbauinstitut der Technischen Universität Berlin, Berlin, pp. 45–57.
- Seeger, S. and Müller, W. W. (2003), 'Theoretical approach to designing protection: selecting a geomembrane strain criterion', in *Geosynthetics: Protecting the Environment* (Eds N. Dixon, D. M. Smith, J. H. Greenwood and D. R. V. Jones), Thomas Telford, London.
- Shackelford, C. D. and Daniel, D. E. (1991a), 'Diffusion in saturated soil. I: background'. *Journal of Geotechnical Engineering, American society of Civil engineers*, **117**, pp. 467–484.
- Shackelford, C. D. and Daniel, D. E. (1991b), 'Diffusion in saturated soil. II: results for compacted clay'. *Journal of Geotechnical Engineering, American Society of Civil Engineers*, **117**, pp. 485–506.
- Simon, F.-G. and Müller W. (2004), 'Standard and alternative capping design in Germany', *Environmental Science and Policy*, **7**, pp. 277–290.
- Stief, K. (1993), 'Zur Gleichwertigkeit von Deponieabdichtungssystemen' in *9. Nürnberger Deponieseminar*, 29–30 April 1993, Grundbauinstitut der Landesgewerbeanstalt Bayern, Nürnberg.
- Suter, G. W., Luxmoore, R. J. and Smith, E. D. (1993), 'Compacted soil barriers at abandoned landfill sites are likely to fail in the long term', *Journal of Environmental Quality*, **22**(2), pp. 217–226.
- Thornton, S. F., Lerner, D. N., Bright, M. I. and Tellam, J. H. (1993), 'The role of attenuation in landfill liners', in *Proceedings of the Sardinia 93 4th International Landfill Symposium*, Santa Margherita di Pula, Cagliari, Sardinia, Italy, 11–15 October 1993, Centro di Ingegneria Sanitaria Ambientale, Università di Cagliari, Cagliari, pp. 407–416.
- US Department of Energy (2000), 'Alternative landfill cover', *Innovative Technology Summary Report OST/TMS ID 10*, Sandia National Laboratories, Sandia, New Mexico, USA.
- Wienberg, R. (1990), 'Zum Einfluß organischer Schadstoffe auf Deponietone', *AbfallwirtschaftsJournal*, **2**, pp. 222–230, pp. 306–314.
- Wienberg, R. (1994), 'Rückhaltevermögen der geologischen Barriere gegenüber organischen Sickerwasserinhaltsstoffen — Definition und Quantifizierung', in *Expertengespräch 'Geologische Barriere'*, 26–27 September 1994, Bundesanstalt für Geowissenschaften und Rohstoffe, Hannover.
- Zanzinger, H., Koerner, R. M. and Gartung, E. (Eds) (2002), *Clay Geosynthetic Barriers*, A. A. Balkema, Lisse.

The use of geosynthetics as barrier materials in civil engineering

H. ZANZINGER
SKZ-TeConA GmbH, Germany

9.1 History

9.1.1 First applications

The use of geosynthetics in containment ponds, reservoirs and canals can be traced back to the 1940s and actually emerged in the 1960s and 1970s (Duquennoi, 2002). It is generally admitted that liquid containment represents the first use of geosynthetic barriers (GBRs), or at least what can be considered as historical GBR forerunners. Koerner (2005) records the probable use of rubber liners as early as the 1930s and the use of poly(vinyl chloride) (PVC) liners in the 1940s. Monjoie *et al.* (1992) confirmed these beginnings by citing the use of isoprene–isobutylene (better known as butyl) rubber liners in the 1940s. Almost at the same time, canal lining techniques using the *in situ* application of sprayed-on bituminous coatings were developed in the USA. It is estimated that, between 1947 and 1951, more than 10^6 m² of bituminous canal liners were applied in that way. Together with this first-generation synthetic liners the first pathologies appear, including brittleness and cracking of unprotected PVC, localized mechanical damage of unreinforced bituminous coatings, etc. These early inconveniences set the trend for technical enhancement, which, from that time, took the following directions.

Another early polymeric geosynthetic barrier (GBR-P), chlorosulphonated polyethylene (CSPE), was introduced for reservoir and landfill liners in the late 1960s. In the 1970s, polymeric, elastomeric and bituminous GBRs were installed as liners to contain water and contaminated industrial liquid effluents in regions where natural clay was not available. While the incentive to develop GBRs may have originated from the substitution where there was a shortage of natural clayey soils, now they are used worldwide. The use of high-density polyethylene (HDPE) GBRs as liners in geotechnical hydraulic applications started in the 1960s while their growth in the USA and Germany was stimulated by governmental regulations originally enacted in the early 1980s in landfill applications. The primary function

is always containment as a liquid or vapour barrier or both. Koerner (2005) reported that the US market is divided as follows: HDPE (40%), linear low-density polyethylene (LLDPE) (25%), PVC (20%), CSPE (5%), flexible polypropylene (fPP) (5%) and ethylene propylene diene terpolymer (EPDM) (5%).

In some countries (such as France and the Netherlands), bituminous geosynthetic barriers (GBR-Bs) are seeing some use for linings of reservoirs, surface impoundments and landfills.

Since the late 1980s, clay geosynthetic barriers (GBR-Cs) have been used as an alternative to soil barriers in various applications to contain liquids, industrial effluents and in association with HDPE polymeric GBRs in landfills. The first product was adhesive-bonded bentonite between two geotextiles. The second product at about the same time was a needle-punched geocomposite consisting of two geotextiles and bentonite powder between. A further bonding method for GBR-Cs is stitch bonding. Another manufacturer uses an adhesive to bond bentonite powder on to an HDPE or LLDPE GBR-P. The engineering function of a GBR-C is containment as a hydraulic barrier to water, leachates or other liquids and sometimes to gases. As such, GBR-Cs are used for replacements to either compacted clay liners (CCLs), or GBR-Ps or GBR-Bs, respectively, or they are used in composite manner to augment the more traditional liner materials.

9.1.2 Terms

The term 'geomembranes' was used in the 1990s and is still in use. It was originally devised to replace previous imprecise terms such as 'pond liners', 'flexible membranes' and 'waterproofing sheets'. The term 'geosynthetic clay liners' (GCLs) is still used today. GBR-Cs are geocomposites consisting of geosynthetics and bentonite. Other names are 'clay blankets', 'bentonite blankets', 'bentonite mats', 'prefabricated bentonite clay blankets' and 'geocomposite clay liners'.

As there were too many definitions on geomembranes and geosynthetic clay liners in various countries, the ISO Technical Committee 221 of the International Organization for Standardization and the CEN Technical Committee 189 of the European Committee for Standardisation decided together, to come up with the new term 'geosynthetic barriers' which covers all GBR-Ps, GBR-Bs and clay geosynthetic barriers. The definitions given in EN ISO 10318: 2005 are the following: 'A geosynthetic barrier is a low-permeability geosynthetic material, used in geotechnical and civil engineering applications with the purpose of reducing or preventing the flow of fluid through the construction. A polymeric geosynthetic barrier is a factory-assembled structure of geosynthetic materials in the form of a sheet, which acts as a barrier. The barrier function is essentially fulfilled by polymers. It is used in contact with soil and/or other materials in geotechnical and civil engineering applications. A clay geosynthetic barrier is a factory-assembled structure of geosynthetic materials in the form of a sheet, which acts as a barrier. The barrier function is essentially fulfilled by clay. It is used in

contact with soil and/or other materials in geotechnical and civil engineering applications. A bituminous geosynthetic barrier is a factory-assembled structure of geosynthetic materials in the form of a sheet, which acts as a barrier. The barrier function is essentially fulfilled by bitumen. It is used in contact with soil and/or other materials in geotechnical and civil engineering applications.'

9.2 Products

9.2.1 Polymeric geosynthetic barriers

Various types of polymers have been used. The principal types appeared in the following order: chlorinated polyethylene (CPE), chlorosulphonated polyethylene 'Hypalon' (CSPE), PVC, polychloroprene 'neoprene', EPDM, HDPE, low-density polyethylene (LDPE), LLDPE, very-low-density polyethylene, fPP and thermoplastic polyolefins (TPO). Various compounds, such as plasticizers, antioxidants and mineral fillers, have been developed and used to enhance chemical stability, durability, thermal, biological and mechanical properties of the GBR-Ps. The inclusion of reinforcing materials was originally used to strengthen bituminous liners but they are not the only liners to be reinforced; CPE-R, CSPE-R, PVC-R, fPP-R and EPDM-R are also reinforced, which the letter R indicates.

The production of the raw materials includes the polymer resin itself, and various additives such as antioxidants, plasticizers, fillers, carbon black and lubricants (as a processing aid). The raw materials are then processed into sheets of various widths and thicknesses by extrusion, calendaring and spread coating.

HDPE, LLDPE and fPP are manufactured by an extrusion method. One process uses a flat die, which forces the polymer formulation between two horizontal die lips, resulting in a smooth polymer sheet of closely controlled thickness from 0.75 to 3.0 mm. The sheet from one extruder varies from 1.8 to 4.6 m. If two parallel extruders are used, the width can be increased to 9.5 m. Another process uses a circular die (called blown film extrusion), which forced the polymer formulation between two concentric die lips oriented vertically upwards. The creation of a roughened surface on a smooth sheet in a process is called texturing. A high-friction surface can be created. These methods are subjected to co-extrusion with nitrogen gas, impingement of hot polyethylene particles, lamination of polyethylene foam and structuring, or patterning, a surface.

PVC, CSPE and scrim-reinforced GBR-Ps including CSPE-R and fPP-R are manufactured by calendaring, a method in which the polymer resin, carbon black, filler, plasticizers (if any) and additive package are weighed and mixed. During mixing, heat is added, which initiates a reaction between the components. As a continuous mass it is conveyed through a set of counter-rotating rollers (called a 'calender') to form the final sheet. When an additional fabric scrim is included, they are called 'reinforced'.

A thermoset GBR-P is EPDM, both non-reinforced and scrim reinforced

(EPDM-R). The processing is similar to the calendering process and an additional autoclaved manufacturing.

9.2.2 Bituminous geosynthetic barriers

A GBR-B is a prefabricated geocomposite, which includes reinforcing fabrics consisting of multiple layers such as geotextiles, glass fibre woven or non-woven and root barriers. The bitumen is coated with sand.

Modified styrene-butadiene-styrene bituminous GBRs should not be in contact with non-polar solvents (aromatic solvents, aliphatics and halogenics) for a long time, nor with very strong acidic and basic solutions ($\text{pH} < 2$ and $\text{pH} > 9$, respectively). By virtue of their inherent porosity, geotextiles rarely serve in the containment function. The exception is when the geotextile is purposely impregnated with bitumen or polymer. These few products will not be seen as GBRs.

9.2.3 Clay geosynthetic barriers

There are two bonding concepts. One is adhesive bonding of the product and the other is needle punching and stitch bonding of the product. The second types of technique can transfer shear stresses through the plane of the plane even in the hydrated stage of the bentonite. Others deliver already prehydrated bentonite for certain reasons. Some products may have a bituminous coating on the outside geotextiles or a polymer-impregnated cover geotextile and others even have an additional LDPE foil on or beneath the cover geotextile.

Bentonite essentially consists of clay minerals of the smectite group, montmorillonite being the dominant species. Because of their particular physico-chemical properties, montmorillonite crystals contain exchangeable cations, mostly sodium or calcium. For practical purposes, a distinction is made between bentonites that predominantly consist of montmorillonite with sodium cations, and bentonites that predominantly consist of montmorillonite with calcium cations. They are encountered in nature and obtained by open-pit mining.

Most of the GBR-Cs use natural sodium bentonite. Some use a bentonite, which in nature occurs as calcium bentonite but by processing is converted to a sodium bentonite. Until now there is only one GBR-C that uses natural calcium bentonite. Some manufacturers add chemicals to improve the performance of their bentonite. The bentonite is delivered to the GBR-C manufacturer as a typically dry (about 10% moisture content owing to the extremely high hydrophilic nature of the bentonite) powder or in granulated form. The masses per unit area range from 3 to 6 kg/m^2 for sodium bentonite and from about 8 to 10 kg/m^2 for calcium bentonite. Although it is derived from a mined natural product, there is very little scatter in the properties of processed bentonites delivered by competent suppliers.

Although bentonite particles are extremely small, their surface area is very large. They can adsorb great amounts of water. Sodium bentonite can reach water

contents of about 600%, and calcium bentonite up to 300%. They swell while they acquire these high water contents. As noticed by the difference in free swell water contents, the swelling capacities of sodium and calcium bentonite are different and so are their hydraulic conductivities, as well as their shear strengths. The hydraulic conductivity is lowest for sodium bentonite which is why this mineral is preferably used for GBR-Cs. The permittivity is typically in the range $(5-1) \times 10^{-9} \text{ s}^{-1}$. However, at the same time, the shear strength is also lowest for sodium bentonite, which causes concerns with respect to the stability of slopes (Madsen and Nüesch, 1995).

Since the properties that make sodium bentonite perform as an excellent sealing material are related to its interaction with water, the quality of bentonites can be evaluated on the basis of their swelling capacity (free swelling), water adsorption capacity, methylene blue adsorption, cation exchange capacity and density of cations.

These properties can be determined by relatively simple tests used to identify bentonites in practice (Egloffstein, 1995).

Since bentonite exhibits swelling with substantial volume increase when water is added, it undergoes shrinkage by equivalent amounts of volume reduction when it desiccates. Sodium bentonite can be subjected to an unlimited number of swelling and shrinkage cycles without changes in its properties as long as the chemistry of the water-clay mineral system is not changed. Desiccation cracks heal and close again because of swelling, provided that the soil structure is not influenced by chemical processes. However, water percolating through soil invariably contains some cations and anions in solution, which can react with the sodium montmorillonite minerals. This means that an exchange of some of or even all the sodium ions by other cations, in practice mainly by calcium ions, has to be anticipated, when wetting-drying cycles occur. So, depending on the physical and chemical milieu parameters, the properties of the GBR-C in place may undergo some changes with time owing to cation exchange.

GBR-Cs are composites of bentonite and geotextiles. The geotextile components provide strength. They determine the mechanical properties of GBR-Cs. The shear strength of hydrated bentonite is extremely low. In fact, a thin wet bentonite layer acts as a lubricant. GBR-Cs without a mechanical bond between the three layers would have no internal shear strength at all. So the ties between the two geotextile layers with the sandwiched bentonite between them are of prime importance. These ties are stressed when the bentonite is hydrating and the swelling bentonite experiences an increase in volume. The swelling pressure that builds up within the GBR-C during hydration, as a result of the restriction of the bentonite volume increase by the bonds, improves the sealing effect. The fibres that tie the GBR-C together are permanently stressed as long as the GBR-C is wet. Their tensile forces increase when the GBR-C is placed on a slope and the textile ties prevent the soil layers above the GBR-C from sliding on a slip plane within the bentonite layer.

Consequently, the internal strength of GBR-Cs must be warranted for long-term conditions. Tests and experience up to now prove that the long-term internal shear strength of the currently available GBR-Cs meets design requirements for slopes in landfill engineering. In most practical cases, interface friction at the upper and lower surfaces of the GBR-C turns out to be the controlling parameter in stability analyses of landfill slopes rather than the internal shear strength.

9.3 Design

9.3.1 Subgrade preparation

The subgrade of any GBR must be free of any vegetal and organic matter. All elements that are potentially aggressive toward the GBR (e.g. sharp stones) should be eliminated and/or avoided. The subgrade then has to be compacted in order to optimize its bearing capacity, according to state-of-the-art soil mechanics. The bottom of the structure should form a slight slope, between 1 and 2% lengthways, and between 2 and 3% sideways. The embankment slopes should be designed according to state-of-the-art soil mechanics; this is important, as GBR lining systems cannot be used to reinforce slopes. For many applications, a 1V:3H slope is advised, and 1V:1.5H is to be considered as the maximum. The embankment top should be wide enough to enable geosynthetic anchoring; minimum anchoring length is generally 2 m for ponds and reservoirs and 1 m for canals, but specific designs must be taken into account.

9.3.2 Underliner drainage and protection

In hydraulic applications such as reservoirs and canals, it is generally not recommended to lay a GBR directly on the subgrade, except in particular cases such as landfills when the risks of puncture of the GBR and underliner pore water of gas pressure have been catered for. A better way to prevent the above-mentioned risks is to design specific underliner systems. Geosynthetics are particularly adapted to this application.

An underlining water drainage system can collect water leaking from a pond, canal or reservoir. It can also prevent an uplift of the GBR due to back pressure from a raised water table. Either gravel layers or geosynthetic drainage layers can be used. They can additionally be used as leakage detection systems. Another issue is the collection of gas from organic fermentation or compressed soil pore air. Both water and gas must be separated and collected in water trenches at the bottom of the system and in gas vents passing through the GBR at the top of the lining system respectively. Geotextiles are generally preferred as they combine different functions: gas drainage and protection of the underliner.

9.3.3 General criteria of the choice of a barrier system

The core of a lining system is the GBR. As the variety of the products is so wide, criteria have to be given to choose the suitable barrier system.

- 1 The cost of a geosynthetic lining system is always critical and depends on many parameters, which cannot all be accurately predicted in a technical article.
- 2 The hydraulic criterion will determine the choice of the behaviour regarding liquid transfer. Mass transfer will generally be smaller through polymeric or bituminous geosynthetic barriers, especially for non-organic chemical species, than through GBR-Cs. Very small liquid flow is possible through GBR-Cs, following Darcy's law. It must be emphasized that this statement holds true for undamaged, continuous polymeric or bituminous GBRs only, which highlights the necessity to protect these systems against puncture and seam defects.
- 3 Mechanical criteria are also very important, even if GBRs are never designed for mechanical functions in a structure. They may nevertheless be subjected to mechanical stress, such as tension on slopes, and in the case of subgrade settlement, or puncture by gravel and irregular subgrade. Even if mechanical stress is lessened or eliminated by proper design, e.g. with a geosynthetic protection, it is generally necessary to select GBRs with mechanical properties adapted to the expected mechanical conditions. The safety criteria depend on the experience and philosophy in different countries and regions.
- 4 Chemical resistance and durability criterion concern the polymer resin as well as the various compounds. It is well known that HDPE is the most chemically stable polymer available; nevertheless, the ageing phenomena depend on the use of an adequate stabilization. The physicochemical durability of PVC GBRs is highly dependent on the durability of the plasticizers and the principal factor of a GBR-C is the ion exchange capacity of the bentonite in combination with desiccation. For a liquid-waste containment, it is therefore of the utmost importance to determine correctly the expected composition of contained liquid and to compare it with the chart of chemical resistance of the GBR.
- 5 The question of whether a mineral liner or a GBR, and which type of GBR would be the better choice in a considered case, has to be answered on a rational basis, reflecting upon the following aspects: type of waste in a landfill or type of chemical solutions in an area where chemicals are stored and trans-shipped, requirements as related to the environment, gas-tightness and/or watertightness of the liner, expected lifetime considering ageing (resistance against environmental stress cracking and oxidation resistance), slope stability analyses, availability of sealing materials and local climatic conditions.
- 6 Nevertheless, it is important also to consider the ease of installation and seam performance criteria. Indeed, the best geosynthetic lining product will always be limited by its ability to be correctly installed and seamed. For example, phenomena such as thermally induced wrinkling or moisture-dependent welding quality may affect some GBRs and must be taken into account in the

planning of the installation. A strict application of a state-of-the-art installation procedure for each type of GBR must be required, as well as a state-of-the-art quality assurance and quality control programme. GBR-Cs are easy to install, but free swelling has to be avoided. The confinement–hydration procedure together with correct overlapping and seaming must be strictly respected.

Besides single-lining systems, it is possible to install double-lining systems using two polymeric geosynthetics with a drainage layer in between, or two GBR-Cs, or a combination of a GBR-P and a GBR-C.

9.3.4 Overliner protection and cover

Generally the best way to prevent ageing of geosynthetics is to limit their exposure to weather by an early covering with soil, for example. Such overliner soil layers prevent damage of the GBR caused by floating or transported ice and wood in canals, by operating vehicles and machines, by burrowing animals and by vandalism. The GBR must be protected against coarse granular material. Therefore, geotextiles are often used as protection layers between the GBR and the cover soil layers. On landfill bottom liner systems, combinations of sand and geotextiles or geocomposites are used as protection systems for the highest requirements against puncturing. Also, in some canals, sand-filled geotextiles were installed as protection layers.

Other common designs consider concrete covers using precast blocks or *in situ* poured reinforced concrete covers. In some installation procedures temporary ballast over the GBR is necessary in order to prevent uplift of the GBR due to wind action. Other applications of GBRs do not need any covering, e.g. many containment ponds and reservoirs. Most of the GBRs in canals use a covering system. All GBRs in landfills are covered as long as it is not only a temporary covering of the waste body.

9.3.5 Connections

GBRs have to be connected to structures such as manholes, shafts, pipes, walls and embankment tops. Difficulties arise when details are required. If the space is limited and automated equipment cannot be used, hand labour and experience are all important. Design in this case is really a matter of detailing and visualizing how settlements, deformations and other stress and strain mobilizing phenomena might influence the connection. A proper construction is not as simple as the drawings may appear. Care and true craftsman-like work are required for trouble-free and leak-free performance (Koerner, 2005).

9.4 Hydraulic applications

9.4.1 Liquid-containment ponds and reservoirs

In former times, polymeric GBRs were also named ‘pond liners’, which was the

original use of the polymeric materials. Hazardous and non-hazardous liquids are stored in containment ponds as well as liquid waste and water from the agriculture industry.

The construction is not simply digging a hole, putting a liner in it and then filling it with the liquid. It is a straightforward task but has much to do with the atmospheric exposure and possible damage to the GBR. To shield the liner from ozone, ultraviolet (UV) light, temperature extremes, ice damage, wind stresses, accidental damage and vandalism, a soil cover of 30 cm is usually required. Slope stability analyses and an adequate anchorage of the GBR are necessary. A geotextile placed beneath the GBR that is directly on the prepared soil subgrade before the placement of the GBR is strongly recommended. It provides a clean working area for making field seams and it adds puncture resistance to the GBR.

In certain cases, reservoirs for liquids and quasisolids such as industrial and agricultural sludge are covered with GBRs. The reasons for that are losses due to evaporation for irrigation reservoirs, savings on algae control chemicals for water reservoirs, reduced air pollution for reservoirs holding chemicals and agricultural waste, reduced need for draining and cleaning, increased safety against accidental drowning, protection from natural pollution entering the reservoir, temperature control for anaerobic decomposition of agricultural and organic wastes, and protection from intentional pollution. GBRs with superior UV and exposed weathering resistance have to be used for those covers. For smaller structures, the cover can be fixed and remain stationary. For larger span lengths, the use of a floating cover that resides directly on the liquid's surface as it varies in elevation will be considered (Koerner, 2005).

9.4.2 Canals

In canals the liquid is moving. The usual liquid is water, but many other liquids, including industrial chemicals and wastes, also need to be conveyed.

The GBR is placed either directly on the prepared soil subgrade or on a previously installed geotextile. A uniform thickness soil cover is commonly placed over the GBR. The cover soil type and its thickness depend on the velocity of the liquid and the turbidity of the flowing water. If these forces are such that the soil cover is eroded, they will act directly on the GBR. Therefore it is not uncommon to cover the liner with a non-erodible cover of asphalt, shotcrete or concrete.

Also the rehabilitation of old canals and their linings with GBRs is a challenging task in a rapidly growing field. It is not only polymeric and bituminous GBRs that are used in canals. Fleischer and Heibaum (2002) reported on an underwater installation of clay GBR in a waterway engineering project in Germany. Normally, the GBR-C will be placed in the dry. In these waterways, the GBR-C is loaded by severe dynamic hydraulic loading due to navigation, i.e. sudden drawdown of the water level, waves and return current. The overlap of the GBR-C sheets was 1 m and divers carefully checked this. The GBR-C was covered with a sandmat of

8000 g/m² mass per unit area. Additionally there are very high hydraulic gradients acting on the GBR-C. Since the thickness of the lining is only 1 cm, the gradient in a canal 4 m deep is more than 400. The experience showed that it is possible to use a GBR-C as an impermeable lining for navigable waterways.

9.4.3 Dams

The position of a waterproofing system is on the upstream face of a dam. The GBRs are typically protected with a facing of, for example, cast-in-place concrete slabs or a soil cover of gravel and random rock fill, if it is an earth dam with adequate slope inclinations. In these cases, the GBRs are protected against UV radiation and against damage from ice, for example. However, there is a need to protect the GBR against puncturing from the bedding layer caused from the high water pressure on the GBR and puncturing from the coarse gravel of the cover layer. Typically, geotextiles are used as protection layers. In many dams, PVC-P geosynthetic barriers are used with thicknesses of 2–3 mm. Thick GBRs provide strength against handling and placement damages and allow high-quality controlled welded seams (Sembenelli *et al.*, 1998). Other GBRs are made of HDPE (Sembenelli *et al.*, 1998) and also heavy bituminous GBRs are used in certain regions (Girard *et al.*, 1998; Gautier *et al.*, 2002).

On old concrete dams with typically vertical facings, GBRs and geocomposites (GCO) are applied for rehabilitation of these dams. In these cases, the GBRs are exposed to all weather conditions without any external protection. Such dams are often located in mountains and are very remarkable elevations with significant UV radiation. The GCOs could consist of a PVC-P GBR and a non-woven geotextile (Cazzuffi, 1998). The advantage of such a GCO is that it allows a continuous fastening along the vertical lines on the concrete and also a horizontal prestressing of the GBR itself. As these GBRs are unprotected, they have to be designed to withstand the action of ice and UV rays, especially when they are exposed to south orientation.

9.5 Tunnelling

Tunnels can be constructed near the surface and also at depth. Flüeler and Böhni (2001) reported studies on long tunnels through the Swiss Alps. Because of the large mountain cover, the GBR-P together with a drainage geocomposite should continuously drain the attracted mountain water, protect the concrete construction against water and locally transfer high compressive loads on to the concrete support structure. The GBR-P is installed between the relatively rough shotcrete outer shell and the concrete inner shell. The drainage geocomposite has to act as protection layer as well. At the base, the large mountain cover of 2500 m also results in rock temperatures of the order of 45 °C owing to geothermal effects. These conditions thus apply to the intruding water that is mostly alkaline, but

acidic in some areas. The expected service lifetime is 100 years with no major repairs within 50 years.

The GBR-Ps used are made of TPO, LLDPE, fPP and PVC-P. They have a light signal layer on a black core layer for easy detection of scrapes and damages in the GBR-P caused from improper installation techniques.

9.6 Transportation

Roads or railways through water protection areas require GBRs in order to prevent the migration of pollutants to the groundwater in cases such as accidents of oil or chemicals' transporters. The barrier has in addition to prevent migration of de-icing salt into the underground (Rathmayer, 2002). These jobs will be done by either GBR-Ps or GBR-Cs. Schmidt (1995) reported on a motorway in south Germany where the whole subgrade was covered with a GBR-C. Heerten (1995) described a project on the new Munich airport where GBR-Cs prevent groundwater contamination due to runway de-icers. GBR-Cs have also been used for the sealing of railway substructures of tracks passing through water conservation zones (Göbel *et al.*, 2002). In these cases, the GBRs have to be installed in such a manner that neither puncturing caused from high traffic loads nor freeze–thaw impacts may affect the barrier function of the GBRs.

9.7 Landfills

Waste material may contain substances that can be harmful to the environment. It is therefore mandatory to handle and store waste in such a way that any contamination of the ground as well as of the groundwater is prevented. So, the primary engineering assignment in designing, constructing and operating solid-waste landfills is to provide efficient barriers against contamination. Since water is the most important transporting agent for pollutants, the infiltration of water into and the extraction of water out of the solid-waste body must be controlled by reliable technical means. Liners and landfill covers are the most significant technical members of landfill structures for this purpose. In connection with dewatering facilities and the leachates collection and removal system, the basal liner and the cap seal are crucial elements with respect to landfill safety.

There is a close relationship between sealing and dewatering elements of the basal and of the cover barrier. Drainage facilities must maintain minimum gradients to facilitate gravitational flow. So, to some extent, the dewatering systems dictate the geometry of the surfaces of sealing layers. On the other hand, collection pipes for leachates should be placed in such a way that the unavoidable penetrations through the sealing layers do not impede the efficiency of the liners. These few examples show that the sealing layers and the dewatering elements form integral parts of barrier systems and have to be designed accordingly. They also influence each other during and after construction. Obviously, the placement of drainage

gravel above GBR-Ps must be executed with greatest care to avoid perforations of the liner.

9.7.1 Basal lining systems

The landfill containment is sealed at the bottom by a basal lining system composed of several layers, each one serving a particular purpose. It consists of the seal, the protector and the drainage blanket. In order to provide a continuous system of low permeability, the seal is placed directly above the subsoil without a drainage layer in between. The main seal may consist of a single or a double liner, and the liner itself could consist of an impervious monolayer or a composite. For example, a composite liner could be composed of a CCL and a GBR-P.

Since the GBR-P is rather thin and sensitive to mechanical damage, a special protective layer is needed above the GBR-P. This layer can be a geosynthetic product, a soil or a composite of both materials. In order to prevent any build-up of the leachates' pressure head above the sealing layers, a drainage blanket is incorporated in the basal lining system. Finally, it may be necessary to place a transition or filter between the drainage blanket and the waste body to maintain the long-term performance of the drainage system.

Extensive research in Germany by August *et al.* (1992), during the 1980s has led to the conclusion that a composite liner is the most efficient seal against the migration of the harmful components of leachates. Accordingly, the German instructions require such a composite liner at the bottom of municipal solid waste landfills and of hazardous waste landfills as a standard solution.

The polymer component acts as a cut-off for the flow of water. Because of its non-polar molecular structure, it prevents the diffusion of polar substances and therefore it is an absolute barrier against heavy-metal cations. Non-polar molecules of hydrocarbons or chlorinated hydrocarbons that may permeate through the GBR-P are retarded at the surface of the CCL owing to its strongly polar molecular structure. The effect is a decrease in the concentration gradient across the GBR-P and, consequently, a reduction in the rate of permeation. So, it is especially the interface of the GBR-P with the CCL that acts as an efficient barrier against the movement of contaminants such as hydrocarbons, provided that both components of the sealing system are in intimate contact.

The function of the GBR-P in the basal liner system of a solid-waste landfill is to retain leachates, a liquid that may be composed of many different substances, some of which can be harmful. In most cases the composition of the leachates cannot be predicted with sufficient certainty; it may vary with time. The only basis for an assessment of the properties of leachates is chemical analyses carried out on a great number of samples taken at many different landfill sites.

GBR-Ps used for landfill liners should be impervious to all the components found in leachates and also to those that might occur, they should resist chemical and biological attack in the landfill milieu without losing their functional

properties and, furthermore, they must be mechanically strong enough to survive transport, handling, placement and subsequent construction activities. The deformation behaviour has to be within acceptable limits, it has to be compatible with the deformations of the other components of the landfill structure, and it has to be predictable. The strength and the interface frictional resistance have to be in agreement with the stability requirements of the landfill structure.

In summary, the GBR-P has to meet a number of requirements concerning its physical, mechanical and endurance properties. Koerner (2005) listed 20 test methods for the determination of the parameters that describe the relevant properties of GBR-Ps. All-important material parameters have to be specified to make sure that the GBR-P is suitable for a landfill liner.

Most European countries have instructions for landfill GBR-Ps. In Germany, an approval system has been installed by legal action. The federal instructions Technische Anleitung Abfall (Federal Ministry for the Environment, Protection of Nature and Safety of Reactors, 1991) and Technische Anleitung Siedlungsabfall (Federal Ministry for the Environment, Protection of Nature and Safety of Reactors, 1993) specify that only approved GBR-Ps shall be used in landfill construction. Experts representing the GBR-P manufacturers, the testing and research institutions, the designers and the regulators agreed upon the approval criteria.

The procedure for the approval of GBR-Ps for landfill applications is executed by the Bundesanstalt für Materialforschung und -prüfung (1999). On the basis of more than 20 years' experience with polyethylene in civil engineering applications and comparative testing of other different GBR-P materials in the laboratories for polymers of Bundesanstalt für Materialforschung und -prüfung (August *et al.*, 1984), it has been decided that only polyethylene should be used in sealing systems of landfills.

The GBR-Ps approved in Germany exhibit excellent chemical resistance and sealing performance against a large variety of substances that could be encountered in the leachates of municipal or hazardous waste landfills. HDPE with a density between 0.932 and 0.942 g/cm³ is used. It must have a carbon black content of 1.8–2.6% and meet a number of strict requirements with respect to physical and chemical properties.

In order to warrant a sufficient robustness of the GBR-P in handling, the specified minimum thickness of approved GBR-Ps is 2.5 mm. This thickness also happens to be very satisfactory with respect to the sealing function. However, HDPE GBR-Ps of 2.5 mm are not very flexible.

The minimum width of the GBR-P roll is 5 m in order to minimize the amount of field seaming needed to create large waterproof sheets. The size and weight of the GBR-P rolls are specified, to make sure that they can be transported to the site and placed without severe handling problems.

The basal lining system includes a drainage blanket of very coarse gravel or crushed rock of typically 16–32 mm grain diameter above the GBR-P liner. Below

the waste body with a thickness of tens of metres, and also below moving construction equipment, the coarse grains exert considerable point loads on to the basal sealing layers. In order to avoid perforations of the GBR-P, a special puncture protection is needed.

9.7.2 Cover systems

When the filling process of a solid-waste landfill or of a larger portion of it is completed, the surface of the waste body has to be covered by a cap. The cover system has to prevent the infiltration of rainwater and the emission of odours, dust and gas, and it has to facilitate landscaping and the growth of vegetation. The main components of the cover of a landfill are a regulating soil layer immediately above the waste body, a gas-venting system, the sealing layers, a drainage system and the restoration profile. Depending on the requirements for the different landfill categories, these layers vary to some extent.

The properties and the behaviour of the waste influence the performance of the cap. They have to be taken into account in design and construction. For waste bodies that contain mineral solids that do not undergo chemical or biological reactions, no major long-term settlements are expected. This applies to landfills, which mainly contain ashes from incinerators, and it should apply to hazardous waste as well. For landfills without long-term differential settlements, the placement of the cover can be carried out as soon as the design height is reached.

Common municipal waste landfills are essentially bioreactors, where degradation processes take place in the waste body, associated with significant volume changes and gas production. The surfaces of this type of landfills usually experience large settlements for quite some time. It is likely that also substantial settlement differences occur locally which sometimes cannot be followed by mineral seals without the development of leaks. Since the bioreactors need a certain amount of water to continue the degradation processes, some leakage is probably of no concern. It makes sense to provide municipal waste landfills with CCLs or GBR-Cs, mineral layers of low hydraulic conductivity, as interim covers. Later these interim covers become parts of the final capping systems which contain a GBR-P as the main seal. The GBR-P should be placed when most of the anticipated differential settlements have occurred. To determine the right time for this action the deformation of the interim cover surface should be monitored.

As an alternative to a CCL, a GBR-C can be installed. The question of the equivalency of GBR-Cs and CCLs has been discussed by Koerner and Daniel (1995) and by Stief (1995) among others. The properties, testing methods and quality assurance aspects of GBR-Cs were compiled by Gartung and Zanzinger (1998). Practical experience shows that GBR-Cs as members of capping systems have some advantages over CCLs. Handling and installation are much easier, less time is needed for placement, waste storage space can be saved owing to the

smaller thickness and the quality of the manufactured geosynthetic product shows less scatter than of the natural clay soils.

On the other hand, it has to be kept in mind that because of their small thickness and small mass of bentonite they are extremely sensitive to damage during and after construction. So great care has to be taken in construction with GBR-Cs. The design of a GBR with GBR-Cs has to consider that desiccation of GBR-Cs has to be avoided because of the fact that dried-out sodium bentonite, for example, will exchange cations, and so sodium bentonite will change to calcium bentonite with much poorer swelling properties than those of sodium bentonite. In some projects in Germany, it was found that under certain conditions with the inadequate protection of the GBR-Cs against desiccation the barrier function of the GBR-Cs was lost (Gartung and Zanzinger, 1998).

Fissuring and growth of roots in mineral seals of landfill capping systems can be prevented by the placement of a GBR-P. A GBR-P can function as a barrier against root penetration as well as against moisture migration. The final sealing layers of cover systems of landfills should consist of the combination of CCLs or GBR-Cs with GBR-Ps. Since the seal at the top of the landfill is not acted upon by chemicals, the synergistic composite effect of polymers and clay soils that facilitates the retention of polar as well as non-polar substances at the bottom of the landfill does not become effective in the capping system. So at the cover the two components do not really act as a composite but rather as a double liner.

Even though GBR-Ps of covers are not exposed to a corrosive chemical environment, the same types of GBR-P could be used for caps as for basal liners. The advantages are high robustness and reliable quality. Their limited flexibility is of some disadvantage. The installation of GBR-Ps of softer polymers such as LDPE would be more favourable with respect to the anticipated deformations of the landfill surface.

The construction requirements and installation techniques are essentially the same for GBR-Ps of the cover as of the bottom liner. The seaming technique and all details of construction quality control and construction quality assurance described for basal liners, apply to covers as well.

The surface of the landfill or of the regulating layer has to be modelled to a shape that allows plane GBR-Ps to be spread without distortions. This design requirement is especially important when HDPE membranes of 2.5 mm thickness are used. It is impossible to place them on three-dimensionally curved surfaces with small diameters of curvature.

Usually landfills are hills with sloping surfaces. So slope stability is a very important issue in designing and constructing landfill covers. Often it is not possible to mobilize enough shear resistance for stability on smooth GBR-P surfaces. Then GBR-Ps with specially structured rough surfaces are used in cover construction. These structured GBR-Ps undergo the same stringent suitability tests as the smooth GBR-Ps for the basal liner do. Particular attention is paid to their long-term tensile strength and stress cracking resistance. In order to avoid tensile

forces in the GBR-P, the mobilized friction at the lower surface of the GBR-P should be greater than at the upper surface. If the slope stability analysis leads to the conclusion that a sufficient safety in the balance of forces can only be reached by additional reinforcing elements, geogrids are placed above the sealing layers of the capping system.

9.8 Construction of geosynthetic barriers

9.8.1 Preparations

The construction materials of the composite basal liner, namely clay soils and GBR-Ps, differ greatly in their material properties. While the mineral component can follow any three-dimensional geometrical feature as long as it can be shaped by earth-moving and compaction equipment, GBR-Ps are plane elements. That is why the subbase has to be designed such that the GBR-P can be spread evenly without distortions. Therefore, in the ideal situation, the surface of the soil consists of only planes that intersect at straight lines.

9.8.2 General aspects of installation

The construction personnel must be highly quality minded. It has to be taken into account that all construction operations at a site are sensitive to weather conditions. The installation of GBR-Ps requires favourable weather. It cannot be carried out in the rain. The minimum temperature for seaming polyethylene sheets is 5 °C. Sufficient time has to be allocated to the placement of GBR-Ps to cope with unavoidable delays arising because of the unfavourable weather that occurs frequently in many parts of Europe.

The manufacturer of the GBR-P must establish his own instructions for handling and installation. If the construction work is not executed by the manufacturer, it must be subcontracted to a specialist. The GBR-P manufacturers list authorized firms for the placement and seaming of the specified GBR-Ps. The construction personnel must be qualified by education and experience. The technicians must be certified welders. The seaming methods to be applied are specified in the approval documents. Strict rules are to be followed for the execution of the construction work.

9.8.3 Placement of geosynthetic barriers

The GBR-P has to be placed without any voids trapped between it and the soil surface. So, ideally, the spread GBR-P should not exhibit any waves. This is very difficult to achieve in practice. In particular, when the weather is fine and sunny, the black polyethylene membrane heats up owing to its high coefficient of thermal expansion. The formation of waves in the GBR-P cannot be avoided under such conditions. However, at night, when the sun disappears and the air temperature

drops, the GBR-P will contract, and the waves will disappear. This physical effect is used systematically. Schicketanz (1992) has developed great expertise in a technology for the placement of GBR-Ps that follows the daily rhythm of temperatures at the construction site.

9.8.4 Welding of polymeric GBRs

Double hot-wedge and extrusion methods are mostly required. The quality of welding work essentially depends on the skills and knowledge of the welder; in landfills, only certified welders should be employed (Corbet and Peters, 1996). Before the welders are allowed to start their work on a landfill construction site, the third-party inspector must satisfy himself that the welders are capable of producing a satisfactory seam with the planned GBR-P's welding machinery and equipment under the conditions of construction site. It is recommended that welding machines that document continuously the welding parameters (the hot-wedge and/or hot-gas temperatures, the force of the rolls and the speed) are used for the fusion welds. The various ambient conditions such as atmospheric humidity, air and GBR-P temperature should also be recorded. The seams are to be tested regarding the external appearance, dimensions, strength and tightness. The visual inspection of the seams and the continuity tests (vacuum, high voltage or compressed air) must be made continuously, and the dimensions and strength tests on random samples. The compressed-air test is used for imperviousness testing of welded seams with a test channel under a defined mechanical stress of 5 bar for 10 min without noticeable loss of pressure. In areas that are not accessible for the automatic hot wedge-welding machine, e.g. sump bottoms, pipe penetrations or patches, the extrusion fillet method is applied. It requires a great deal of good craftsmanship to reach the same quality as the automatic dual hot-wedge fusion technique.

9.8.5 Quality assurance

All personnel responsible for quality management must be experienced in construction with geosynthetics. Only GBR-Ps without any visible flaws are accepted. Experience shows that the quality of GBR-Ps manufactured under a quality assurance system such as that approved in Germany is generally very good. If a GBR-P roll has to be rejected upon delivery at the construction site, the objections are usually due to damage that occurred during loading, transport or unloading. Sometimes the action of unloading the bulky heavy GBR-P rolls from their shipping containers is very tricky, and exercise is needed for the personnel to handle GBR-P rolls successfully without damage.

The quality inspectors have to check whether the seaming equipment is suitable for the job, and whether it functions properly. In particular, the generator for electric power has to meet the demand of the welding operations to warrant uniform seams. Every day at the beginning and at the end of the seaming work, the

controlling parameters of the seaming machine have to be determined by a test strip. The geometry is checked; the seam is examined visually and by peel tests. Once the welding parameters have been established for the day, the work proceeds at a rather constant rate. If the weather conditions change, adjustments have to be made on the basis of new test strips. The seaming machine records the data on advance rate, temperature and pressure automatically and occasional checks are made by the inspector.

Experience shows, that a reliable execution of the construction quality assurance programme is of utmost importance for the GBR-P. Even though the education of the installers is generally very good and, although the construction personnel are aware of the importance of their work, mistakes do occur. Fortunately, they are detected in time and can be corrected without delay, provided that the construction quality assurance personnel are at the site continuously. Sometimes, owners of landfills do not recognize the necessity for the external inspector to be present at the site during the entire period of GBR-P installation, and they order only occasional visits. It is likely that, in such cases, the savings in expenses for the presence of the external supervisor will be more than compensated by extra expenses for corrections and for delays due to deficiencies noticed at a later time.

9.9 References

- August, H., Tatzky, R., Patsuska, G. and Win, T. (1984), 'Untersuchung des Permeationsverhaltens von handelsüblichen Kunststoffdichtungsbahnen als Deponiebasisabdichtung gegenüber Sickerwasser, organischen Lösungsmitteln und deren wäßrige Lösungen', *Forschungsbericht 103 02 208, Abfallwirtschaft, UFOPLAN des Bundesministers des Innern, Im Auftrage des Umwelt Bundesamt, Bundesanstalt für Materialforschung und -prüfung, Berlin.*
- August, H., Tatzky-Gerth, R., Preuschmann, R. and Jakob, I. (1992), 'Permeationsverhalten von Kombinationsdichtungen bei Deponien und Altlasten gegenüber wassergefährdenden Stoffen', *Forschungs- und Entwicklungsvorhaben 102 03 412, Bundesanstalt für Materialforschung und -prüfung, Berlin.*
- Bundesanstalt für Materialforschung und -prüfung (1999), *Richtlinie für die Zulassung von Kunststoffdichtungsbahnen als Bestandteil einer Kombinationsdichtung für Siedlungs- und Sonderabfalldeponien sowie für Abdichtungen von Altlasten, Bundesanstalt für Materialforschung und -prüfung, Berlin.*
- Cazzuffi, D. (1998), 'Long term performance of exposed geomembranes on dams in Italian Alps', in *Proceedings of the 6th International Conference on Geosynthetics* (Ed. R. K. Rowe), Atlanta, Georgia, USA, International Fabrics Association International, Roseville, Minnesota, pp. 1107–1110.
- Corbet, S. P. and Peters, M. (1996), 'First Germany/USA Geomembrane Workshop', *Geotextiles and Geomembranes*, **14**(12), 647–726.
- Duquennoi, C. (2002), 'Containment ponds, reservoirs and canals', in *Geosynthetics and their Applications*, (Ed. S. K. Shukla), Thomas Telford, London, pp. 299–325.
- Egloffstein, T. (1995), 'Properties and test methods to assess bentonite used in geosynthetic clay liners', in *Geosynthetic Clay Liners* (Eds R. M. Koerner, E. Gartung and H. Zanzinger), A. A. Balkema, Rotterdam, pp. 51–72.

- Fleischer, P. and Heibaum, M. (2002), 'Installation of clay geosynthetic barriers under water — three years of experience', in *Clay Geosynthetic Barriers*, (Eds H. Zanzinger, R. M. Koerner and E. Gartung), Swets & Zeitlinger, Lisse, pp. 41–48.
- Flüeler, P. and Böhni, H. (2001), 'The sealing of deep-seated Swiss Alpine Railway tunnels — new evaluation procedure for waterproofing systems', in *Proceedings of the 11th International Techtexil Symposium for Technical Textiles, Nonwovens and Textile-Reinforced Materials*, Messe, Frankfurt, 2001, CD ROM.
- Gartung, E. and Zanzinger, H. (1998), 'Engineering properties and use of geosynthetic clay liners', *Geotechnical Engineering of Landfills* (Eds N. Dixon, E. J. Murray and D. R. V. Jones), Thomas Telford, London, pp. 131–149.
- Gautier, J.-L., Lino, M. and Carlier, D. (2002), 'A record height in dam waterproofing with bituminous geomembrane: La Galaube dam on Alzeau river', in *Proceedings of the 7th International Conference on Geosynthetics* (Eds P. Delmas and J. P. Gourc), Nice, France, A. A. Balkema, Lisse, pp. 975–978.
- Girard, H., Poulain, D., Mine, C. and Potié, G. (1998), 'Installation damage field tests on a geomembrane and waterproofing of the SELVET dam', in *Proceedings of the 6th International Conference on Geosynthetics*, (Ed. R. K. Rowe), Atlanta, Georgia, USA, International Fabrics Association International, Roseville, Minnesota, pp. 1125–1130.
- Göbel, C., Lieberenz, K., Großmann, S. and Horstmann, J. (2002), 'Investigation on the use of geosynthetic clay liners (GCL) as sealing element in railway substructures', in *Clay Geosynthetic Barriers*, (Eds H. Zanzinger, R. M. Koerner and E. Gartung), Swets and Zeitlinger, Lisse, pp. 49–54.
- Heerten, G. (1995), 'Groundwater protection using a GCL at the Franz-Josef-Strauss airport', in *Geosynthetic Clay Liners* (Eds R. M. Koerner, E. Gartung and H. Zanzinger), A. A. Balkema, Rotterdam, pp. 161–174.
- Koerner, R. M. (2005), *Designing with Geosynthetics*, 5th edition, Pearson Prentice Hall, Upper Saddle River, New Jersey.
- Koerner, R. M. and Daniel, D. E. (1995), 'A suggested methodology for assessing the equivalency of GCLs to CCLs', in *Geosynthetic Clay Liners* (Eds R. M. Koerner, E. Gartung and H. Zanzinger), A. A. Balkema, Rotterdam, pp. 73–98.
- Madsen, F. and Nüesch, R. (1995), 'Characteristics and sealing effect of bentonites', in *Geosynthetic Clay Liners* (Eds R. M. Koerner, E. Gartung and H. Zanzinger), A. A. Balkema, Rotterdam, pp. 31–49.
- Monjoie, A., Rigo, J. M. and Polo-Chiapolini, C. (1992), *Vade-mecum pour la Réalisation des Systèmes d'Étanchéité-drainage Artificiels pour les Sites d'Enfouissement Technique en Wallonie*, Faculté des Sciences Appliquées, Université de Liège, Liège.
- Rathmayer, H. G. (2002), 'Guidelines for environmental slope protection at infrastructure', in *Clay Geosynthetic Barriers* (Eds H. Zanzinger, R. M. Koerner and E. Gartung), Swets and Zeitlinger, Lisse, pp. 347–356.
- Schicketanz, R. (1992), 'Wirkungsweise der Kombinationsdichtung und Anforderungen an die mineralische Oberfläche', *Müll und Abfall*, **5**, 287–295.
- Schmidt, R. (1995), 'GCL installation in a water protection area for the A96 motorway near Leutkirch, Germany', in *Geosynthetic Clay Liners* (Eds R. M. Koerner, E. Gartung and H. Zanzinger), A. A. Balkema, Rotterdam, pp. 199–206.
- Sembenelli, P., Sembenelli, G. and Scuero, A. M. (1998), 'Geosynthetic system for the facing of Bovilla Dam', in *Proceedings of the 6th International Conference on Geosynthetics*, (Ed. R. K. Rowe), Atlanta, Georgia, USA, International Fabrics Association International, Roseville, Minnesota, pp. 1099–1106.
- Stief, K. (1995), 'On the equivalency of liner systems — The state of discussions in

Germany', in *Geosynthetic Clay Liners* (Eds R. M. Koerner, E. Gartung and H. Zanzinger), A. A. Balkema, Rotterdam, pp. 3–15.

Federal Ministry for the Environment, Protection of Nature and Safety of Reactors (1991), *Zweite allgemeine Verwaltungsvorschrift zum Abfallgesetz, Teil 1: Technische Anleitung zur Lagerung, chemisch/physikalischen, biologischen Behandlung, Verbrennung und Ablagerung von besonders überwachungsbedürftigen Abfällen, TA Abfall*, Vom 12. März 1991, *Gemeinsames Ministerialblatt*, 42. Jahrgang, No. 8, Carl Heymanns-Verlag, Köln, pp. 139 ff.

Federal Ministry for the Environment, Protection of Nature and Safety of Reactors (1993), *Dritte Allgemeine Verwaltungsvorschrift zum Abfallgesetz, Technische Anleitung zur Verwertung, Behandlung und sonstigen Entsorgung von Siedlungsabfällen, TA Siedlungsabfall*, Vom 14. Mai 1993, *Bundesanzeiger*, Köln.

The use of geosynthetics to improve the performance of foundations in civil engineering

J. G. COLLIN
The Collin Group Ltd, USA


10.1 Introduction

The use of geosynthetics to improve the performance of foundations when constructing on soft compressible foundation soils has evolved considerably over the last two decades. Geosynthetics are being used for the following applications: embankments over soft soils, column-supported embankments (CSEs), shallow foundations constructed over reinforced soil, and bridging voids in the subsurface or roadway shoulders. The mechanism for soil improvement can be as simple as separating native soils from fills or can include tension membrane, soil arching and alteration of failure surfaces. This chapter will focus on two of these applications, namely column-supported embankments and shallow foundations, providing a brief overview of these applications and the research associated with the development of design procedures presented.

The design suggestions presented in this chapter cover the key design issues and the current state of knowledge and state of practice for their use (based on US practice). The state of practice varies considerably across the world and a discussion of this variation is beyond the scope of this chapter. As with any emerging technology, there are still gaps in our knowledge with respect to certain aspects of the design. These gaps will be presented and briefly discussed. However, only with further research will we be able to fill in the gaps in our knowledge.

10.2 Column-supported embankments

The problems associated with constructing highway embankments over soft compressible soil (i.e. large settlements, embankment stability and the long period of time required for consolidation of the foundation soil) have led to the development and/or extensive use of many of the ground improvement techniques in use. Wick drains, surcharge loading, geosynthetic reinforcement, stone columns, deep soil mixing and vibroconcrete columns (VCCs) have all been used to solve the

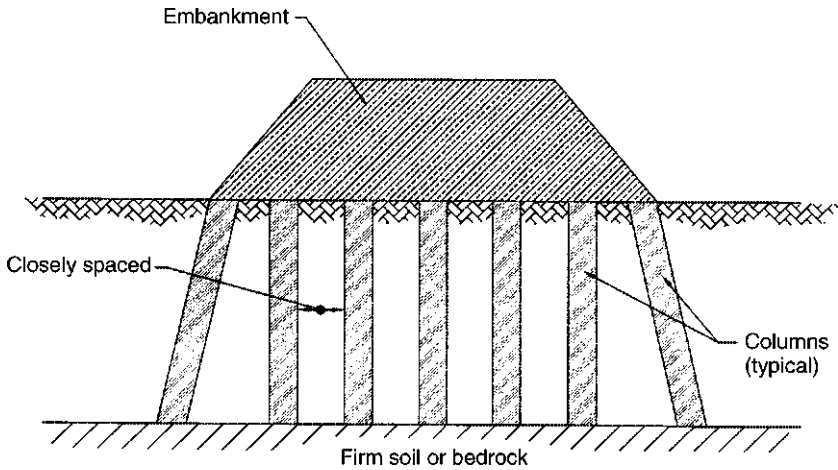


10.1 Conventional CSE (Han, 2003).

settlement and embankment stability issues associated with construction on marginal soils. However, when time constraints are critical to the success of the project, owners have resorted to another innovative approach: CSEs reinforced with geosynthetic reinforcement. In the last 15 years, this technology has been used successfully on numerous projects both in the USA and abroad.

CSEs consist of vertical columns that are designed to transfer the load of the embankment through the soft compressible soil layer to a firm foundation. The selection of the type of column used for the CSE will depend on the design loads, constructability of the column, cost, etc. The load from the embankment must be effectively transferred to the columns to prevent punching of the columns through the embankment fill which causes differential settlement at the surface of the embankment. If the columns are placed close enough together, soil arching will occur and the load will be transferred to the columns. Figure 10.1 shows a conventional CSE. The columns are spaced relatively close together, and some battered columns are required at the sides of the embankment to prevent lateral spreading. In order to minimize the number of columns required to support the embankment and to increase the efficiency of the design, a geosynthetically reinforced load transfer platform (LTP) may be used. The load transfer platform consists of one or more layers of geosynthetic reinforcement placed between the top of the columns and the bottom of the embankment. Figure 10.2 shows schematically a CSE with geosynthetic reinforcement.

10.2.1 Historical overview

The first documented use of a CSE with geosynthetic reinforcement was in 1984 for a bridge approach embankment in Europe (Reid and Buchanan, 1984). Concrete

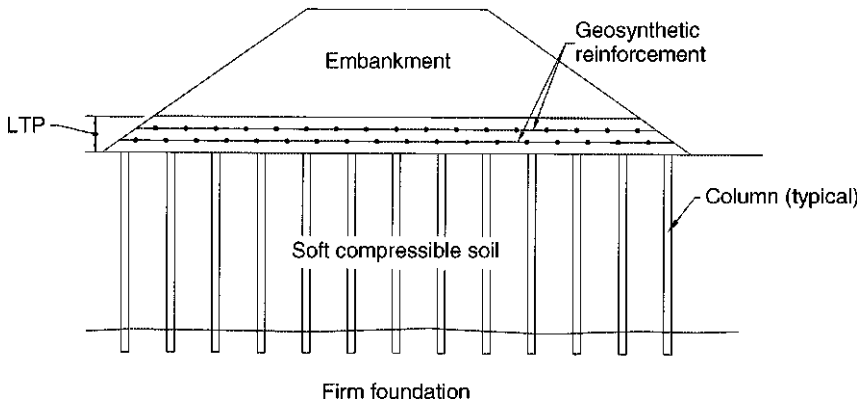

10.2 CSE with geosynthetic reinforcement (Han, 2003).


piles were used as the columns for the project. Each column had a reinforced concrete pile cap. The clear span between pile caps varied from 2 to 3 m (from 6.6 to 10 ft). One layer of geosynthetic reinforcement was used to create the LTP. The height of the embankment was 9 m (29.5 ft).

The first application of a CSE with geosynthetic reinforcement in the USA was in 1994 for the Westway Terminal in Philadelphia, Pennsylvania. This project involved the support of a large-diameter tank for the storage of molasses. The foundation consisted of VCCs and an LTP. The platform consisted of a well-graded granular fill, reinforced with three layers of geogrid reinforcement. The CSE was selected over a more conventional pile foundation with a concrete mat because of both time and money savings.

One of the first (2001) transportation related projects in the USA to use a CSE was for an embankment over soft soils, at a river crossing, for the New Jersey Light Rail (Young *et al.*, 2003). The foundation for the embankment consisted of VCCs and an LTP. The VCCs were placed on a 2.3–3.0 m (6.6–9.8 ft) center-to-centre triangular spacing. The platform was 1 m (3.3 ft) thick and was reinforced with three layers of geogrid. A well-graded granular soil was used as structural fill for the platform. Figure 10.3 shows a typical cross-section of the project. The CSE was selected for this project to eliminate the ‘bump’ at the end of the bridge without having to wait for the foundation soil to consolidate.

The use of a CSE with geosynthetic reinforcement has increased dramatically in the last decade both in the USA and abroad. More than 20 case histories are now available in the literature documenting the use of this technology (Han, 1999).

There is a wide range of columns that may be used for CSE. Conventional (i.e. timber, steel H, steel pipe, precast concrete and cast-in-place concrete shell) piles may be used for pile-supported embankments. However, conventional piles, with the exception of timber piles, have a rather high structural capacity (i.e. 400–2000 kN (90–450 klb)) that is seldom required for CSE and are, therefore, economically

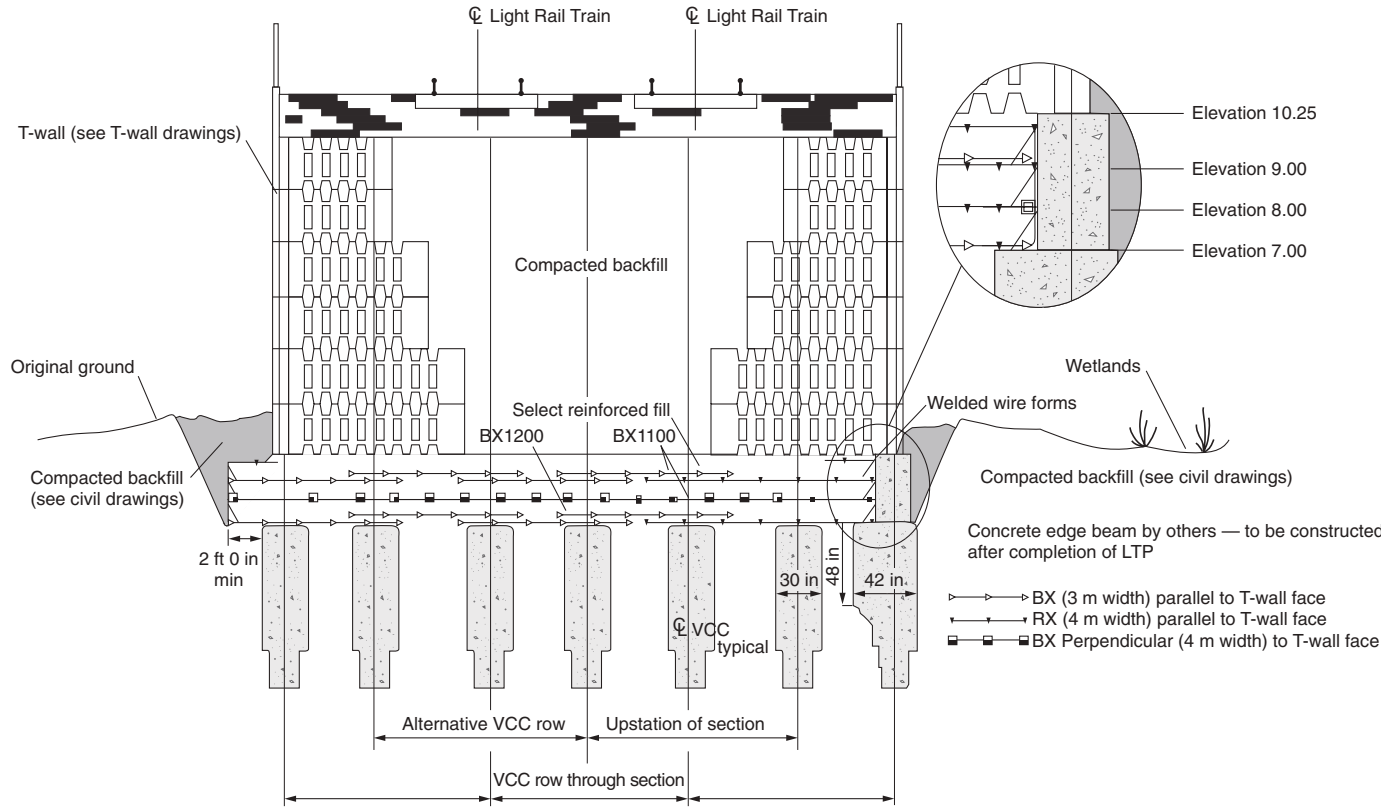

10.3 New Jersey Light Rail project (Young *et al.*, 2003).

not as attractive as non-traditional columns. Augered piles have been used in the USA and Europe with success.

The newer elements that have been used for columns in CSEs include soil mix columns, stone columns, geotextile-encased columns (GECs), geopier-rammed aggregate piers and VCCs.

Combined soil stabilization with vertical columns (CSV) is a new technology that has recently been brought to the USA from Germany. The columns are constructed by introducing dry granular material into the soft foundation soil by an auger, which has a compaction head attached at its tip. The auger rotates in the opposite direction to the pitch of the flights. Soil is, therefore, not removed during the drilling operation, but rather compacted around the auger. As the auger advances into the ground, it compacts the soil around the auger. During withdrawal of the auger, dry granular material (typically a sand cement mix) is transported to the tip of the auger and compacted. CSV columns have typical diameters of 150–200 mm (6–8 in) and have a capacity of 45–90 kN (10–20 kips).

The LTP transfers the embankment load to the columns. Two types of LTPs are available. A reinforced concrete structural mat may be used to transfer the embankment load to the columns. This requires a structural design of the mat to assure that the load is effectively transferred to the columns. Concrete mats have generally been found to be economically cost prohibitive and will not be discussed further.

The second type of LTP consists of one or more layers of geosynthetic reinforcement and select backfill to create a system to transfer the embankment load to the foundation columns, as shown in Fig. 10.2.

10.3 Advantages and disadvantages of column-supported embankments

10.3.1 Advantages

CSEs provide a technical and potentially economical alternative to more conventional construction techniques (i.e. surcharge loading, wick drains and staged construction with or without geosynthetic reinforcement). The key advantage to CSEs is that construction may proceed rapidly in one stage. There is no waiting time for dissipation of pore water pressure in the soft foundation soil. CSEs are also more economical than the removal and replacement of deep poor bearing soils, particularly on larger sites where the groundwater is close to the surface. Where the infrastructure precludes high-vibration techniques, the type of column used for the CSE system may be selected to minimize or eliminate the potential for vibrations. Total and differential settlement of the embankment may be drastically reduced when using CSEs over conventional approaches.

One major benefit of CSE technology is that it is not limited to any one column type. If contaminated soils are anticipated at a site, the column type may be selected

so that there are no spoils from the installation process. If very soft soil is anticipated, VCCs, GECs, augered piles or timber piles may be selected as the column type for the project. In stronger foundation soils, stone columns or rammed aggregate piers may be economically more attractive. The designer has the flexibility to select the most appropriate column for the project.

10.3.2 Disadvantages

A major disadvantage of CSEs is often the initial construction cost when compared with other solutions. However, if the time savings when using CSE technology is included in the economic analysis, the cost may be far less than other solutions.

Another major disadvantage is that there is currently no single well-accepted design procedure. There are many different design approaches, and they all give different results. Without some standardization of the LTP design, the technology will be limited in its use and acceptance.

10.4 Feasibility evaluations


CSEs may be used whenever an embankment must be constructed on soft compressible soil. To date, the technology has been limited to embankment heights in the range of 10 m. The depth of the soft soil layer is not a critical component in the determination of feasibility because of the many different types of column available for use.

A generalized summary of the factors that should be considered when assessing the feasibility of utilizing CSE technology on a project is presented below. This summary is empirically based on the present author's experience with the design and successful construction of over 20 CSE projects in the USA.

- 1 The clear span between columns should be less than the embankment height and should not exceed 3 m (10 ft). This requirement is based on documented case histories. Wider clear spans may lead to unacceptable differential settlement between columns.
- 2 The fill required to create the LTP shall be a select structural fill with an effective friction angle greater than or equal to 35° .
- 3 The columns shall be designed to carry the entire load of the embankment.
- 4 CSE technology reduces-post construction settlements of the embankment surface to typically less than 50–100 mm (2–4 in).

10.5 Design concepts

The design of CSEs is a complex soil–structure interaction problem. There are currently several empirical methods for the design that focus predominantly on the analysis of the load transfer platform. The methods that will be presented in this

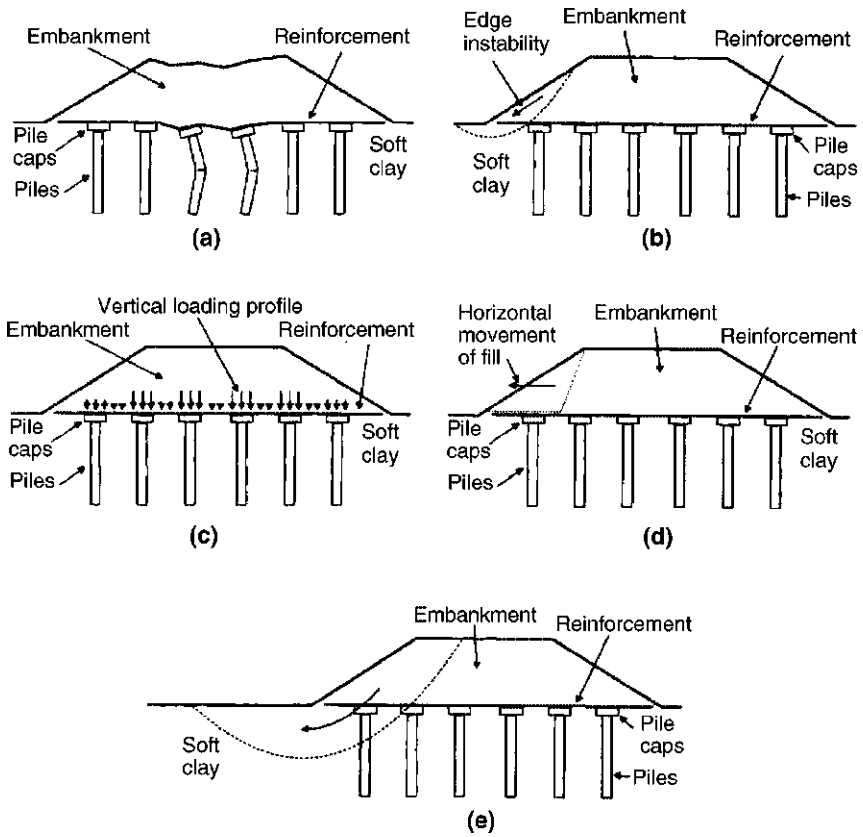


10.4 Limit state failure modes (British Standards Institution, 1995): (a) pile group capacity; (b) pile group extent; (c) vertical load shedding; (d) lateral sliding; (e) overall stability.

chapter include the British Standard BS 8006 (British Standards Institution, 1995), the Swedish method, the German method and the Collin method. Each approach has been used successfully on numerous projects and, through those projects, each method has been demonstrated to work well.

10.5.1 Fundamental concepts

The design of CSEs must consider both the limit state and serviceability state failure criteria. The limit state failure modes are shown in Fig. 10.4. The columns must be designed to carry the vertical load from the embankment without failing [Fig. 10.4(a)]. The columns are typically assumed to carry the full load from the embankment. The lateral extent of the columns under the embankment must be determined [Fig. 10.4(b)]. The LTP must be designed to transfer the vertical load from the embankment to the columns [Fig. 10.4(c)]. The potential for lateral

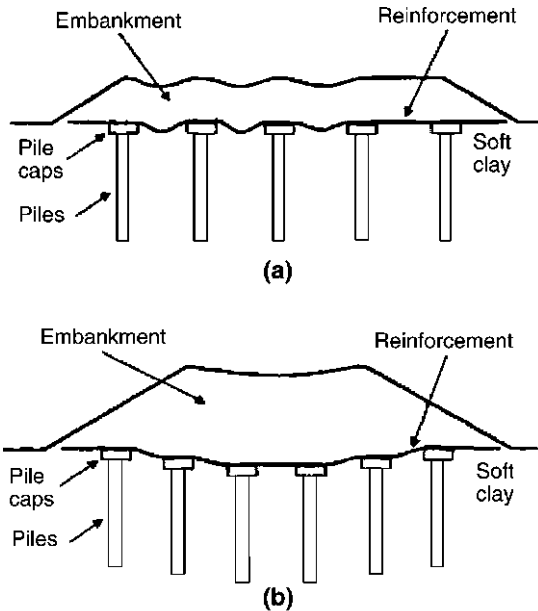


10.5 Serviceability state (British Standards Institution, 1995): (a) reinforcement strain; (b) foundation settlement.

sliding of the embankment on top of the columns must be addressed [Fig. 10.4(d)]. Finally, global stability of the system must be evaluated [Fig. 10.4(e)].


In addition to a limit state analysis, serviceability state design must be considered. The strain in the geosynthetic reinforcement used to create the LTP should be kept below some maximum threshold to preclude unacceptable deformation reflection (i.e. differential settlement) at the top of the embankment. Settlement of the columns must also be analysed to assure that unacceptable settlement of the overall system does not occur, as shown in Fig. 10.5.

The general design steps for a CSE are as follows:

- Step 1* Estimate the preliminary column spacing (use feasibility assessment guidelines).
- Step 2* Determine the required column load.
- Step 3* Select preliminary column type based on the required column load and site geotechnical requirements.
- Step 4* Determine the capacity of the column to satisfy the limit and serviceability state design requirements.
- Step 5* Determine the extent of columns required across the embankment width.
- Step 6* Select the LTP design approach (i.e. catenary or beam).
- Step 7* Determine the reinforcement requirements based on the estimated column spacing (Step 1). Revise the column spacing as required.
- Step 8* Determine the reinforcement requirements for lateral spreading.

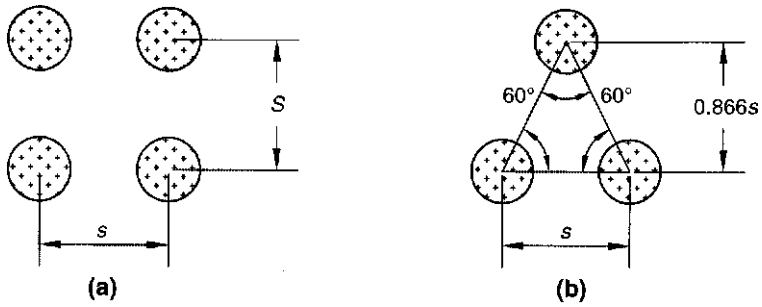

$D_e = 1.05s$ for triangular spacing
 $D_e = 1.13s$ for square spacing

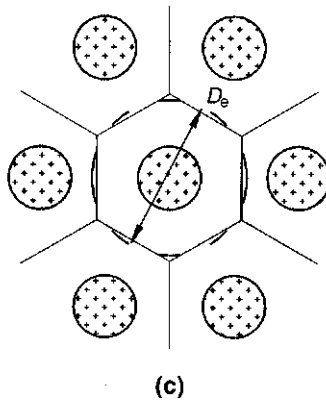

10.6 Column layout: (a) square spacing; (b) triangular spacing; (c) effective diameter.

- Step 9 Determine the overall reinforcement requirements based on LTP and lateral spreading.
- Step 10 Check the global stability.
- Step 11 Prepare the construction drawings and specifications.

10.5.2 Column design

The selection of column type is most often based on constructability, load capacity, and cost. The load that a column is required to carry is typically based on the tributary area for each column. In the USA, the embankment and any surcharge load are typically assumed to be carried in their entirety by the columns.

For purposes of determining the design vertical load in the column, it is convenient to associate the tributary area of soil surrounding each column, as illustrated in Fig. 10.6. Although the tributary area forms a regular hexagon about the column, it can be closely approximated as an equivalent circle having the same

total area. For a square column pattern, the effective diameter D_e is equal to 1.13 times the centre-to-centre column spacing. For a triangular column pattern, the effective diameter is equal to 1.05 times the centre-to-centre column spacing [a typical centre-to-centre column spacing ranges from 1.5 to 3.0 m (from 5 to 10 ft)].

The required design vertical load Q_r in the column is determined according to:

$$Q_r = \pi \left(\frac{D_e}{2} \right)^2 (\gamma H + q) \quad [10.1]$$

where:

D_e = effective tributary area of column

H = height of embankment

q = live and dead load surcharge (typically 12 kN/m² (250 lbf/ft²))

γ = unit weight of the embankment soil.

The design of concrete, steel and timber piling is well established. Design guidelines have been developed by the Federal Highway Administration (FHWA) and may be found in *Design and Construction of Driven Pile Foundations* (Hannigan *et al.*, 1998). For the design of timber piles, the reader is also referred to the book by Collin (2002). The design and construction of micropiles has been provided by Armour *et al.* (2000).

The vertical load capacity design of VCC, and CSV is not well defined and is typically performed by the contractor. The design verification for these systems is typically achieved with a static load test.

10.5.3 Edge stability; lateral extent of columns


The lateral extent of the column system across the width of the embankment should extend a sufficient distance beyond the edge of the embankment to ensure that any instability or differential settlement that occurs outside the column-supported area will not affect the embankment crest [Fig. 10.4(b)]. There are several approaches that may be used to check the edge stability. The computer software ReSSA developed for the FHWA for the design of both reinforced and non-reinforced slopes and embankments is an excellent tool for checking edge stability.

BS 8006 (British Standards Institution, 1995) requires that the columns extend to within a minimum distance L_p of the toe of the embankment. Figure 10.7 defines the terms for edge stability. L_p is determined from:

$$L_p = H (n - \tan \theta_p) \quad [10.2]$$

where:

n = side slope of the embankment

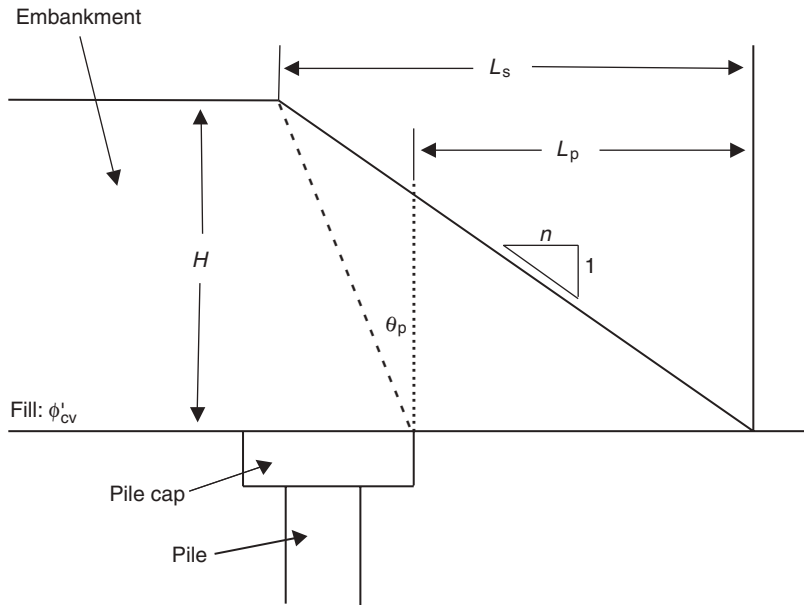

10.7 Edge stability (British Standards Institution, 1995).

θ_p = is the angle (from vertical) between the outer edge of the outer-most column and the crest of the embankment ($\theta_p = 45 - \phi_{emb}/2$).
 ϕ_{emb} = effective friction angle of embankment fill.

The British method is an excellent check of the more rigorous stability analysis using limit equilibrium techniques (i.e. ReSSA). For preliminary designs and/or feasibility analysis, the simplified British approach is sufficient.

10.5.4 Lateral spreading


The potential for lateral spreading of the embankment must be analysed (Fig. 10.8). The geosynthetic reinforcement must be designed to prevent lateral spreading of the embankment. This is a critical aspect of the design, as many of the columns that are appropriate for CSEs are not capable of providing adequate lateral resistance to prevent spreading of the embankment without failing.

The geosynthetic reinforcement must be designed to resist the horizontal force due to the lateral spreading of the embankment. The required tensile force T_{ls} to prevent lateral spreading is determined from:

$$T_{ls} = \frac{K_a (\gamma H + q) H}{2} \tag{10.3}$$

where:

K_a = coefficient of active earth pressure ($\tan^2 (45 - \phi_{emb}/2)$)

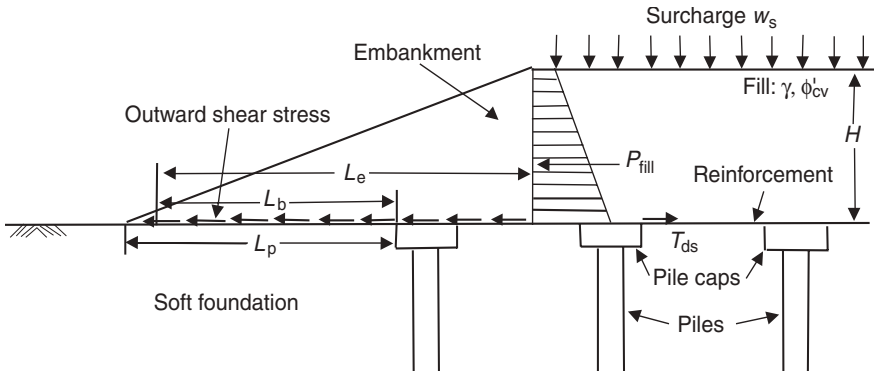

10.8 Lateral spreading (British Standards Institution, 1995).

The minimum length L_e of reinforcement necessary to develop the required strength of the reinforcement without the side slope of the embankment sliding across the reinforcement is determined using:

$$L_e = \frac{T_{ls}}{0.5\gamma H(c_{iemb} \tan \phi_{emb})} \quad [10.4]$$

where:


c_{iemb} = coefficient of interaction for sliding between the geosynthetic reinforcement and embankment fill.

10.5.5 Load transfer platform design

There are two fundamentally different approaches to the design of the LTP. The first approach, which is used by BS8006 (British Standards Institution, 1995), the Swedish method (Rogbeck *et al.*, 1998, 2002), and the German method (Alexiew and Gartung, 1999; Alexiew, 2003) is for the reinforcement to act as a catenary. The reinforcement transfers the load from the embankment fill to the columns through catenary tension in the reinforcement, as shown in Fig. 10.9. In essence, the reinforcement behaves as a structural element, and any benefits achieved by the creation of a composite-reinforced soil mass are ignored. The primary assumptions in the catenary theory are as follows:

- 1 A soil arch forms in the embankment.
- 2 Reinforcement is deformed during loading.
- 3 One layer of reinforcement is used; if more than one layer of reinforcement is used, only the tensile strength of the multiple layers is considered.

The second approach for the design of the LTP (the Collin method) is to use

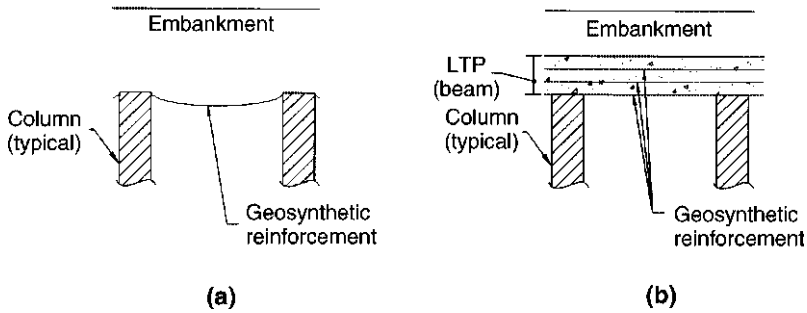

10.9 Load transfer mechanisms: (a) catenary theory; (b) beam theory.


multiple layers of reinforcement to create a stiff reinforced soil mass. The Collin method is a refinement of a method sometimes referred to as the Guido method (Hewlett and Randolph, 1988; Bell *et al.*, 1994; Jenner *et al.*, 1998). The reinforced soil mass acts as a beam to transfer the load from the embankment above the platform to the columns below. The primary assumptions for the beam theory are as follows:

- 1 A minimum of three layers of reinforcement is used to create the platform.
- 2 Spacing between layers of reinforcement is 200–450 mm (8–18 in).
- 3 Platform thickness is greater than or equal to one half of the clear span between columns.
- 4 A soil arch is fully developed within the depth of the platform.

The catenary method generally requires higher strength reinforcement for the same design conditions, as opposed to the beam method (i.e. column spacing and embankment height). The beam method will generally allow for larger column-to-column spacing than the catenary method for standard geosynthetics (i.e. materials available off the shelf).

All LTP design methods covered in this chapter consider soil arching. Soil arching is defined by McNulty (1965) as ‘the ability of material to transfer loads from one location to another in response to a relative displacement between locations’. Terzaghi and Peck (1967) explained arching theory using the ‘trapdoor’ analogy. If a dry cohesionless sand is placed on a platform that contains a trapdoor and the trapdoor is mounted on a scale, then, according to Terzaghi and Peck (1967): ‘As long as the trapdoor occupies its original position, the pressure on the trapdoor as well as that on the adjoining platform is equal to γH per unit area. However, as soon as the trapdoor is allowed to yield in a downward direction, the pressure on the door decreases to a small fraction of its initial value, whereas the pressure on the adjoining parts of the platform increase.’ This phenomenon of pressure transfer is known as ‘arching’.

In addition to soil arching, the LTP design includes tension membrane theory. The vertical load from the soil within the arch and any surcharge load, if the

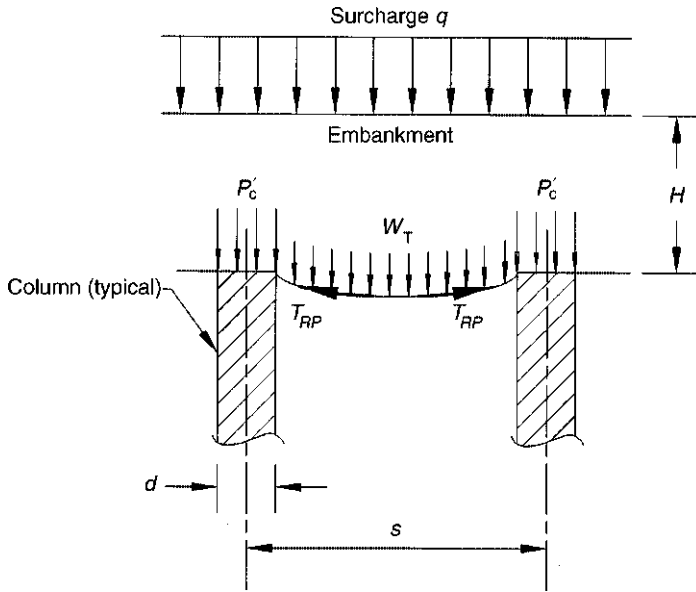

10.10 Definition of terms.

thickness of the embankment is not great enough to develop the full arch, is carried by the reinforcement. There are several theories available to estimate the tension in the reinforcement (Fluet *et al.*, 1986; Giroud *et al.*, 1990). A detailed discussion on tension membrane theory is beyond the scope of chapter.

The symbols used by the BS 8006, the Swedish standard, the German method, and the Collin method have been standardized for ease of reference. Figure 10.10 shows the common symbols that will be used in presenting these methods. They are defined as follows:

- d = diameter of the column
- H = height of embankment
- P'_c = vertical stress on the column
- q = surcharge load
- s = centre-to-centre column spacing
- T_{RP} = tension in the extensible reinforcement
- W_T = vertical load carried by the reinforcement.

BS 8006

The British Standard BS8600 (British Standards Institution, 1995) recommends that the embankment height be a minimum of 1.4 times the clear span between columns. This is to ensure that differential settlement cannot occur at the surface of the embankment. Soil arching between adjacent columns induces greater

vertical stresses on the columns than on the surrounding foundation soil. The ratio of the vertical stress on the columns to the average vertical stress at the base of the embankment is determined from the following equation and is based on the formula given by Marston and Anderson (1913):

$$\frac{P'_c}{\sigma'_v} = \left(\frac{C_c d}{H} \right)^2 \quad [10.5]$$

where:

P'_c = vertical stress on the column

σ'_v = the average vertical stress at the base of the embankment equal to

$$f_{fs} \gamma H + f_q q$$

f_{fs} = partial soil unit mass load factor (equal to 1.3)

f_q = partial surcharge load factor (equal to 1.3)

C_c = arching coefficient, equal to $1.95H/d - 0.18$ for end bearing columns (unyielding), and to $1.50H/d - 0.07$ for frictional columns (normal)

d = column diameter.

The vertical load carried by the reinforcement spanning between columns for the case where $H > 1.4(s - d)$ may be determined as follows:

$$W_T = \frac{1.4 s f_{fs} \gamma (s - d)}{s^2 - d^2} \left(s^2 - d^2 \frac{P'_c}{\sigma'_v} \right) \quad [10.6]$$

where:

s = centre-to-centre spacing between columns.

For the case where $0.7(s - d) < H < 1.4(s - d)$, the distributed vertical load carried by the reinforcement is determined from

$$W_T = \frac{s f_{fs} \gamma H + f_q q}{s^2 - d^2} \left(s^2 - d^2 \frac{P'_c}{\sigma'_v} \right) \quad [10.7]$$

The tension T_{rp} in the extensible reinforcement per lineal metre of reinforcement resulting from the distributed load is:


$$T_{rp} = 0.5 W_T \frac{s - d}{d} \left(1 + \frac{1}{6\varepsilon} \right)^{0.5} \quad [10.8]$$

where:

ε = strain in the reinforcement.

The initial tensile strain in the reinforcement is needed to generate a tensile load. BS 8006 recommends that a practical upper limit of 6% strain be imposed to ensure all embankment loads are transferred to the piles.

The tensile load T_{rp} develops as the reinforcement deforms under the weight of the embankment. This normally occurs during construction of the embankment

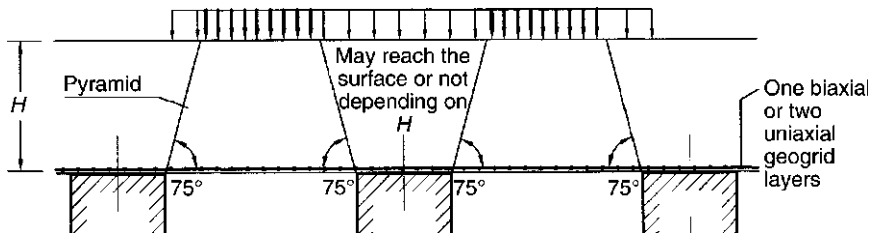

10.11 Swedish method soil arch (Rogbeck *et al.*, 2002).

but, in situations where the reinforcement cannot deform during construction, the reinforcement will not carry the applied loads until the foundation settles. The above equation is appropriate for those reinforcements that can undergo deformation during loading (i.e. extensible reinforcements). For inextensible reinforcements, alternative relationships should be used to determine their required strength.


The long-term strain in the reinforcement (due to creep) should be kept to a minimum to ensure that the long-term localized deformations do not occur at the surface of the embankment. A minimum creep strain of 2% over the design life of the reinforcement should be allowed.

The Swedish method

The Swedish method (Rogbeck *et al.*, 2002) has many similarities to the BS 8006. The Swedish method is valid when the following assumptions and parameters are satisfied.

- 1 Arch formation occurs.
- 2 The reinforcement is deformed during loading.
- 3 One layer of reinforcement is used.
- 4 The reinforcement is located within 0.1 m (4 in) above the column.
- 5 The embankment height is greater than or equal to the clear distance between columns.
- 6 The ratio of column or column cap area to influence area per column is greater than or equal to 10%.
- 7 The embankment fill effective friction angle is 35°.
- 8 The initial strain in the reinforcement is limited to 6%.
- 9 Long-term (creep) strain is limited to 2%.
- 10 The total strain is less than 70% strain at failure.

Figure 10.11 shows the model used in the Swedish method to determine the vertical load carried by the reinforcement. The cross-sectional area of the soil under the arch, which is the load carried by the reinforcement, is approximated using the soil wedge shown in Fig. 10.11. This applies even when the embankment height is lower than the top of the soil wedge [i.e. $(s - d)/(2 \tan 15^\circ)$].

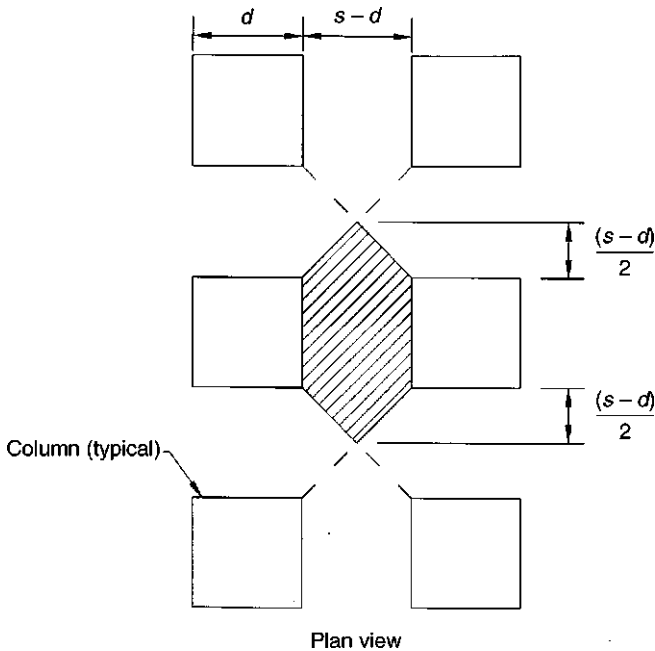

10.12 Swedish method: load distribution between columns (Rogbeck *et al.*, 2002).

The two-dimensional weight W_T of the soil wedge is determined from:

$$W_T = \frac{(s - d)^2 \gamma}{4 \tan 15^\circ} \text{ per unit length in depth} \tag{10.9}$$

The three-dimensional effects are estimated through load distribution, where the load is distributed over the surface according to Fig. 10.12 and is taken up by the reinforcement along the edge of the column. The force in the reinforcement, per lineal metre of depth, due to the vertical load in three dimensions is calculated using the equation:

$$T_p = 0.5 \left(1 + \frac{s}{d} \right) W_T \left(1 + \frac{1}{6\varepsilon} \right)^{0.5} \tag{10.10}$$

The German method

The German method (Alexiew and Gartung, 1999; Alexiew, 2003) unlike either the BS 8006 or the Swedish method, considers the effect of the soft foundation soil in determining the load carried by the reinforcement. Specifically, the undrained shear strength of the foundation soil is considered to provide some resistance to the

vertical load from the embankment. The German method also directly considers the shear strength of the embankment material in determining the arching within the embankment. This method is only valid when the height H of the embankment is greater than the column spacing s .

Two failure criteria are considered: failure of the embankment fill at the crown of the arch (typically controls for light surcharge loads and large column spacing); failure at the bearing point of the arch. The ratio E of the vertical load on the columns to the average load at subgrade is a function of which failure mode controls the design.

For failure to occur at the crown of the arch (this condition occurs for relatively shallow embankments with wide column spacing) E is determined from:

$$E = 1 - \left[1 - \left(\frac{d}{s} \right)^2 \right] (A - AB + C) \quad [10.11]$$

where:

$$A = \left(1 - \frac{d}{s} \right)^{2(K_p - 1)} \quad [10.12]$$

$$B = \frac{s}{1.41H} \frac{2K_p - 2}{2K_p - 3} \quad [10.13]$$

$$C = \frac{s - d}{1.41H} \frac{2K_p - 2}{2K_p - 3} \quad [10.14]$$

$$K_p = \frac{1 + \sin \phi'}{1 - \sin \phi'} \quad [10.15]$$

and where:

ϕ' = effective friction angle of the embankment fill.


Failure at the bottom of the arch must also be analyzed with the following equation:

$$E = \frac{\beta}{(1 + \beta)} \quad [10.16]$$

where:

$$\beta = \frac{2K_p}{(K_p + 1)(1 + d/s)} \left[\left(\frac{1 - d}{s} \right)^{-K_p} - \left(1 + \frac{K_p d}{s} \right) \right] \quad [10.17]$$

The minimum value of E controls the stress σ_s applied to the soil between columns. The stress that is applied to the soil between columns (Fig. 10.13) is determined from:

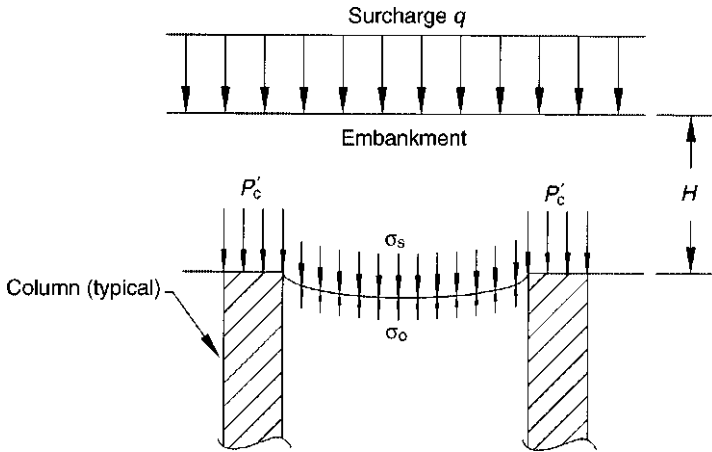

10.13 German method.

$$\sigma_s = \frac{\gamma H + q}{(s^2 - d^2)(1 - E)s^2} \tag{10.18}$$

The geosynthetic reinforcement is subjected to the stress σ_s on the soil less a vertical reaction stress produced by the supporting effect of the soil between columns (i.e. the bearing capacity) (Fig. 10.13). The factored (e.g. safety factor of 2) undrained shear strength c_u of the soil is used to determine the bearing capacity of the foundation soil. The equation for determining this allowable stress σ_o is:

$$\sigma_o = \frac{(2 + \pi)c_u}{FS} \tag{10.19}$$

where:

FS = factor of safety for undrained shear strength (typically 2).


The vertical load W_T on the geosynthetic reinforcement spanning between columns is determined as follows:

$$W_T = \frac{\sigma_s(s^2 - d^2)}{2(s' - d)} - \frac{\sigma_o(s^2 - d^2)}{2(s' - d)} \text{ per lineal metre} \tag{10.20}$$

where:

$s' = s$ for a square-column pattern, and $1.4s$ for a triangular-column pattern.

For the case of more than one layer of reinforcement, the vertical load W_T may be distributed between the layers proportionally to their strain resistance. The German method, presented above, is based on the fact that the reinforcement is located vertically, less than 0.5 m (1.6 ft) above subgrade. Special procedures are provided

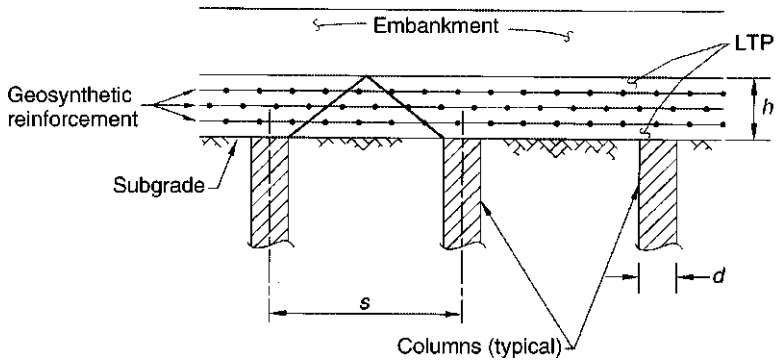

10.14 LTP.

by the German method for the case where the reinforcement is located between 0.5 and 1 m (between 1.6 and 3.3 ft) above subgrade (Kemfert *et al.*, 1997).

The tensile force in the reinforcement per unit length of reinforcement is determined on the basis of catenary tension and is determined by:



$$T_{rp} = W_T \frac{(s' - d)}{2d} \left(1 + \frac{1}{6\epsilon} \right)^{0.5} \quad [10.21]$$

The Collin method

The Collin method (Elias *et al.*, 2004) is fundamentally different from BS8006, the Swedish method or the German method (Collin *et al.*, 2005a). The Collin method is based on the premise that the reinforcement (minimum of three layers of reinforcement) creates a stiffened beam of reinforced soil that distributes the load from the embankment above the LTP (i.e. stiffened beam) to the columns below the platform (Fig. 10.14).

The Collin method is based on the following assumptions:

- 1 The thickness h of the LTP is equal to or greater than one half of the clear span $s - d$ between columns.
- 2 A minimum of three layers of extensible (geosynthetic) reinforcement is used to create the load transfer platform.
- 3 Minimum distance between layers of reinforcement is 200 mm (8 in).
- 4 Select fill is used in the LTP.
- 5 The primary function of the reinforcement is to provide lateral confinement of the select fill to facilitate soil arching within the height (thickness) of the LTP.
- 6 The secondary function of the reinforcement is to support the wedge of soil below the arch.
- 7 All the vertical load from the embankment above the LTP is transferred to the columns below the platform.
- 8 The initial strain in the reinforcement is limited to 5%.

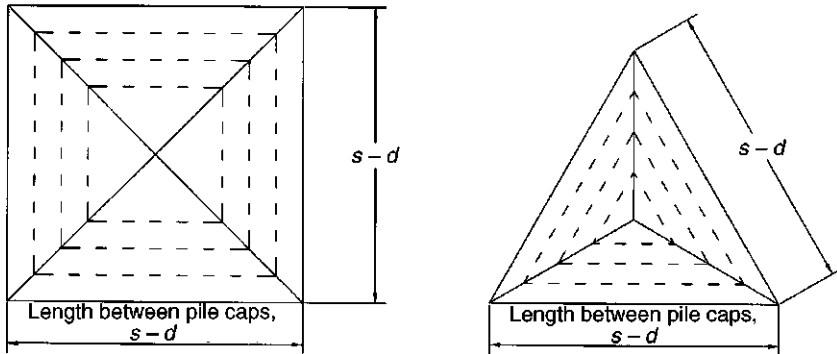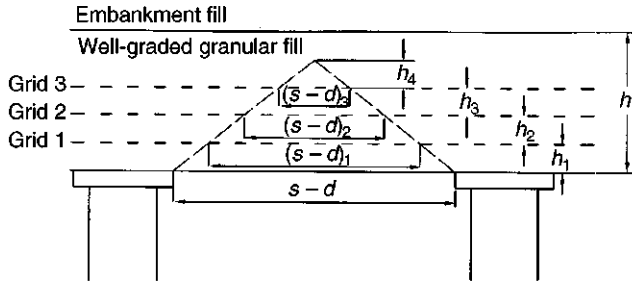

10.15 LTP design for the Collin method.

The vertical load carried by each layer of reinforcement is a function of the column spacing pattern (i.e. square or triangular) and the vertical spacing of the reinforcement. Each layer of reinforcement is designed to carry the load from the platform fill that is within the soil wedge below the arch. The fill load attributed to each layer of reinforcement is the material located between that layer of reinforcement and the next layer above (Fig. 10.15).

The uniform vertical load W_{Tn} on any layer n of reinforcement may be determined from:

$$W_{Tn} = \frac{[(\text{area at reinforcement layer } n + \text{area at reinforcement layer } n + 1)/2] (\text{layer thickness}) (\text{LTP fill density})}{\text{area at reinforcement layer } n}$$

For a triangular pattern,

$$W_{Tn} = \frac{[(s-d)_n^2 + (s-d)_{n+1}^2] \sin 60^\circ h_n \gamma}{(s-d)_n^2 \sin 60^\circ} \tag{10.22}$$

and for a square pattern,

Table 10.1 Values of Ω

Ω	Reinforcement strain (ϵ) (%)
2.07	1
1.47	2
1.23	3
1.08	4
0.97	5

$$W_{Tn} = \frac{[(s-d)_n^2 + (s-d)_{n+1}^2]h_n \gamma}{(s-d)_n^2} \quad [10.23]$$

The tensile load in the reinforcement is determined on the basis of tension membrane theory (Giroud *et al.*, 1990), and is a function of the amount of strain in the reinforcement. The tension in the reinforcement is determined from

$$T_{rpn} = \frac{W_{Tn} \Omega D}{2} \quad [10.24]$$

where:

D = design spanning for tension membrane (dimensionless factor) equal to $(s-d)_n$ for square-column spacing and to $(s-d)_n \tan 30^\circ$ for triangular-column spacing

Ω = dimensionless factor given in Table 10.1.

The modified Collin (beam) method

Based on research recently completed (Collin *et al.*, 2005b; Han and Collin, 2005; Huang *et al.*, 2005a, 2005b) using numerical modelling, the above procedure has been modified. The modification involves the addition of one layer of reinforcement at subgrade. This layer of reinforcement is designed as a catenary to carry the load from the soil below the arch (Fig. 10.16).

The uniform vertical load W_{TC} on the catenary layer of reinforcement may be determined from:

$$W_{TCn} = \frac{(\text{volume pyramid below the arch}) (\text{LTP fill density})}{\text{area at reinforcement catenary layer}}$$

For square- or triangular-column spacing,

$$W_{Tn} = \frac{h_n \gamma}{3} \quad [10.25]$$

The tensile load in the reinforcement is determined on the basis of tension

Table 10.2 LTP design method summary

Method	Design approach	Number of reinforcement layers	Angle of arch from horizontal (deg)	Subgrade support	Allowable strain ϵ in reinforcement (%)
British	Catenary	1 ^a	70	No	6
Swedish	Catenary	1 ^a	75	No	6
German	Catenary	1 ^a	NA ^b	Yes	5–6
Collin	Beam	≥ 3	45	Yes	5

^aMore than one layer of reinforcement may be used, based on the required strength of the reinforcement. However, the layers are not discretely placed with a minimum of 200 mm (8 in) between layers, as in the Collin method.

^bNA, not applicable.

membrane theory and is a function of the amount of strain in the reinforcement. The tension in the reinforcement is determined from:

$$T_{rPC} = \frac{W_{TC} \Omega D}{2} \tag{10.26}$$

where:


D = design span for the tensioned membrane equal to $1.41\{(s - d) - 2[\sum \text{vertical spacing}/(\tan 45^\circ)]\}$ for square-column spacing, and to

$0.867\{(s - d) - 2[\sum \text{vertical spacing}/(\tan 45^\circ)]\}$ for triangular-column spacing

Ω = dimensionless factor from tensioned membrane theory.

The reinforcement to create the beam above the catenary layer of reinforcement is designed according to Equations [10.22]–[10.24].

The design methods summarized in this section have many similarities. However,

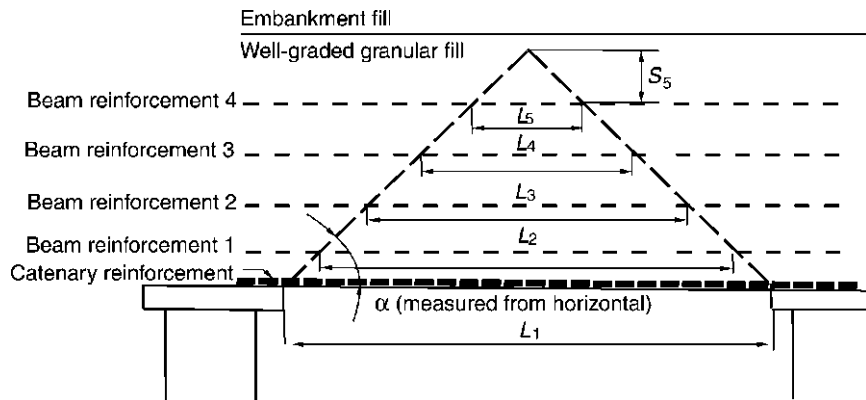

10.16 Modified Collin method reinforcement.

there are significant differences between the approaches that deal with the fundamental concepts of the load transfer platform. Table 10.2 provides a summary of these differences.

The use of CSEs is expanding both in the USA and abroad. Numerous design guidelines have been developed for the design. Currently, there are at least five to ten methods to design the LTP. The beam method presented here is one that has been developed by the present author and used with great success. However, the recommendations provided here cover only the basic steps in the design of the LTP. The detailing of the platform (i.e. edge detail), selection of geosynthetic reinforcement, creep characteristics of the geosynthetic, overlaps, etc., are beyond the scope of this chapter but must be considered in the design.

10.5.6 Reinforcement total design load

Independent of the method used to analyze the LTP, the total (maximum) design load T_{total} in the geosynthetic reinforcement should be determined as follows: in the direction along the length of the embankment

$$T_{\text{total}} = T_{\text{rp}}$$

and, in the direction across the width of the embankment

$$T_{\text{total}} = T_{\text{rp}} + T_{\text{ls}}$$


10.5.7 Global stability

Global stability of CSEs may be evaluated using limit equilibrium computer software, taking into consideration the added shear resistance of the columns and the tensile capacity of the geosynthetic reinforcement. Figure 10.17 shows the approach used in the BS 8006 for incorporating the benefit of the columns and geosynthetic.

While it is recommended that the global stability of the CSE be evaluated, it is the present author's opinion that, if the behaviour is that of a true CSE with an LTP, there is very little potential for a global stability problem.

10.5.8 Settlement

Total settlement of the CSE will be a function of the column design. For methods to estimate settlement, the reader is referred to numerous geotechnical engineering textbooks. Differential settlement between columns caused by the LTP should be less than 20–30 mm (0.8–1.2 in) when the LTP design follows the guidelines established for BS 8006, the Swedish method, or the Collin method. When using the German method, differential settlement calculations are required.

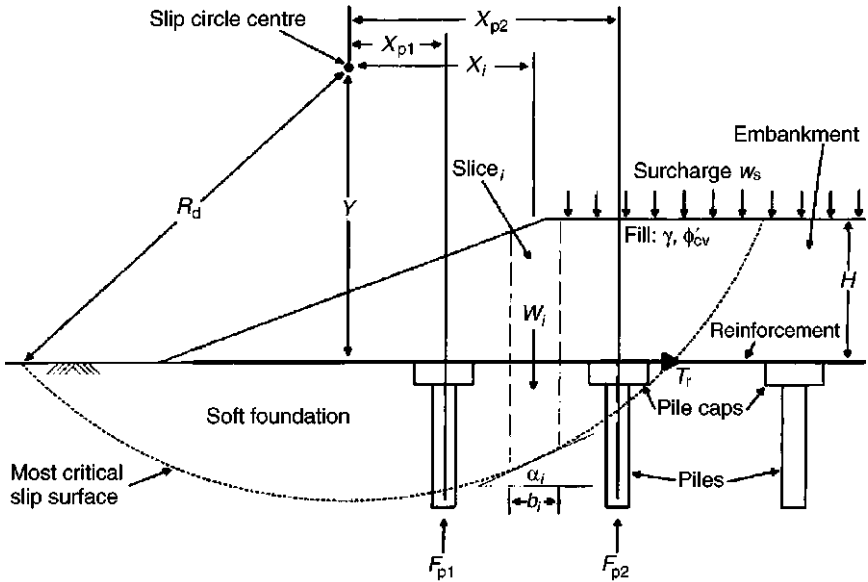

10.17 Variables used in the global stability analysis (British Standards Institution, 1995).

10.5.9 Current research needs

Gabr and Han (2005) suggested some directions for further study. The current design methods should be validated by full-scale well-instrumented field measurements investigating strains in the geosynthetic, deformation characteristics and stress distribution between column and native soil.


Soil-arching models currently employed assume rigid supports at the edges; for certain types of deformable soil improvement method, this assumption may be valid but, for other soil improvement techniques that result in less stiff columns, this assumption needs further verification. The current design methods do not allow the designer to estimate total and differential settlements. Finally, the effect of soil resistance between the native soil and the geosynthetics layer and the effect of geosynthetics creep within the formed earth beam are also poorly understood.

To apply tensioned membrane theory properly, sufficient strain must develop in the geosynthetic to result in some tension. As a result, there will be some displacement that occurs to generate this strain. This deformation typically occurs during placement and compaction of the embankment fill. However, further research is needed to verify this observation.

10.6 Geosynthetic-reinforced soil foundations

10.6.1 Overview

The use of geosynthetics in civil engineering applications is increasing annually.

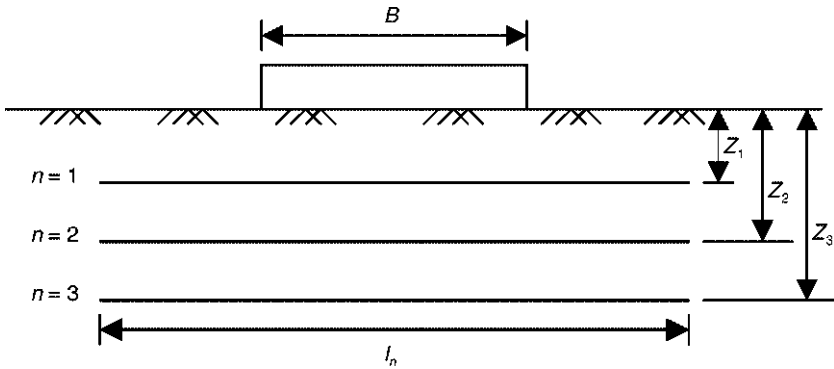

10.18 Schematic diagram of a GRSF (Munfakh *et al.*, 2001).

One new application, the construction of a geosynthetic-reinforced soil foundation (GRSF) to support a shallow spread footing has considerable potential as a cost-effective alternative to over-excavation and replacement, consolidation, densification and chemical stabilization. In this technique, one or more layers of a geosynthetic reinforcement and controlled fill are placed below a shallow spread footing to create a composite material with improved performance characteristics over the existing foundation soils (Fig. 10.18).

Reinforcement of fill or natural soils with geosynthetics beneath shallow foundations has been explored for nearly three decades, after the pioneering soil reinforcement work of Binquet and Lee (1975a, 1975b). Das (1995) summarized results of predominantly small model strip or square footings in test boxes filled with sand or clay. Their work has identified, for the situations tested, a series of bounds on reinforcement spacing, number of reinforcing layers, total reinforced depth and reinforcement width, i.e. they have identified dimensions relative to the width of the footing where no additional benefit is gained. These tests seem to suffer from unknown scale effects, as explained by Michalowski (2004), and it is unclear whether the findings are general enough to apply to other soils.

Adams and Collin (1997) performed the first (and, to this date only) prototype-scale tests on square footings. This work was sponsored by the FHWA and was performed at Turner–Fairbank Highway Research Center in a large test pit filled with sands reinforced with geogrids and geocells. Their results seemed to confirm some of the relationships noted by Das and his colleagues and showed that an increase in bearing capacity could be obtained using reinforced soils.

In general, few design methods are available for determining the bearing capacity of shallow foundations. Huang and Menq (1997) suggested an empirical formula for reinforced soils after the ‘deep footing’ effect reported by Schlosser *et al.*, where the reinforcement spreads the load with depth, such that the system can be modelled as a wider footing acting at the depth of the last reinforcement layer. The increase ΔB in footing width is estimated by the Huang and Menq

method using the Binquet and Lee (1975a, 1975b) laboratory-scale testing results of soils reinforced with geosynthetics, fibres, aluminium strips, etc. The same criticism of Das's work can be applied to this analysis.

Michalowski (2004) suggested a method to estimate the upper bound of bearing capacity for reinforced-soil-mass-based failure surfaces determined by plasticity theory. His results were for strip footings only, and take a form similar to a typical bearing capacity equation. This method is promising but still requires considerable calibration and refinement before it can be adopted for use in practice.

Research has also focused on optimizing the location of the reinforcement below the shallow spread footing (Guido *et al.*, 1987; Chadbourne, 1994; Omar *et al.*, 1994; Yetimoglu *et al.*, 1994; Espinoza and Bray, 1995); Adams and Collin, 1997; Adams *et al.*, 1997).


The optimum location of the geosynthetic below the spread footing has been suggested by researchers to be somewhere between $0.5B$ and $1.5B$ (where B is the width of the footing). The location of the reinforcement has a direct impact on the economy of a GRSF. If the reinforcement extends to a depth of $1.5B$, the cost of the GRSF may be several times greater than a GRSF that extends to a depth of $0.5B$ below the spread footing. Work by Adams and Collin (1997) and Adams *et al.* (1997) quantified the vertical and lateral strain at several locations below shallow spread footings, both with and without a reinforced soil foundation. Recommendations were then developed with respect to the location of the geosynthetic reinforcement for optimal performance of the GRSF based on the location of the zone of maximum strain in the foundation soil.

10.6.2 Design considerations

The maximum improvement in bearing capacity at low strains ($s/B = 0.5\%$) occurs when the depth to the top layer of reinforcement is within a depth of $0.25B$ from the bottom of the footing ($z_1 < 0.25B$). The GRSF should extend to a depth of $0.5B$ below the bottom of the footing. The maximum vertical spacing between layers of reinforcement should be less than 0.5 m ($z_n - z_{n-1} < 0.5$ m) and the length of the reinforcement should be at least equal to $2.0B$ ($l_n = 2.0B$).

When using the above guidelines for minimum reinforcement spacing and length, the design of a GRSF is based on the Westergaard layered elastic theory. The Westergaard theory is based on the assumption that the stress from the footing is distributed within the stiff layer as vertical stress only (e.g. no horizontal stress or deformation). The use of many layers of tensile reinforcement (geosynthetic reinforcement) in the reinforced soil foundation reduces lateral deformations within this layer to virtually zero, thus making the Westergaard theory appropriate for design.

The GRSF acts as a stiff soil layer overlying a softer soil deposit. The stiff GRSF acts like a beam and distributes the stresses from the footing over a larger area. This reduces the unit stress on the foundation soil from the footing. Figure 10.19 may

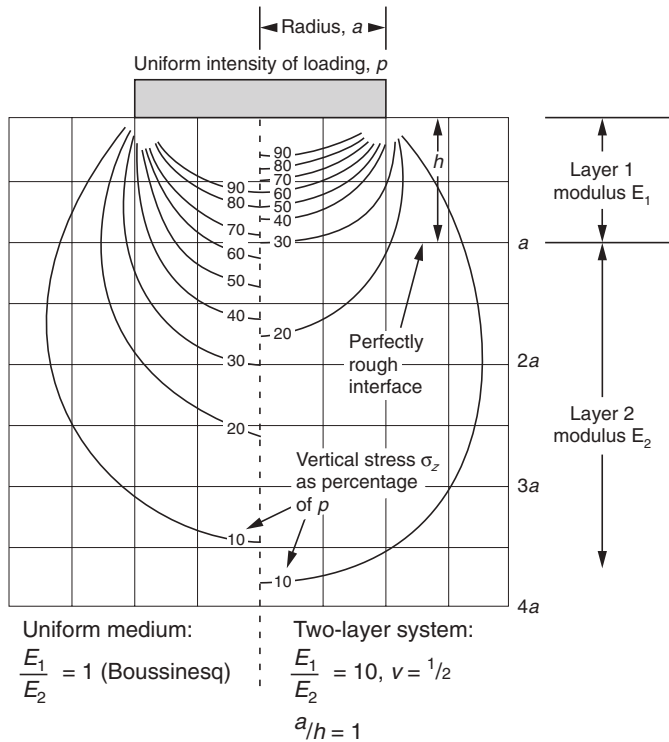

10.19 Westergaard stress distribution for a two-layer system (Munfakh *et al.*, 2001).

be used to estimate the vertical stress exerted on the foundation soil when using a GRSF. The steps in the design of a GRSF are briefly outlined as follows:

- Step 1 Perform site investigation and develop the design cross-sections for the proposed structure.
- Step 2 Perform laboratory tests to evaluate the shear strength and load versus deformation characteristics for the foundation soils.
- Step 3 Design the shallow foundation system for the structure without a reinforced soil foundation.
- Step 4 Develop the design cross-section (using the guidelines provided above for minimum reinforcement spacing and length).
- Step 5 Determine the vertical stress distribution in the foundation soil using the Westergaard elastic layer theory.
- Step 6 Determine the bearing capacity of the reinforced soil foundation. In this step, treat the reinforced soil below the footing as a stiff soil with a large

friction angle and check the bearing capacity of this layer. Also check the bearing capacity of the foundation soil including the effect of embedment.

Step 7 Check the settlement of the foundation soil using the vertical stress distribution determined in Step 5.

Step 8 Determine the required geosynthetic properties.

The use of a GRSF has been very limited in the USA. The above generalized design methodology is presented to provide insight into the steps that are believed to be important in the design of a GRSF. These recommendations are provided as a tool to determine the feasibility of a GRSF. However, the recommendations provided here cover only the basic steps in the design. The selection of geosynthetic reinforcement, creep characteristics of the geosynthetic, overlaps, etc, are beyond the scope of this chapter but must be considered in the design.

10.6.3 Future research needs

Clearly, the development of a relatively simple design methodology for a shallow foundation on a reinforced soil mass is important for state-of-practice implementation. The methodology presented in the previous section is based on limited research and actual implementation. Testing on a wider range of soils with either geogrids or geotextiles seems imperative, as do a wider range of instrumented full-scale tests on different footing shapes. Current methods also do not quantify how to determine the optimum size and spacing of geosynthetic reinforcement.

In most cases, bearing capacity does not control shallow foundation design. Some work has been carried out to calibrate measured strains in large-scale laboratory tests to existing settlement calculations. This must be considered for a wider range of geosynthetics to verify the assumptions of the elastic modulus increase, and for a variety of spacings.

Finally, the economics of reinforced soils should be addressed. Unless the footing is being placed over reinforced soil for a mechanically stabilized earth wall or other reinforced soil slope, the construction of the reinforcement zone requires excavation of an area to a depth where the attenuated stresses do not exceed the subgrade strength. When adding in the cost of geosynthetics and backfilling with competent material, the cost of simply constructing a larger traditional footing must be considered.

10.7 References

- Adams, M. T. and Collin, J. G. (1997), 'Large model spread footing load tests on geosynthetic reinforced soil foundations', *Journal of Geotechnical and Geoenvironmental Engineering*, **123**(1), 66–72.
- Adams, M. T., Lutenegeger, A. J. and Collin, J. G. (1997), 'Design implications of reinforced soil foundations using soil strain signatures and normalized settlement criteria', in *Proceedings of the International Symposium on Mechanically Stabilized Backfill*, Denver, Colorado, USA, February 1997, A. A. Balkema, Rotterdam, pp. 159–165.

- Alexiew, D. (2003), *Piled Embankment Design: Methods and Case Histories*, Huesker, Gescher.
- Alexiew, D. and Gartung, E. (1999), 'Geogrid reinforced railway embankment on piles — performance monitoring 1994–1998', in *Anais do 3° Simpósio Brasileiro de Geossintéticos'99*, Rio de Janeiro, Brazil, October 1999, pp. 403–411.
- Armour, T., Groneck, P., Keeley, J. and Sharma, S., (2000), *Micropile Design and Construction Guidelines, Publication FHWA-SAS-97-070*, Federal Highway Administration, Washington, DC.
- Bell, A. L., Jenner, C., Maddison, J. D. and Vignoles, J. (1994), 'Embankment support using geogrids with vibro concrete columns', in *Proceedings of the 5th International Conference on Geotextiles, Geomembranes and Related Products*, Vol. 1, Singapore, 1994, International Geosynthetics Society, South East Asian Chapter, Singapore, pp. 335–338.
- Binquet, J. and Lee, K. (1975a), 'Bearing capacity tests on reinforced earth slabs', *Journal of the Geotechnical Engineering Division, American Society of Civil Engineers*, **101**(12), 1241–1255.
- Binquet, J. and Lee, K. (1975b), 'Bearing capacity analysis on reinforced earth slabs', *Journal of the Geotechnical Engineering Division, American Society of Civil Engineers*, **101**(12), 1257–1276.
- British Standards Institution (1995), BS 8006 (1995), *Code of Practice for Strengthened/Reinforced Soils and Other Fills*, British Standards Institution, London.
- Chadbourne, W. (1994), 'An investigation into the performance of shallow spread footings in reinforced cohesionless soil', Research project performed at Turner–Fairbank Highway Research Centre, Mclean, Virginia submitted in partial fulfilment of the requirements of Master of Sciences, Tufts University, Medford, Massachusetts.
- Collin, J. G. (2002), *Timber Pile Design Construction Manual*, American Wood Preservers Institute, Fairfax, Virginia.
- Collin, J. G., Han, J. and Huang, J. (2005a), 'Design recommendations for column supported embankments', *Publication FHWA-HRT-XXX*, Federal Highway Administration, Washington, DC.
- Collin, J. G., Watson, C. H. and Han, J. (2005b), 'Column supported embankment solves time constraint for new road construction', in *Proceedings of the ASCE–GeoInstitute Geo-Frontiers Conference*, Austin, Texas, USA, January 2005, American Society of Civil Engineers, Reston, Virginia.
- Das, B. M. (1995), *Principles of Foundation Engineering*, 3rd edition, PWS Publishing, Boston, Massachusetts.
- Elias, V., Welsh, J., Warren, J., Lukas, R., Collin, J. G. and Berg, R. R. (2004), 'Ground improvement methods', *Report FHWA-NHI-04-001*, Federal Highway Administration, Washington, DC.
- Espinoza, R. D. and Bray, J. D. (1995), 'An integrated approach to evaluating single layer reinforced soils', *Geosynthetics International*, **2**(4), 723–739.
- Fluet, J. E., Christopher, B. R. and Slaters, A. R. (1986), 'Geosynthetic stress–strain response under embankment loading conditions', in *Proceedings of the 3rd International Conference on Geotextiles*, Vol. 1, Vienna, Austria, 1986, A. A. Balkema, Rotterdam, pp. 175–180.
- Gabr, M. A. and Han, J. (2005), 'Advances in reinforcements for embankments and shallow foundation on soft soils', in *Proceedings of the ASCE–GeoInstitute Geo-Frontiers Conference*, Austin, Texas, USA, American Society of Civil Engineers, Reston, Virginia.
- Giroud, J. P., Bonaparte, R., Beech, J. F. and Gross, B. A. (1990), 'Design of soil layer–geosynthetic systems overlying voids', *Geotextiles and Geomembranes*, **9**(1), 11–50.

- Guido, V. A., Knueppel, J. D. and Sweeny, M. A. (1987), 'Plate load tests on geogrid-reinforced earth slabs', in *Geosynthetics '87, Conference Proceedings*, New Orleans, Louisiana, USA, Industrial Fabrics Association International, St Paul, Minnesota, pp. 216–225.
- Han, J. (1999), 'Design and construction of embankments on geosynthetic reinforced platforms supported by piles', in *Proceedings of the 1999 ASCE–PaDOT Geotechnical Seminar*, Central Pennsylvania Section, American Society of Civil Engineers – Pennsylvania Department of Transportation, Hershey, Pennsylvania, 14–16 April, 1999.
- Han, J. (2003), 'Development of design charts for geotechnically reinforced embankments on deep mixed columns', *Report for National Deep Mixing Cooperative Research Program, Project NDM 202*, Transportation Research Board.
- Han, J. and Collin, J. G. (2005), 'Geosynthetic support systems over pile foundations', in *Geosynthetics in Transportation and Geotechnical Engineering, Proceedings of the GRI 18 Conference*, Austin, Texas, USA, January 2005, Geosynthetic Institute, Philadelphia, Pennsylvania.
- Hannigan, P. J., Goble, G. G., Thendean, G., Likinis, G. E. and Rausche, F. (1998), 'Design and construction of driven pile foundations', *Publication FHWA-HI-97-013*, Federal Highway Administration, Washington, DC.
- Hewlett, W. J. and Randolph, M. F. (1988), 'Analysis of piled embankments', *Ground Engineering*, **22**(3), 12–18.
- Huang, C. C. and Menq, F. Y. (1997), 'Deep footing and wide-slab effects on reinforced sandy ground', *Journal of Geotechnical and Geoenvironmental Engineering*, **123**(1), 30–36.
- Huang, J., Collin, J. G. and Han, J. (2005a), '3D numerical modeling of a geosynthetic-reinforced pile-supported embankment—stress and displacement analysis', in *Proceedings of the 16th International Conference on Soil Mechanics and Geotechnical Engineering*, Osaka, Japan, 12–16 September 2005, Millpress, Rotterdam.
- Huang, J., Collin, J. G. and Han, J. (2005b), 'Geogrid-reinforced pile-supported railway embankments — three dimensional numerical analysis', in *Proceedings of the 84th Annual Transportation Research Board Meeting*, Washington, DC, 9–13 January 2005, National Academies, Washington, DC.
- Jenner, C. G., Austin, R. A. and Buckland, D. (1998), 'Embankment support over piles using geogrids', in *Proceedings of the 6th International Conference on Geosynthetics*, Vol. 1, Atlanta, Georgia, USA, 1998, Industrial Fabrics Association International, Roseville, Minnesota, pp. 763–766.
- Kemfert H., Stadel, M., and Zaeske, D. (1997), 'Design of geosynthetic-reinforced bearing layers over piles' (in German), *Bautechnik*, **74**(12), 818–825.
- Marston, A. and Anderson, A. O. (1913), 'The theory of loads on pipes in ditches and tests of cement and clay drain tile and sewer pipe', *Bulletin 31*, Iowa Engineering Experiment Station, Ames, Iowa.
- McNulty, J. W. (1965), 'An experimental study of arching in sand', *Technical Report I-674*, US Army Engineer Waterways Experiment Station, Corps of Engineers, Vicksburg, Mississippi.
- Michalowski, R. L. (2004), 'Limit loads on reinforced foundation soils', *Journal of Geotechnical and Geoenvironmental Engineering*, **130**(4), 381–390.
- Munfakh, G., Arman, A., Collin, J. G., Hung, J. C. and Brouillette, R. P. (2001), 'Shallow foundations reference manual', *Report FHWA-NHI-01-023*, Federal Highway Administration, Washington, DC.
- Omar, M. T., Das, B. M., Puri, V. K., Yen, S. C. and Cook, E. E. (1994), 'Bearing capacity

- of foundations on geogrid-reinforced sand', in *Proceedings of the 13th International Conference on Soil Mechanics and Foundation Engineering*, New Delhi, India, January 1994, Oxford and IBH Publishing, New Delhi, pp. 1279–1282.
- Reid, W. M. and Buchanan, N. W. (1984), 'Bridge approach support piling', in *Piling and Ground Treatment*, Thomas Telford, London, pp. 267–274.
- Rogbeck, Y., Alen, C., Franzen, G., Kjeld, A., Oden, K., Rathmayer, H., Want, A. and Oiseth, E. (2002), *Nordic Handbook Reinforced Soils and Fills Draft 2002–12–20*, Nordic Geosynthetic Group, Oslo.
- Rogbeck, Y., Gustavsson, S., Södergren, I. and Lindquist, D. (1998), 'Reinforced piled embankments in Sweden — design aspects', in *Proceedings of the 6th International Conference on Geosynthetics*, Atlanta, Georgia, USA, 1998, Industrial Fabrics Association International, Roseville, Minnesota, pp. 755–762.
- Schlosser, F., Jacobsen, H. M. and Hovic, N. (1983), 'Soil reinforcement', in *General Report, 8th European Conference on Soil Mechanics and Foundation Engineering*, Helsinki, Finland, A. A. Balkema, Rotterdam, pp. 83–103.
- Terzaghi, K. and Peck, R. B. (1967), *Soil Mechanics in Engineering Practice*, Wiley, New York.
- Yetimoglo, T., Wu, J. T. H. and Saglamer, A. (1994), 'Bearing capacity of rectangular footings on geogrid-reinforced sand', *Journal of Geotechnical Engineering*, **120**(12), 2083–2099.
- Young, L. W., Milton, M. N., Collin, J. G. and Drooff, E. (2003), 'Vibro-concrete columns and geosynthetic reinforced load transfer platform solve difficult foundation problem', in *Proceedings of the 22nd World Road Congress*, Durban, South Africa, 2003, World Road Association (PIARC), La Defense.

D. SMITH
EDGE Consultants UK Ltd, UK

11.1 Introduction

When civil engineers talk about quality assurance in respect of geosynthetics, there is an inevitable immediate link with landfill engineering and, in particular, the geomembrane liner element. There have been many guidance documents produced from around the early 1980s onwards relating to the quality assurance requirements for design and construction of landfill lining systems utilizing geosynthetics.

The need for good quality assurance throughout the design and construction of a landfill site cannot be underestimated. The landfill environment is arguably the most demanding for any construction material and not just geosynthetics. However, good quality assurance in connection with other applications of geosynthetics should not be assumed nor ignored.

Geosynthetics are utilized at some stage within almost every civil engineering construction project undertaken, from the small project requiring a filter geotextile within a short length of gravel-filled drainage system to the major project incorporating massive geosynthetic-reinforced soil walls and everything in between. Whatever construction work is being undertaken, some form of quality assurance system must be in place to ensure that the geosynthetic system and its constituent parts will function as required.

This chapter provides some definitions of quality, quality assurance and quality control, some guidance on who has the responsibility for the various elements of quality assurance and some comment on design aspects. It then goes on to deal with manufacturer's quality control and construction quality control (CQC) and construction quality assurance (CQA) before outlining some of the benefits of a quality assurance system and providing some indication of the costs involved. The chapter is written generally with geosynthetic lining systems in mind because this is where most of the literature provides guidance. Where appropriate, guidance relating to other geosynthetic types is provided.

11.2 Definitions

It is useful to provide some definitions relating to quality. Quality assurance is not the only aspect of quality that should be considered. There is also the aspect of quality control.

The *Compact Oxford English Dictionary of Current English* (2005) gives the following definitions.

- 1 *Quality*. The degree of excellence of something as measured against other similar things.
- 2 *Assurance*. A positive declaration intended to give confidence.
- 3 *Quality control*. A system of maintaining standards in manufactured products by testing a sample against the specification.

From this, it is apparent that 'quality assurance' is meant to provide confidence that what is being 'assured' is of a required 'quality'. 'Quality control' on the other hand is intended to ensure that a particular standard has been met.

Quality assurance is not limited to the construction materials and the construction process but should be applied throughout the project process, including selection of designer, the design itself, validation of the design, selection of appropriate construction materials, construction and validation of construction.

In relation to construction materials and the construction itself, there are generally two aspects to quality control and assurance. There is the control and assurance performed by the supplier or manufacturer of the material to ensure that the product delivered to site is correct, to specification and of the required quality and also the control and assurance performed during the construction process to ensure that what is constructed is also correct, to specification and of the required quality.

In the context of geosynthetics, it is convenient to adopt terminology used within the landfill lining sector to describe quality assurance and quality control. Koerner (1997) provides definitions for manufacturing quality control, manufacturing quality assurance, CQC and CQA. Although these definitions are directed specifically at requirements for landfill lining systems, they are equally valid for all applications of geosynthetics.

The various definitions detailed by Koerner are not repeated here. Essentially, however, quality assurance can be said to embrace all activities and functions concerned with the attainment of quality, rather than the proof associated with the word 'assurance'. Thus, quality assurance includes the determination and assessment of quality. The concept of quality control is to ensure that the quality of the end product meets a predetermined standard. The term may be applied to the system of control or to the product or service being controlled.

11.3 Responsibilities

The process of quality assurance within the project is started by the client. Under

normal circumstances the client who has the requirement for a particular construction project is responsible for appointing a designer to work with him or her to develop the scheme into something that meets requirements. He or she must ensure that a designer is appointed who is appropriately qualified and experienced to undertake the work. He or she is also responsible for providing the designer with an appropriate and realistic brief.

The designer is responsible for ensuring that reasonable skill and care are demonstrated in developing the design. A recognition and use of relevant published guidance and standards are essential. The designer is responsible for producing reports, drawings, specifications, schedules etc. to present all the required construction details in such a manner as to allow a construction company to undertake the works. There are some variations on this general approach, e.g. design and build, and partnering, but essentially this is the basic process.

At various stages of the process, depending on the type of project, there may be a requirement for some input from regulators and/or inspectors from environmental, planning or other stakeholders. The regulators and/or inspectors will be responsible for ensuring that the whole of the construction meets their local minimum standards. It is the responsibility of the designer to ensure that the client is aware of these minimum standards and that the design complies with them.

Both the manufacturer and constructor are responsible for implementing appropriate quality assurance and quality control procedures to ensure that the end product meets the required specification. There is a tripartite responsibility for monitoring these procedures.

- 1 The designer must satisfy himself or herself that the quality assurance and quality control procedures are in place – supported by the client as necessary.
- 2 A third-party quality assurance and quality control reviewer may be appointed to manage and control the whole quality assurance and quality control package. The reviewer will be responsible for making such records as necessary to provide the proof that the procedures have been followed. It is common for the designer to undertake the quality assurance and quality control review role in many cases. This can be an acceptable way forward; ensuring that the quality assurance and quality control reviewer is familiar with the site and the design before the works are undertaken. It may also improve communication between the designer and the quality assurance and quality control reviewer. The type of quality assurance and quality control review arrangement should be assessed on a case-by-case basis.
- 3 The regulator/inspector must review and approve the proof that the quality assurance and quality control procedures have indeed been implemented.

11.4 Design aspects

Designing with geosynthetics follows standard relationships of stress, strain,

temperature, pressure, flow, etc. The literature contains many methodologies that have been developed from these basic principles that can be utilized in the design of geosynthetic systems. There is also a plethora of statutory guidance, national standards and case histories relating to all aspects of designing with geosynthetics. It is simply not acceptable to pull a 'standard specification' off the shelf for a particular geosynthetic application in the hope that it will perform adequately. Appropriate design will ensure that the correct geosynthetic material parameter values are determined to allow the correct specification to be prepared.

Design is best undertaken within a quality-assured system. This should ensure that all aspects of the project are taken into account within the design process. It is essential that all aspects of the construction project are designed appropriately. Geosynthetics are likely to be only part of a larger system within a construction project. Particular attention must be given to the interaction of all components of the structure system. Understanding the interaction of the individual components will enable the designer to identify where incompatibilities lie, where the weak points of the system are and to put in place measures to design these issues out. For example, it may be the case that ground conditions are such that a certain type of geosynthetic reinforcement or filter geotextile is more appropriate than another; different polymers and products may perform better under certain conditions.

There are essentially five functions that geosynthetics perform.

- 1 Reinforcement.
- 2 Separation.
- 3 Filtration.
- 4 Containment.
- 5 Drainage.

In some cases a geosynthetic may be required to perform multiple functions, e.g. separation and filtration, or reinforcement and drainage. In other cases, composites of geosynthetics may be formed that perform multiple functions.

In some cases, there may be a number of different methods of designing a particular system. For example, many methodologies have been published over the years relating pore opening size and particle size to designing a geotextile filter. Essentially, in all design work relating to geosynthetics, as with other construction materials, it is the designer who should ensure that the most appropriate relationship is adopted in the particular case under consideration. It is possible that this will include the testing of particular geosynthetic products together with site-specific materials to assess performance and to test the design assumptions that have been made, e.g. shear box testing of reinforcement geosynthetics together with material to be used in construction to assess interface friction values or compliance testing of geomembranes with site-specific leachate to assess compatibility.

11.5 Manufacturing quality control

Geosynthetics are manufactured from a variety of polymer resins. The selection of the resin and the method of joining the molecules together will result in different final characteristics of the geosynthetic. Quality control at this stage of the process is very important, but the civil engineering designer probably does not need to know all the intricacies of the quality control measures put in place by the manufacturer at this stage. However, the designer does need to know that the manufacturer takes the quality control process seriously and needs to be confident that the product that is being delivered to site after passing through the quality control process is suitable for use and meets specification.

Manufacturer's quality control processes will generally include random sampling and testing of the raw materials, visual and automated inspection during manufacture and sampling and testing of the final product. Sprague (1995) suggested a sampling and testing frequency for all manufacturers to follow in order to introduce some consistency in the reporting of material properties. The frequency varies with the size of the lot being manufactured. The larger the lot, the lower the frequency of testing required. Minimum frequency suggested is around 10% of the manufactured units.

It is important that the designer understands what the values quoted on the manufacturer's product literature mean when selecting products which potentially meet specification. Manufacturer's product literature quotes characteristic values for various properties of the geosynthetic. The range of characteristic values quoted depends on the intended function of the geosynthetic. In general terms the parameters quoted are the minimum average roll values (MARVs). Sprague (1995) explains that it is essential that the confidence limit associated with the MARV is also reported so that the designer can use the value with confidence.

The European Union (EU) has introduced the CE marking scheme to geosynthetic products. All geosynthetic products sold within the EU should have a CE mark. This effectively means that the manufacturer has gone through a process to sample, test and prove that the product meets certain minimum standards. The roll of geosynthetic delivered to site with a CE mark must have an accompanying certificate that details the properties of that particular roll. The properties reported are defined by the minimum standards documents. This system provides confidence to the user that the product being used has attained the standard quoted, although it does not provide any site-specific guarantees. It should be noted that at this point in time (2006) the UK Government, unlike other EU countries, is choosing not to enforce the requirement for CE marking on geosynthetic products. This potentially allows substandard geosynthetics to be sold in the UK and is despite the fact that all UK geosynthetic manufacturers have invested significant time and expense in achieving the CE mark for their products.

The designer must ensure that details of the manufacturer's quality control policy are obtained and that the details are appropriate and are being followed.

11.6 Installation and construction

Installation or construction quality assurance and quality control should be adopted to ensure that the geosynthetic products being delivered to site and utilized in the construction meet specification and are installed correctly. The degree of construction quality assurance and quality control should be proportionate to the scale, complexity and economics of the construction project under consideration. The amount of quality assurance and quality control adopted for our small project requiring a filter geotextile around a gravel-filled trench will be significantly different from that required for the major geosynthetic-reinforced soil wall and different again from the requirements within a landfill lining system.

It is possible that the properties listed on the manufacturer's product literature, together with a certificate of compliance will be sufficient evidence for the designer to be assured of the required quality. At the other extreme, a detailed CQA plan may be required to define exactly what sampling, testing, inspection and reporting regime must be followed.

To illustrate the detailed requirements of a CQA regime, it is convenient to consider a landfill lining project. Typical elements of the CQA regime are likely to include the following.

- 1 The lining material delivered to site (usually taken from rolls delivered to site but can be taken from the suppliers store if programme requires it and the designer can be assured that the rolls sampled and tested will be used in the works) should undergo conformance testing. Both identification and performance testing should be undertaken (Rollin and Rigo, 1991). The testing regime should be designed to suit the application.
- 2 The delivery, handling and storage of the lining material must be undertaken in such a way as to prevent any damage before the installation is undertaken. Visual inspection of all rolls should be undertaken and it is essential that each roll can be positively identified and related back to manufacture details such as batch number, date of manufacture and roll identification number. Certificates detailing properties for each roll will normally be required.
- 3 It must be ensured that the subgrade to accept the lining system is prepared to reduce the risk of puncture and settlement of the subgrade to a minimum. In some cases, it may be necessary for the liner installer to accept formally the subgrade from an earthworks contractor. This should be signed on to by all parties involved.
- 4 Each element of the lining system must be placed in an appropriate manner. Visual inspection of each sheet or panel of each component of the lining system is essential. Any anomalous features should be recorded and, where necessary, affected sheets or panels should be replaced or repaired. Records of actions taken to rectify any anomalies should be made.
- 5 The individual sheets or panels should be joined together in an appropriate manner. For the geomembrane this will require test seams to be carried out as

a minimum every day and for each combination of operator and seaming machine, with test seams being destructively tested. For other geosynthetic components of the lining system this may require sewing, lapping or other joining techniques to be undertaken. Testing of joints may be required depending on the function and requirements of the design.

- 6 The weather must be monitored and recorded during the installation process. An increase in wind speed can cause sheets or panels to move around suddenly and violently, making conditions very hazardous for the installers. A change in air and geomembrane temperature throughout the day may mean that the welding machines may need to be recalibrated.
- 7 The condition of the liner surfaces before welding should be monitored to ensure they are clean and dry.
- 8 Destructive and non-destructive testing of geomembrane seams must be carried out to ensure their integrity and strength. Every seam made on site should have some form of test undertaken. Locations of destructive tests should be selected carefully to reduce the number of patches required to a minimum within the operational landfill cell. For cases where there is confidence that the installation team is of good quality and are performing the seaming with care throughout, the number of destructive tests on seams can be reduced. It may be appropriate for all destructive tests to be undertaken at the ends of seams rather than the middle of seams to satisfy this requirement in this case. Where the installer's performance history is unknown, then the number of destructive seams should be increased to suit. It is recommended that the number of midseam destructive tests is kept to an absolute minimum. Some further guidance on this is provided by the International Association of Geosynthetic Installers (2004).
- 9 Destructive and non-destructive testing of joints should be performed on other geosynthetic sheets or panels utilised in the landfill lining system.
- 10 Conformance testing must be carried out on other materials utilized within the landfill lining system. This may include mineral lining, mineral protection or mineral drainage components. Note that all these functions can be met by the use of geosynthetics.
- 11 A leak detection survey on the installed system must be undertaken to check for holes and then any holes located must be repaired appropriately. There are a number of leak detection survey methods available.
- 12 It must be ensured that the first layer of waste placed within the cell does not damage the lining system.

It would be normal practice to prepare a report detailing all aspects of CQA undertaken. The CQA report would typically contain the following information as a minimum.

- 1 A brief description of the project, including the type of facility, name of site, location, name of owner, design engineer, liner installer and main contractor.

- 2 A detailed description of the lining system, including the surface area, cross-section and definition of all materials.
- 3 A reference to the CQA plan.
- 4 A copy of all subgrade inspection forms.
- 5 A statement that construction has been carried out in substantial accordance with the design (including modifications, if any, approved by the engineer).
- 6 The regulator's agreement in writing to any design modifications as sought before implementation.
- 7 A construction record drawing clearly showing changes from design drawings.
- 8 As-constructed drawings of each layer of the lining system, including basal and surface surveys of any mineral liners and drainage layers.
- 9 A discussion of any particular problems encountered and their solutions.
- 10 A copy of specifications for all elements of the lining system.
- 11 A copy of (or reference to) the geosynthetic manufacturer's quality control documentation.
- 12 A quality assurance record drawing indicating panel code numbers, seam code numbers, dates of seaming and repairs and locations and nature of all repairs.
- 13 A general record of activities, such as dates of performance of quality assurance operations, number and names of quality assurance monitors, names of personnel of liner installers.
- 14 Copies of all forms and logs filled out by quality assurance monitors.
- 15 Copies of all field and laboratory test results.
- 16 A photographic record including general photographs of the site at different phases of construction and specific construction details.

It can be seen that the CQA requirements for landfill lining systems can be onerous. They should only be carried out by qualified and experienced personnel. It is inappropriate to define frequencies of testing and exact methodologies to adopt. Adams *et al.* (2001) suggested that blindly following regulatory-driven CQA programmes in landfill lining applications is not the way forward. Making use of the advances in technology, e.g. leak location surveys and improved seaming techniques, to reduce the overall requirements of a CQA programme while retaining the confidence in the overall end product is a more appropriate methodology.

There are site-specific issues that must be referenced to the regulatory regime at the facility location and discussed and agreed with the appropriate regulator before undertaking the works. As an absolute minimum, the agreement of the CQA plan with the regulator in advance of a project must be obtained. Otherwise, there is a disaster waiting to happen.

The Environment Agency (2005) in the UK has provided draft guidance which states that best available techniques must be applied to CQA at landfills and gives general guidance in relation to specific geosynthetic elements within the system. Similar documents are available in other countries.

11.7 Benefits

The adoption of good CQA procedures during construction of landfill lining systems has been clearly demonstrated to result in less leakage from the lining system in numerous papers published over the years. The most recent of these (Koerner and Koerner, 2006) showed that the average number of leaks per hectare reduces from 22 to four when CQA is adopted. The paper by Koerner and Koerner outlined the Geosynthetic Research Institutes' CQA and inspectors certification programme. This highlights the importance of utilizing appropriately trained personnel for CQA work. In the UK, the Environment Agency introduced a training course for CQA inspectors on landfills in the late 1990s, although this does not result in a formal qualification.

Direct proof of benefits in other geosynthetic applications has not been published in detail as far as the author is aware. For example, there has not been a study into the number of reinforced soil slopes and walls that have failed with and without a quality assurance and quality control regime in place. However, it is logical that adopting a good quality assurance process when designing with geosynthetics will provide benefits in terms of increased confidence in the various elements of the structure.

11.8 Costs

As stated above, the degree of quality assurance activity required when using geosynthetics will depend on the scale and complexity of the project being undertaken and also the economics of the project.

Darileck and Laine (2001) suggested some costs for identifying defects in geomembranes (sheet or seams) following regulatory-driven CQA regimes in landfill applications in the USA. They concluded that direct conventional CQA costs would be on average about US\$8000 per problem identified. They compared this with simply undertaking a leak location survey on completion of the works and concluded that leak location survey costs were around US\$1200 per problem identified.

Although these figures give an indication of the general costs of CQA, they are not particularly useful as they are not related to area. They also assume that the holes in a liner are inevitable whereas the ideal result of adopting an appropriate CQA regime within a landfill lining application will be to ensure that there are no holes in the liner on completion. This is possible.

Quantifying the cost of CQA is difficult as it depends on many factors including operating area, size of facility, type of facility and regulatory regime amongst others. There will inevitably be a balance to be struck in determining the required extent of the quality assurance regime to be adopted. This will be heavily influenced by the risk associated with the failure of the geosynthetic element being used and needs to be considered carefully within the design process.

11.9 Future trends and sources of further information

Quality assurance related to the use of geosynthetics in civil engineering will always be required as with all other construction materials. In some areas of use this will inevitably be more complex than in others as detailed above.

The increasing number of directives and guidance published throughout the world, in particular in relation to environmental issues, will inevitably lead to more detailed requirements for quality assurance and quality control at the various stages of all construction projects. It is essential that this is kept in perspective, that the quality assurance and quality control requirements are appropriate for the usage of the geosynthetic and that the cost benefits are positive. As technology advances, the use of modern methodologies to assist in the quality assurance and quality control process must be encouraged where appropriate, particularly where this improves the final product and reduces the risk of failure occurring while at the same time reducing costs.

The designer should obtain guidance on quality assurance and quality control requirements from the local regulators (e.g. the US Environmental Protection Agency or the UK Environment Agency) or design standards. Further guidance can be obtained from organizations such as the International Geosynthetics Society (2006) and the Geosynthetics Research Institute (2006) and from publications such as *Geosynthetics* (www.geosyntheticsmagazine.info) (Industrial Fabrics Association International, 2006), *Geosynthetics International* and *Geotextiles and Geomembranes*.

11.10 References

- Adams, M., Hullings, D. and Swyka, M. (2001), 'Geomembrane construction quality assurance update', *GFR*, **19**(4), 18–21.
- Darileck, G. T. and Laine, D. L. (2001), 'Costs and benefits of geomembrane liner installation CQA', in *Proceedings of the Geosynthetics Conference, 2001*, Industrial Fabrics Association International, Roseville, Minnesota, pp. 65–75.
- Environment Agency (2005), 'Guidance for the landfill sector, technical requirements of the Landfill Directive and Integrated Pollution Prevention and Control (IPPC), external consultation 1', *Sector Guidance Note IPPC S5.02*
- Geosynthetics Research Institute (2006), <http://www.geosynthetic-institute.org>.
- Industrial Fabrics Association International (2006), <http://www.gfrmagazine.com>.
- International Association of Geosynthetic Installers (2004), 'Improving geomembrane installations', *White Paper, GFR Engineering Solutions*, **22**(4), 24–31.
- International Geosynthetics Society (2006), <http://www.geosyntheticsociety.org>.
- Koerner, G. R. and Koerner, R. M. (2006), 'Construction quality assurance and inspectors certification program (CQA-ICP)', *Geosynthetics*, **24**(2), 46–49.
- Koerner, R. M. (1997), *Designing with Geosynthetics*, 4th edition, Prentice Hall, Englewood Cliffs, New Jersey.
- Rollin, A. and Rigo, J. M. (Eds) (1991), *Geomembranes Identification and Performance Testing*, Chapman & Hall, London.

- Sprague, C. J. (1995), 'Manufacturing quality control and certification of geotextiles', *Geosynthetics International*, 2(3), 587–601.
- Soanes, C. and Hawker, S. (Eds) (2005), *Compact Oxford English Dictionary of Current English*, Oxford University Press, Oxford, available online at <http://www.askoxford.com/dictionaries/compact-oad/?view=uk>.

12.1 Introduction

Over the past 50 years the use of man-made polymeric materials to produce high-strength durable technical fabrics has resulted in the widespread use of geotextiles to improve the engineering performance of the ground. Whilst the polymeric technical fabrics have long working lives, they are often used in practical situations where a geotextile is only needed to be fully functional for a relatively short period of time, e.g. a separator layer beneath a temporary access road, or basal reinforcement of an embankment built on soft clay. The technical requirements of such fabrics could be satisfied by geotextiles which can be designated as ‘limited-life geotextiles (LLGs)’ i.e. high-specification geotextiles that are designed on the basis of having a limited, clearly definable working life (Sarsby, 1997). These materials are designed so that progressive loss of their capability with time is matched by improvement in the ground conditions with time (usually due to drainage and consolidation). Vegetable fibres are natural candidates for use in the manufacture of LLGs since they are a renewable resource (and are often a waste or by-product from food production), they are environmentally friendly and their degradation with time is accounted for in the design of the LLG. Although man-made fibres dominate the technical textiles market (Byrne, 2000) a significant quantity of natural fibres are also used to make high-specification products (Table 12.1) and it is this type of product that has the potential to make a major contribution to a sustainable construction industry through enhanced use of renewable natural resources. The use of indigenous natural fibres also helps developing countries through support of agro-industry, provision of local employment and avoidance of costly imports. However, the ability of natural fibre products and components to meet technical and customer appeal requirements at a competitive price remains to be demonstrated.

12.2 Concept of limited-life geosynthetics

There are a significant number of ground engineering situations where the critical

Table 12.1 Global fibre production in 2000 (after Davis, 2001)

Fibre	Quantity (x 10 ³ t)
Cotton	19 800
Flax/Linen/Ramie	590
Jute and other vegetable fibres	4 000
Silk	90
Wool	1 300
Total natural fibres	25 860
Polyester	18 900
Polyamide	4 100
Acrylic	2 700
Polypropylene (including tape)	6 000
Elastane, aramids, etc.	310
Cellulosics	2 800
Glass	2 600
Total man-made fibres	37 410
Total	63 270


case for stability or functionality is either immediately (or very shortly) after construction and beyond this stage the stability of the system is constant or increases with time or the need for full functionality declines with time.

12.2.1 Filtration


Ground drains are typically vertical-sided trenches lined with a geosynthetic and then filled with coarse gravel. The geosynthetic acts as a filter by permitting the flow of liquid and gases but prevents major passage of soil particles which could cause blockage of the drain or settlement due to loss of ground. Initial loss of fine soil particles adjacent to the geosynthetic encourages the formation of a zone in the ground wherein particles bridge over the pores in the geosynthetic. This zone retains smaller particles, which in turn retain even smaller particles. Thus, a natural graded filter is formed which will prevent additional washout of fine particles. This arrangement of particles is structurally stable and the geosynthetic becomes redundant. The generalized design life envelope, i.e. variation in required functional effectiveness with time, is illustrated schematically in Fig. 12.1.

12.2.2 Separation

A geosynthetic acts as a separator by preventing the intermixing of coarse and fine soil materials whilst allowing the free flow of water across the fabric. A typical situation is when a geosynthetic is placed between the subsoil and the granular subbase of an unpaved temporary access road. The section of fabric beneath a wheel or machine track acts like a tensioned membrane (since it is 'anchored'

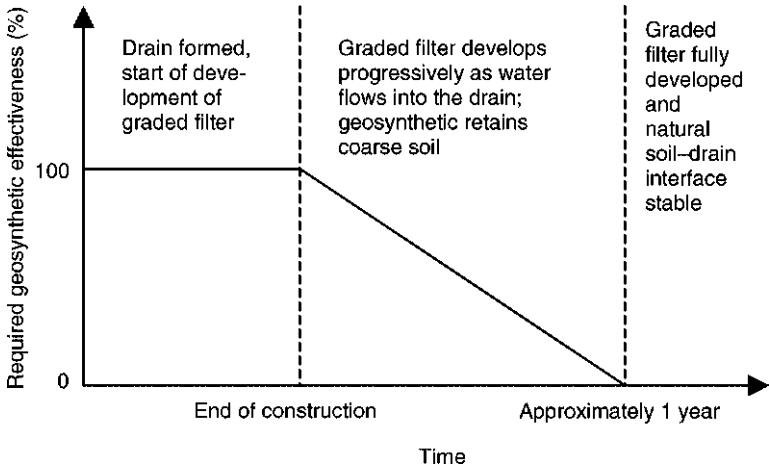


12.1 Design life envelope for a filtration geosynthetic.

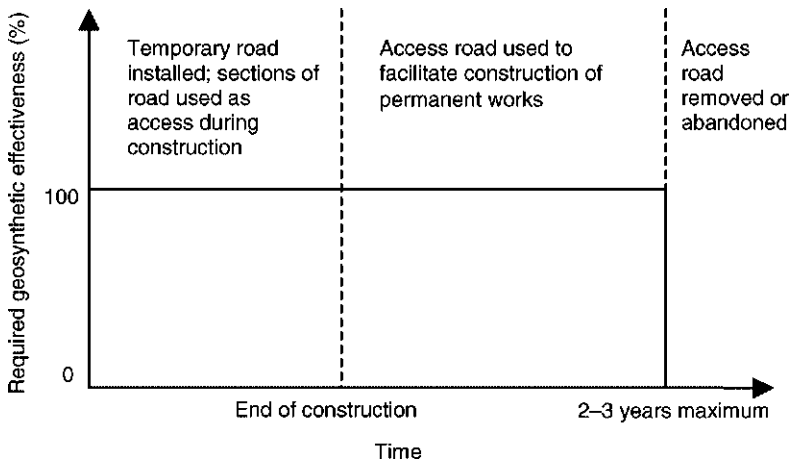

12.2 Design life envelope for a separation geosynthetic.

within the fill either side of the wheel or track) and prevents the aggregate from being punched down into the soil during initial compaction and subsequent dynamic loading from vehicle axles. At the same time, the geosynthetic allows water to pass upwards through itself but prevents large quantities of fine soil from doing so. Once the permanent works are completed, the temporary haul road can be dug up and the granular material-geosynthetic mixture is disposed of. The design life envelope for a separation geosynthetic is illustrated in Fig. 12.2.

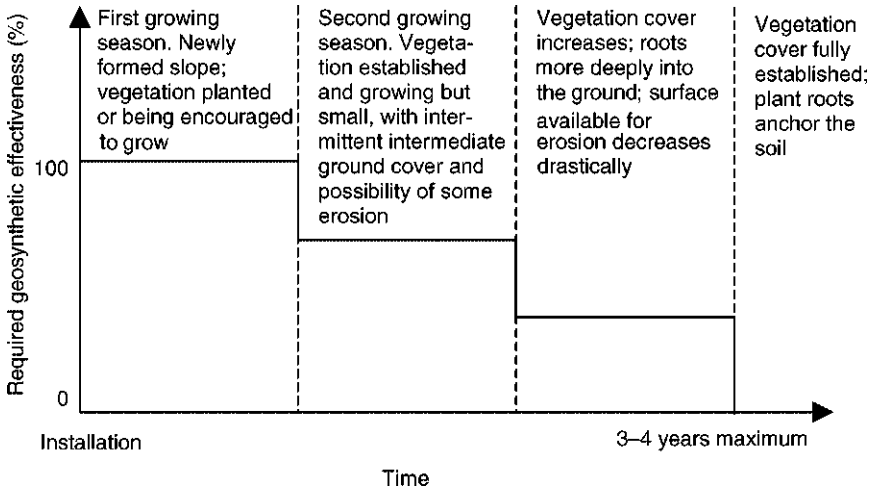

12.3 Design life envelope for an erosion control geosynthetic.


12.2.3 Erosion control

A current major area for geosynthetic utilization is in the erosion control industry. This usage differs from the other applications of geosynthetics in that these materials are laid on the ground and are not buried in the soil. The main aim is to control erosion whilst helping to establish vegetation which will then control erosion naturally. Geosynthetics can reduce run-off, retain soil particles and protect soil that has not been vegetated from the sun, rain and wind. Even when no longer needed for erosion control, the fabric may be utilized (to input nutrients into the soil as it degrades) if it is made from suitable material. The design life envelope is shown in Fig. 12.3.

12.2.4 Reinforcement

When an embankment is constructed over soft compressible ground, the load from the fill promotes foundation failure in the underlying ground without creating any immediate increase in its shear strength. The insertion of geosynthetics within the embankment and/or at its base will provide extra lateral force to prevent the embankment from failing by splitting or rotation. With time, pore water in the foundation will migrate from beneath the embankment and the shear strength of the foundation will increase. The stability of the embankment will thus improve in time as the underlying soft soil consolidates. As the underlying soil strength increases so the stabilizing force which needs to be provided by the geosynthetic diminishes (Fig. 12.4).

Tables 12.2 and 12.3 contain summaries of the relative importance of geosynthetics

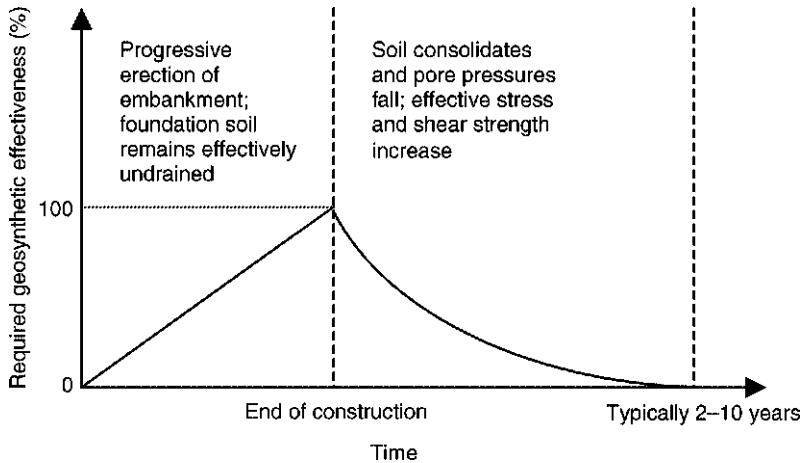

12.4 Design life envelope for an embankment reinforcement geosynthetic.

properties for different engineering applications. In Table 12.2, the entries in bold type indicate those properties that are needed only until the end of the construction/installation stage. In Table 12.3, the entries in bold type indicate those properties that are needed after construction and installation but the importance of which diminishes rapidly (and even vanishes) with time. It is readily apparent that there are many ground engineering situations where geosynthetics are only required to function at full capacity for a limited time period. If a conventional geosynthetic is used in these situations, for most of its working life it will be effectively redundant. Consequently, the construction work is overdesigned and, if the geosynthetic is a costly import, it will have a detrimental effect on both the economy and the industry of the locality where the work is being undertaken. In such situations, the use of a non-conventional geosynthetic which has a limited but predictable working life, i.e. a LLG, is good engineering practice, particularly if this geosynthetic is made from local, environmentally friendly, renewable resources.

Vegetable fibres are an ideal 'raw material' for the manufacture of LLGs; it is accepted that they 'degrade' with time but there is a huge range of natural fibres available, with some having very high initial tensile strength and with some exhibiting very slow progressive loss of strength with time. Hence, it is possible to 'tailor' composites of natural fibres to produce a material with the required strength-time profile for a variety of engineering situations (Sarsby *et al.*, 1992). Kumar *et al.* (2001) described a classical limited-life product for use in consolidation of soil.

12.3 Natural fibres as industrial materials

The exploitation of natural fibres in construction can be traced back at least to the

Table 12.2 Functional requirements for geosynthetic applications (adapted from Pritchard *et al.*, 2000)

	Degree of importance ^a of the following properties						
	Tensile strength	Elongation	Flexibility	Puncture resistance	Creep	Permeability	Resistance to flow
Reinforcement	H	H	L	L	H	L	
Filtration	L-M	L-M	L-M	M		M-H	L
Separation	H	M	H	H	L	M-H	M
Drainage	L	L-M	M	M-H		H	L
Erosion control	M	M	H	L-M	L	M	H

^aH, highly important; M, moderately important; L, of some importance.

Table 12.3 Post-installation functional requirements for geosynthetic applications

	Degree of importance ^a of the following properties						
	Tensile strength	Elongation	Flexibility	Puncture resistance	Creep	Permeability	Resistance to flow
Reinforcement	H	H	L		H		
Filtration				M		M-H	
Separation	H	M	H	H	L	M-H	M
Drainage	L			M-H		H	L
Erosion control	M	M			L	M	H

^aH, highly important; M, moderately important; L, of some importance.

Table 12.4 Ultimate load capacities of typical ropes

Rope, diameter (mm)	12	16	20	24	28	32
Rope, circumference (mm)	41	51	64	76	89	102
Coir, tensile strength (kN)	2	3	5	7	10	13
Sisal, tensile strength (kN)	11	17	27	39	50	65
Italian hemp, tensile strength (kN)	11	18	28	41	55	71
Hardy hemp, tensile strength (kN)	14	28	44	58	92	133

fifth and fourth millennia BC when dwellings were formed from mud–clay bricks reinforced with reeds or straw. Two of the earliest surviving examples of material strengthening by natural fibres are the ziggurat in the ancient city of Dur-Kurigatzu (now known as Agar-Quf) and the Great Wall of China (Jones, 1996). The Babylonians constructed the ziggurat some 3000 years ago using reeds in the forms of woven mats (laid in horizontal beds of sand or gravel at vertical spacings of between 0.5 and 2.0 m) and plaited ropes (approximately 100 mm in diameter) as reinforcement. It is believed that it was originally over 80 m high; even today it is 45 m tall. The Great Wall of China, completed circa 200 BC, utilized tamarisk branches to reinforce mixtures of clay and gravel.

A major element in the development of all natural fibres in the past 50 years has been competition with synthetics. The intensity of this competition on the different fibres has varied according to relative prices and their respective technical properties and their function. In many cordage and twine applications, synthetics have almost completely taken the market from natural fibres. Vegetable fibres are generally perceived to have inherently low tensile strength and poor durability when in contact with the natural environment. However, for many centuries ropes made from natural fibres were used as ships' rigging, to lift large loads at docksides and mines, etc. The significant load capacity of typical natural fibre rope is displayed in Table 12.4.

The first documented engineering use of a vegetable fibre textile fabric in Civil Engineering was in 1926, when the highways department in South Carolina undertook a series of tests, using woven cotton fabrics as a simple type of geotextile or geomembrane, to reduce cracking and ravelling failure of roads (Beckman and Mills, 1957). The basic system of construction was to place the cotton fabric on a previously primed earth base and to cover it with hot asphalt. Although results obtained before 1935 appeared to indicate some improvement in road performance, especially for fabric which had been in service for 9 years, further widespread development of this fabric as a geotextile did not take place. Unfortunately, the construction made the fabric perform more like a geomembrane than a geotextile, i.e. it separated the layers of the road rather than uniting them. Furthermore, the high extensibility of the cotton fabric and its poor durability negated the slight improvement in road performance that the fabric produced.

More recent usage of vegetable fibres in construction include the following.

- 1 Plant fibres bonded together in large numbers (as in wood) have found an application in the production of cement-based composites. Wood-fibre-reinforced cement products are widely available and combine the high tensile strength, impact resistance and workability of wood with the fire resistance, durability and dimensional stability of cement-based materials (Askew, 2000).
- 2 Sisal fibres have been used to reinforce cement-roofing sheets in East Africa since the 1970s (Mwasha *et al.*, 2002).
- 3 Jute, coir and straw continue to be used extensively in erosion control products in the form of nets, meshes, blankets and reinforcement mats which are laid directly on the ground surface (Mandal, 1989; Mandal and Murti, 1989; Rickson, 1994).

Currently, renewed interest in the use of natural fibres as engineered tensile materials in their own right is being led by the automobile industry. When used in appropriate situations, fibres such as flax, hemp and jute are cheaper, have better stiffness per unit weight and have lower impact on the environment than man-made fibres do. This could give considerable benefits by facilitating recycling, reducing energy consumption during vehicle production and improving day-to-day fuel economy. Schuhe (1999) reported that a weight reduction of about 20% has been achieved by using a plant-fibre-reinforced material consisting of a flax-sisal fibre mat embedded in an epoxy resin matrix for the door panels of cars. Furthermore, this substitution has actually enhanced the mechanical properties of the door panels.

Hence, when natural fibres are used in appropriate situations and within a suitable framework or form they can be successfully employed as flexible high-specification tensile elements.

12.4 Agro-industrial fibres

Vegetable fibres are usually classified according to the part of the plant from which they come (Lightweight Structures BV, 2005). Five different categories can be defined.

- 1 *Bast or stem fibres*, which are the fibrous bundles in the inner bark of the plant running the length of the stem. Retting is employed to free the fibres from the cellular and woody tissues, i.e. the plant stalks are rotted away from the fibres. Examples include coir, flax, hemp, kenaf, ramie, rosette and rena.
- 2 *Leaf fibres*, which run the length of the leaves. The fibres are extracted by retting and scraping the pulp from the fibres. Examples include banana, sisal, henequen, abaca, pineapple, cantala, mauritius and phormium.
- 3 *Seed-hair and fruit fibres*, which are produced by a plant to give protection to seeds and fruit. Examples include coir, cotton, kapok and milkweed floss.
- 4 *Core, pith or stick fibres*, which form the low-density spongy inner part of the stem of certain plants.
- 5 *Plant fibres* not covered by the foregoing categories.

Table 12.5 Major potential fibre sources (worldwide) (after Rowell and Jacobson, 2002)

Source	Dry mass (x 10 ⁶ t)
Wood	1750
Straw (barley, flax, oats, rice, rye and wheat)	1145
Stalks (corn, cotton and sorghum)	970
Sugar cane bagasse	75
Reeds	30
Bamboo	30
Cotton staple	15
Core (coir, hemp and kenaf)	8
Papyrus	5
Bast (coir, hemp and kenaf)	3
Cotton linters	1
Esparto grass	0.5
Leaf (abaca, henequen and sisal)	0.5
Sabai grass	0.2

While individual single fibres in all the categories are quite short (except for flax, hemp, ramie, cotton and kapok), fibre bundles can be quite long. For example hemp, coir and kenaf can have fibre bundles as long as 4 m and abaca, mauritius and phormium are about half this length.

Major fibre sources with potential for usage within an agro-industrial context, such as the production of vegetable fibre geotextiles for use in a wide variety of construction scenarios, are indicated in Table 12.5. Hard fibres (such as abaca, sisal, henequen and coir) are relatively unimportant in terms of the global value of international trade. However, they provide significant economic support to the population in certain impoverished and least-developed areas of a number of producing countries. No hard fibre shares a major end use with another and for the most part, no single country produces any significant quantity of more than one hard fibre. Modes of production differ significantly between fibres and between producing regions.

- 1 In African countries, sisal is produced essentially on single-crop holdings.
- 2 Brazil produces sisal as a part of a mixed agriculture.
- 3 Abaca is grown largely in the Philippines as a secondary crop.
- 4 Coir is produced as a by-product of other coconut products.

Around the world there are copious supplies of cheap indigenous fibres which local textile industries can use to replicate common geotextile forms that are made from man-made fibres (Booth *et al.*, 2005). In many cases, these vegetable fibres are waste products, by-products or co-products of crop systems and food production (Ali, 1992). Specific advantages to be gained from the development of vegetable fibre geotextiles using indigenous materials include:

- 1 The raw materials employed are 'environmentally friendly' because they are a renewable resource and they can be returned to the ground without leaving a pollution residue.
- 2 The fibres have low unit cost (at the point of production) and the conversion costs are usually low (Azziz, 2000); however, if the finished product has to be transported any distance to its point of usage, then the expenditure on delivery becomes an excessive proportion of its value.
- 3 Natural fibres have significant initial strength (in some cases they are superior to man-made fibres) and they can be very resistant to harsh environments.
- 4 Suitable materials are often readily available in developing countries and frequently are a major contributor to the local economy (Shamte, 2000).
- 5 They create new markets for agricultural products by introducing additional uses of by-products or new uses for waste agricultural products and increase the range of crops (including some that are currently regarded as weeds) that farmers can grow and sell. Because the new markets are primarily close to the production point, money is attracted into rural areas and regions without incurring major expenditure on transportation.

However, if vegetable fibres are to become widely used to produce high-specification technical materials which supplant products made from man-made fibres, there are factors to be considered which would not be an issue for man-made polymeric materials:


- 1 Any method for extracting the fibres from the parent plants must not cause serious damage (such as overstressing, cracking, weakening and permanent plastic deformation) to the fibres.
- 2 The relevant properties of the fibre must be equivalent or superior to those of the existing chemical fibres used for the same purpose, in terms of manufacturing capability, product quality and consistency, stability (with regard to both ambient conditions and time) and ease of utilization.
- 3 There must be consistent annual production of the fibre. Unfortunately, for any agricultural crop there are a large number of factors (a number of which are not under the agriculturalist's control) which can cause variability of the final product, such as:
 - (a) Climatic conditions during the growing season (usually harvesting has to be done at certain, more or less fixed times of the year).
 - (b) Plant diseases and insect attack.
 - (c) Harvesting methods.
 - (d) Conditions during the harvesting period.
 - (e) Fibre extraction and separation processes.
 - (f) The conditions (temperature, humidity, residence time, etc.) during fibre extraction and separation.
 - (g) Storage method and conditions, and duration of storage.
 - (h) Handling and shipping.

- 4 Inherent reluctance within industry (particularly the construction industry) to use new untried materials.

Of the 2000 or so fibre-yielding plants throughout the world there are some 15–25 plants that satisfy the criteria for commercial fibre exploitation although a number of these are only farmed on a small scale Pritchard (1999). These main fibres are as follows.

- 1 Bast fibres: flax, hemp, jute, kenaf, nettle, ramie, roselle, sunn and urena.
- 2 Leaf fibres: abaca, banana, cantala, date palm, henequen, New Zealand flax, pineapple and sisal.
- 3 Seed and fruit fibres: coir, cotton and kapok.

However, when consideration is given to relevant technical properties (such as strength, extensibility or stiffness, flexibility and durability), ready availability of large quantities at different times within a year, variability of products, manufacturing capacities, etc., the list of promising vegetable fibres is much smaller. Cotton, which has the highest annual production rate, has existing markets and also is not capable of satisfying high-strength requirements when buried in the ground (but it still can be used as a weft ‘distribution’ fibre in geotextile products). Currently the most promising fibres (in order of decreasing annual production tonnage) seem to be jute, flax, coir, sisal, hemp and abaca, (Tables 12.6, 12.7, 12.8, 12.9 12.10 and

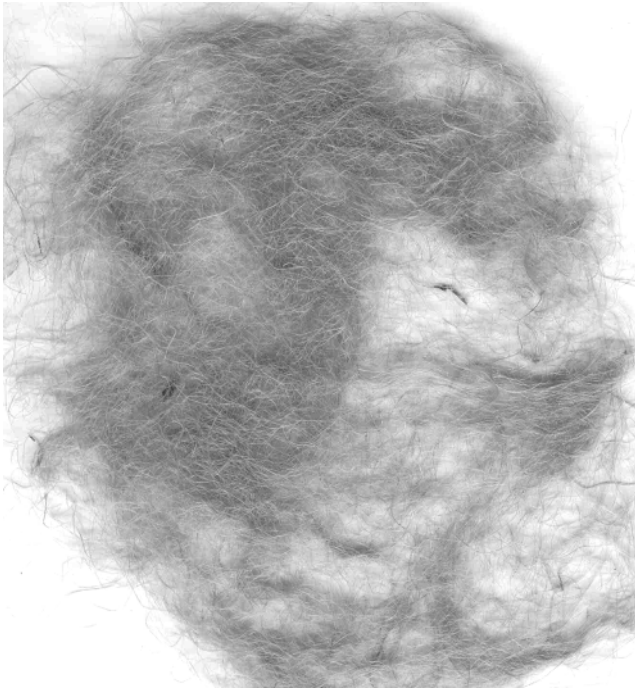


12.5 Jute fibres.

Table 12.6 Jute fibres

Growing	Bast fibre; annual plant; stem diameter, 20 mm; stem length, 2.5–3.5 m
Production	Grown in the India subcontinent, the Far East, Africa, Asia, and Central and South America. Easily cultivated and harvested. Plants easily damaged by excessive heat, drought, rainfall and floods and by pests (semilooper, mite, caterpillar and apion). Second most important fibre worldwide in terms of cash and acreage. Fibre extraction – retting. Oil and water emulsion is added to soften the fibre for spinning into yarns
Uses	Cheap and used in great quantities. Ropes, bags, sacks and cloths. Erosion control applications include ‘geojute’ and ‘soil-saver’
Properties	Poor tensile strength, not as strong as hemp and flax nor as durable. If kept dry, will last indefinitely. Fibre deteriorates rapidly when exposed to moisture. High initial deformation modulus, but very little recoverable elasticity; exhibits brittle fracture



12.6 Coir fibres.

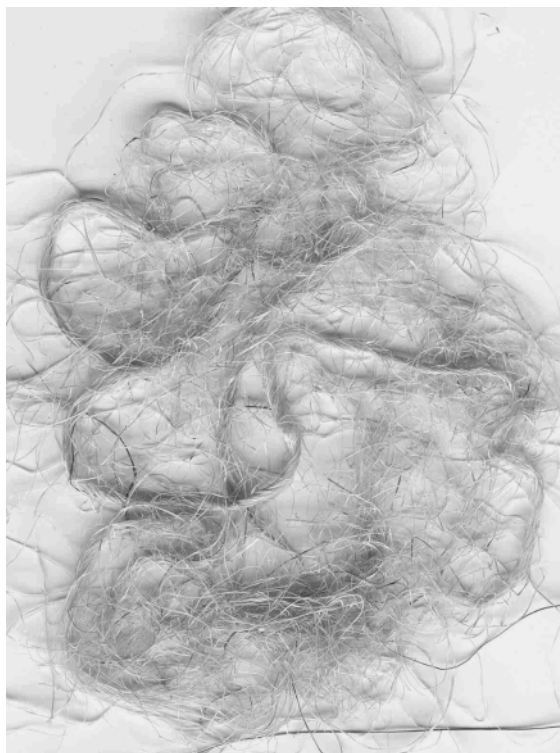

12.7 Sisal fibres.

Table 12.7 Flax fibres

Growing	Bast fibre; annual plant; stem diameter, 16–32 mm; stem length, 0.9–1.2 m; harvested after 90 days
Production	Grown predominantly in Russia (80%), China, Egypt, Turkey, Philippines, Malaysia and UK. Apart from fleas and beetles, flax is not generally vulnerable to pests. Third most important fibre worldwide in terms of cash and acreage and ranks fourth for the total fibre production. Fibre extraction – retting. After retting, fibre is broken away from the stems and combed
Uses	Linen, twines, ropes, fishing nets, bags, canvas and tents. Tow fibre, and high-grade paper, i.e. cigarette paper and banknotes. Linseed oil and linseed flax fibre
Properties	Fibre strength increases when wet. Physical and chemical properties are superior to cotton. Relatively inextensible fibre; more elongation obtained when dry. One of the highest tensile strengths and moduli of elasticity of the natural vegetable fibres. Density same as polymers



12.8 Hemp fibres.

Table 12.8 Coir (coconut fibres)

Growing	Seed and fruit fibre; perennial plant; fruit picked every alternate month throughout the year; economic life, 60 years. The fibre is produced from the coconut husk
Production	Grown in India (22%), Indonesia (20%), Sri Lanka, the Far East, Brazil, the Philippines, East Africa, Latin America and throughout the Pacific regions. Fibre derives from the nut of a tree that has an economic life of 60 years. Grows on a wide range of soils; prefers high humidity and plenty of sunlight. Ranks fourth in world annual production. Fibre extraction – retting; dehusked manually or mechanically
Uses	It has many established uses, including as a filling in upholstery, mattresses and car seats and in the manufacture of doormats, rugs, brooms and brushes, ropes and cordage
Properties	Abrasive and rot resistant under wet and dry conditions and retains a high percentage of initial tensile strength. Resistant to degradation by sea water; endures sudden pulls that would snap much stronger ropes. Erosion control products from coir are well established in applications that demand limited life at low cost

Table 12.9 Sisal fibres

Growing	Leaf fibres; perennial plant; leaves, 1–2 m long, each containing about 1000 fibres
Production	Grown in Central America, Mexico, Brazil, the Philippines, East Africa and Venezuela. Prefers temperatures between 27 and 32 °C; optimum rainfall, 1200–1800 mm but can withstand droughts; requires substantial amounts of strong sunlight; waterlogging and salinity are fatal to sisal. The fibre extraction method includes retting (soaking in water), followed by beating and scraping of the leaves so that only fibres remain and all other parts are washed away by water. The fibres are then thoroughly dried and bleached in the sun or oven dried. Sisal is not generally prone to pest attack and, provided that the climatic conditions are not unfavourable, a consistent annual harvest and fibre product is obtained
Uses	Twines, ropes (widely used in marine environments), rugs, sacking, carpets, cordage and agricultural. Tow (waste product) used for upholstery. Traditionally used primarily for harvest (baler) twine and other cordage; the proportion being used for traditional purposes is decreasing and more is being used for new uses such as carpets and paper
Properties	Sisal is resistant to salt water. Shorter, coarser and not quite as strong as abaca. Also lower breaking load and tends to break suddenly without warning. Can be spun as fine as jute but stiff and somewhat inflexible

Table 12.10 Hemp fibre

Growing	Bast fibre; annual plant; stem diameter, 4–20 mm; stem length, 4.5–5 m; harvested after 90 days
Production	Grown in Russia, Italy, China, Yugoslavia, Romania, Hungary, Poland, France, Netherlands, UK and Australia. No pesticide protection required for growth. Fibre extraction – retting. Separation of the fibre from the straw can be carried out mechanically (green hemp)
Uses	Ropes, marine cordage, ships sails, carpets, rugs, paper, livestock bedding and drugs
Properties	Not weakened or quickly rotted by water or salt water. Stronger, more durable, stiffer, more rigid and coarser than most vegetable fibres. Suitable for weaving of coarse fabric

12.11, respectively). Figures 12.5, 12.6, 12.7 and 12.8 show jute, coir, sisal and hemp fibres, respectively.

12.5 Vegetable fibre characteristics

Table 12.12 contains indicative data about fibre composition and physical charac-

Table 12.11 Abaca or manila hemp fibres

Growing	Leaf fibre; perennial plant; 12–30 stems per plant; leaves, 2–4 m. Plant life, 10–20 years; productive life, 1–8 years; harvest 3 stalks every 4–5 months
Production	Grown in the Philippines (85%) and Ecuador (15%). Needs a warm climate, shade, abundant moisture (rainfall of 2.5–3.0 m distributed uniformly through the year) and good drainage. Too much heat causes damage to leaves and fibres. Attacked by brown aphids, corn weevil and slug caterpillar. Relatively small annual production tonnage. Fibre obtained from the stem of the leaves and not the expanded portion of the leaf. Fibre extraction – retting. Fibre extracted by separating the ribbons of the fibre from the layers of pulp and then hung to dry
Uses	Marine cordage (naturally buoyant), fishing nets, ropes, tea bags, coffee filters and currency notes. Was traditionally used for ropes and other cordages but now is almost entirely pulped for special papers
Properties	Good water-resisting properties; hygroscopic; not affected by salt water. Superior to flax; better than hemp for marine ropes and hawsers. Very light weight. Strong and sufficiently flexible to provide a degree of give when used in ropes

teristics. It is very difficult to quantify and assign precise values to the characteristics of individual vegetable fibres because of the inherent variability of their dimensions as a result of their agricultural origins. Within the textile industry, this difficulty is overcome by measuring a form of average value, i.e. it is normal practice to quote strength and tensile modulus in terms of tex which is the mass in grams of 1 km of fibre. Hence, any strength or modulus will be based on the behaviour of a number of fibres rather than on individual units. For instance, the tenacity (ultimate load per tex) for cotton is in the region of 0.35 N/tex (this corresponds to an ultimate tensile stress of about 0.5×10^6 kN/m²) but individual fibres can easily have tensile strengths within $\pm 20\%$ of this value. For flax, abaca and sisal the tenacity is between 0.4–0.6 N/tex (corresponding to a tensile strength of $(0.4\text{--}1.0) \times 10^6$ kN/m²); the tenacity of ordinary chemical fibres (polyester) is around 0.4 N/tex (Pritchard, 1999). Carefully separated individual flax fibres have a strength of around 10^6 kN/m² and modulus of 80×10^6 kN/m (Leflaive, 1988), i.e. of the same order as Kevlar, a very-high-strength chemically modified polyamide fibre.

It is readily apparent that economically-viable vegetable fibre fabrics (a collection of numerous fibres) cannot be guaranteed to match the tensile properties of steel or solid polymeric strips or sheets (Table 12.13); synthetic fibres have a high strength, high tensile modulus and limited elongation to failure. However, natural fibre products can be manufactured which have similar technical characteristics to geotextiles made from man-made fibres (Table 12.13). On the other hand, fibres such as cotton, jute and coir (woven and fibre form) have a number of advantageous characteristics which are not possessed by man-made fibres.

Table 12.12 Dimensions and chemical composition of some common agro-fibres (from Esau, 1977; livessalo-Pfaffli, 1995 and Han and Rowell, 1997)

Type	Cellulose (%)	Lignin (%)	Mean length (mm)	Mean width (mm)
Abaca	56–63	7–9	6	0.024
Bamboo	26–43	21–31	2.7	0.014
Cereal straw	31–45	16–19	1.5	0.023
Coir	35–63	30–45	2.5	0.020
Coniferous wood	40–50	26–34	4.1	0.025
Corn straw	32–35	16–27	1.5	0.018
Cotton	85–90	0.7–1.6	25	0.020
Deciduous wood	38–49	23–30	1.2	0.020
Esparto	33–38	17–19	1.9	0.013
Hemp	57–77	9–13	20	0.022
Kenaf	44–57	15–19	2.6	0.020
Papyrus	38–44	16–19	1.8	0.012
Rice straw	28–36	12–16	1.4	0.008
Seed flax	43–47	21–23	30	0.020
Sisal	47–62	7–9	3.3	0.020
Sugar cane bagasse	32–37	18–26	1.7	0.020
Wheat straw	33–39	16–23	1.4	0.015

Table 12.13 Stress–strain data for some reinforcing materials

Reinforcing material	Ultimate tensile strength ($\times 10^3$ kN/m ²)	Modulus of elasticity ($\times 10^3$ kN/m ²)	Strain at failure (%)
Steel strip	410	210 000	5
Plastic grid	520	5 300	15
Geotextile	85	850	20
Jute rope	49	340	33
Coconut rope	14	16	85

- 1 They can absorb and store moisture.
- 2 Their natural flexibility allows them to conform closely to a soil profile.
- 3 Their bulk gives a high protective cover–weight ratio.
- 4 Their production is compatible with the surrounding environment and does not use scarce resources or cause pollution.

To appreciate the similarity of technical characteristics, the ultimate strength, extension at failure and tensile modulus of various natural fibres have been expressed as a percentage of the values for polyester and are presented in Table 12.14. This table clearly demonstrates the following.

- 1 Many vegetable fibres have similar ultimate strengths to polyester (as indicated by tenacity in Table 12.14).

Table 12.14 Natural fibre properties as a percentage of polyester values (after Bisanda and Anselm (1992), Chand *et al.* (1986, 1988) and Mukherjee and Satyanarayana (1984))

Natural fibre	Tenacity	Failure elongation	Tensile modulus
Abaca	156	12	278
Coir	33	20	33
Cotton	76	20	78
Flax	111	12	211
Hemp	100	12	222
Henequen	56	20	167
Jute	89	8	189
Ramie	118	16	167
Sisal	89	12	222
Viscose	44	80	56
Wool	33	140	22
(Polyester)	100	100	100)

- 2 The rupture strain of vegetable fibres is much smaller (by a factor of between 5 and 8 approximately) than that of polyester.
- 3 The tensile moduli of many 'fresh' vegetable fibres are significantly higher than that of polyester.

However, in order to utilize the foregoing advantageous properties in engineered design, it must be remembered that all natural fibres will biodegrade in the long term as a result of the action of the micro-organisms and this must be clearly accounted for within any design methodology.

The problem of durability of natural fibres is complex and contradictory, and examples of both very fast decay and remarkable stability are cited. However, the material degradation rate is determined by the actual combination of relevant factors (ambient moisture content, degree of acidity or alkalinity, etc.) rather than just on the factors themselves and, for natural fibres, the most important factor is whether the ambient conditions favour the growth of bacteria which will feed on the fibres. Hence, natural fibres have been used extensively to make sails and fishing nets, which have performed satisfactorily under hostile conditions (saline water, periodic wetting and drying) but within a relatively sterile environment.

In the 1920s and 1930s, an extensive investigation was undertaken by the then Imperial Institute into the suitability of sisal for the manufacture of marine cordage. Numerous samples of sisal rope were subjected to cyclic wetting (with seawater) and drying over a period of 12 months. Table 12.15 shows results from a preliminary study of the percentage loss of tensile strength of three types of sisal rope (Anon., 1927). These data show the following two potential concerns with regard to the use of this type of material to create LLGs.

- 1 There are significant differences between the durability characteristics of the three ropes types (and each value is in fact an average of several values).

- 2 The ropes exhibited high rates of loss of tensile strength and integrity with immersion time.

Subsequent investigations of the influence of exposure conditions on the loss of tensile strength of sisal ropes showed similar trends for specimen subjected to cyclic wetting with seawater (Table 12.16) (Anon., 1935). However, these investigations also showed the following.

- 1 Sisal ropes kept in relatively dry conditions, i.e. in conventional covered storage sheds, lost very little tensile strength with time.
- 2 Sisal ropes subjected to cycles of wetting (with rainwater) and drying (by wind and sunlight) underwent progressive strength loss with time (at a similar rate to that determined more recently (Pritchard, 1999). However, the time-dependent strength loss was at a sufficiently slow rate to be able to satisfy economically typical durability requirements for LLGs.
- 3 Sisal ropes which were tarred in the usual manner of the time, i.e. by being passed through a bath containing tar, and were then immersed in seawater showed a much lower rate of strength loss than the untreated rope.

In more recent times, further research has been conducted with a view to reducing the bio-degradation rate of natural fibres. For instance, rotproofing of cotton and flax used in tarpaulins, tents, etc., could be achieved by treating the fabrics with fungicides such as pentachlorophenol esters (Hamlyn, 1990); the average life of

Table 12.15 Percentage loss of tensile strength of sisal ropes immersed in seawater

Rope type	Loss after the following exposure periods			
	4 months	6 months	9 months	12 months
East African sisal, quality 1	35	47	51	63
East African sisal, quality 2	51	60	65	75
Manila hemp	42	51	53	69

Table 12.16 Percentage loss of tensile strength of sisal ropes according to exposure

Exposure conditions	Loss after the following exposure periods			
	2 months	4 months	6 months	9 months
Immersion in seawater	16	22	57	76
In covered storage	0	4	4	4
Uncovered, on the laboratory roof	1	4	11	12

jute bags was increased sixfold when the fabric was treated with copper salts such as copper sulphate, copper ammonium sulphate, copper acetate or copper naphthenate (MacMillan, 2005); sisal fibres treated with toluene-di-isocyanate derivatives showed significantly greater durability and lower water absorption than untreated fibres (Mwasha, 2005). However, the foregoing forms of treatment vastly reduce the 'environmental friendliness' of vegetable fibres. The real key to developing geosynthetics from biodegradable natural fibres is the concept of designing by function, i.e. identifying the functions and characteristics required to overcome a given problem and then selecting appropriate fibres and manufacturing the product accordingly. When correctly designed natural fibre materials can compete with synthetic materials, sometimes they will even have superior performance.

Natural fibre geotextiles may be used where the design life of the fabric structure is relatively short or where strength or integrity requirements decrease with time – note that the definition of a short-term time scale varies from site to site and from application to application.

12.6 Erosion control

Currently, the major use of natural fibre geotextiles is in the erosion control industry (Mitchell *et al.*, 2003). Soil erosion is the removal of surface layers of soil and it involves a process of both particle detachment and particle transport by the disturbing agencies. Erosion is initiated by drag, impact or tractive forces acting on individual particles of soil. The two most common agents of erosion are rainfall and wind. This erosion is controlled by a number of soil, climatic and topographical factors including intensity and duration of precipitation, ground roughness, length and steepness of slope, inherent soil strength, and type and extent of cover (Morgan *et al.*, 1984; Gray, 1991; Rao and Balan, 2000). Surface erosion by water commences when the kinetic energy of rainfall is transferred to individual soil particles, breaking the bonding between particles and moving the particles upwards and laterally. On level ground the net transport of soil particles will be almost zero since the soil particles splash uniformly in all directions. However, on a slope, more soil will be transported downhill by the impact (Ellison, 1944).

If rainfall exceeds the infiltration capacity of a soil, continued precipitation results in overland flow which begins at a shallow depth (thin-film flow). The runoff water collects in small rivulets which may erode very small channels (rills). These rills may eventually merge into larger and deeper channels (gullies). Figure 12.9 shows gullies formed by water running down the surface of a tip of waste material (which is a difficult medium on which to establish good vegetation cover). If the soil is permeable and has a favourable structure, infiltration will be enhanced and overland run-off will be reduced. If the energy of the falling rain can be absorbed or dissipated by vegetation or by impacting on some other soil cover or



12.9 Eroded surface of a waste tip (note the sparseness of the vegetation).

surface obstruction, energy transfer to the soil particles which results in detachment will be reduced and there will be a consequent reduction in soil erosion. Slowing the flow of water downslope reduces the soil transport capacity of the thin sheet flow, thereby minimizing the displacement of dislodged soil particles.

Ground erosion is often the result of human activity, e.g. formation of cuttings and embankments when roads are built, creation of waste tips, and placement of final caps over engineered landfill sites. Promotion of vegetation on the final caps of landfill sites is very important for long-term effectiveness of the cap (prevention of water infiltration and prevention of uncontrolled gas escape, which requires the cap to be structurally intact and stable). Figure 12.10 shows a vegetable fibre net placed on top of a landfill cap to provide anchorage for vegetation.

It has been estimated that soil erosion by water and soil erosion by wind is responsible for about 56 and 28%, respectively, of worldwide land degradation (Wibisono, 2000). Furthermore, the US Army Corp of Engineers has estimated that in the USA alone the damage caused by soil erosion costs at least £140 million annually (Wibisono, 2000).

12.6.1 Surface erosion control

Erosion control measures can be classified into three broad categories (with the applicability of the method depending on the classification of the site): agronomic, soil management and mechanical (Ingold and Thomson, 1990).

In nature, vegetation (which is in effect an agronomic erosion control solution)



12.10 Vegetable fibre net on a landfill final cap.


is the major factor in the prevention of erosion of soil slope by the following mechanisms.

- 1 Binding and restraining soil particles in place (root action).
- 2 Filtering soil particles out of run-off (performed by stems and organic litter).
- 3 Intercepting raindrops (canopy action).
- 4 Retarding velocity of run-off (undertaken by stems and organic litter).
- 5 Maintaining infiltration (root action).


Artificial ground cover is the most common solution for ‘interventional’ erosion protection with dual functions of blocking out the light (thereby depriving weeds of growth potential) and providing a favourable microclimate for establishment of imported plants. This solution is a mixture of soil management and mechanical stabilization. The ground cover ranges from inert facings (concrete and stone layers), to organic mulches (hay, wood chips, straw, etc.) and live materials (seedlings and cuttings). Different types of ground cover for erosion control are outlined in Fig. 12.11 (as explained in detail by Theisen, 1992).

When geosynthetics are used as erosion control products, they are intended to simulate the properties of vegetation and also to provide assistance to vegetation to establish itself permanently. Figure 12.12 shows a new slope which has been covered with a vegetable fibre geotextile to provide anchorage and ‘agricultural support’ for vegetation. Different types of geotextile simulate different functions of natural vegetation cover as indicated in Table 12.17.

The prime requirements of a mulch is to provide tight ground cover to suppress weed growth and to enhance the growth of vegetation by providing a beneficial microclimate around plants. Thus, there is no need for longevity, and strength is needed primarily for handling purposes.

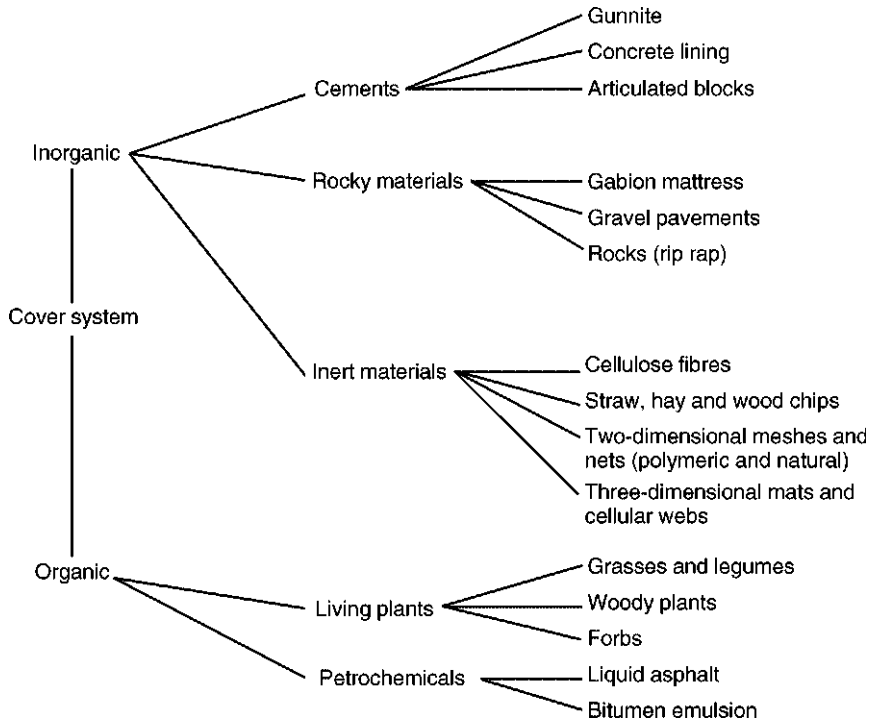

12.11 Surface erosion control methods.

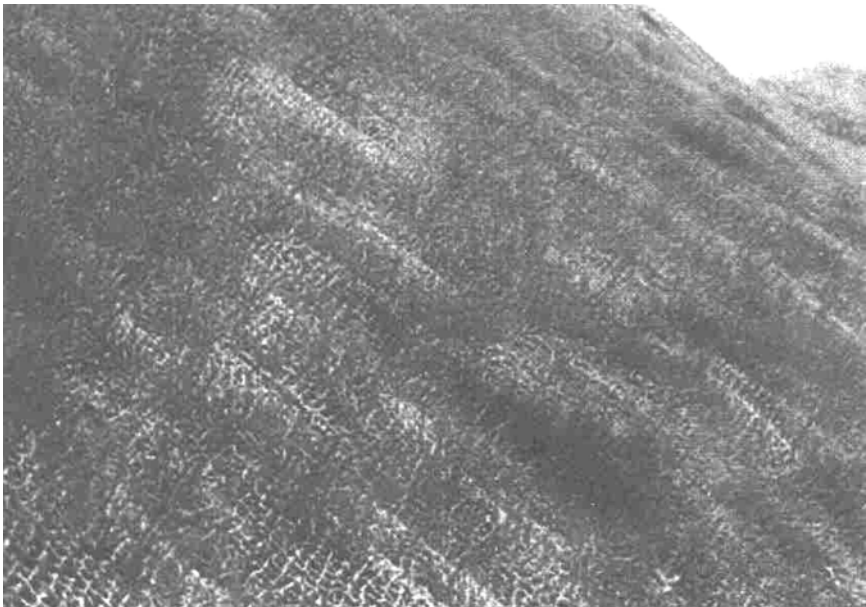

12.12 Vegetation growing through netting covering a new slope.

Table 12.17 Simulation of functions of vegetation (adapted from Rao and Balan, 2000)


Geotextile type	Degree of similarity ^a for the following components of natural vegetation			
	Canopy	Stems	Roots	Litter
Woven meshes (often natural fibres)	H	H	L	M
Two-dimensional mats (often natural materials)	H	M	L	H
Three-dimensional meshes (often using man-made materials)	L	L	H	L
Geocells, geowebbs (synthetic materials)	L	L	M	L

^aH, high similarity to nature; M, medium similarity to nature; L, low similarity to nature.

Geotextiles used in soil erosion control are often very effective in controlling rates of soil detachment by raindrop impact. Geotextiles used in soil erosion control can be natural or synthetic materials and may be installed on the surface or buried within the ground. Like vegetative canopies, geotextiles will intercept and store rainfall water. The composition of some products (especially the natural fibre geotextiles such as coir) imparts a roughness to run-off in much the same way as vegetation stems. Buried geotextiles simulate the root effect and biodegradable geotextiles act as a mulch in controlling soil erosion. Geotextiles reduce soil erosion by absorbing the impact and kinetic energy of falling raindrops and checking surface run-off. Seeds and vegetation are protected from being washed away.

The ability of natural fibres to absorb water and to degrade with time (thereby contributing nutrients to vegetation and eliminating obstruction of growth of vegetation) are the prime properties which give their products an edge over synthetic geotextiles for erosion control purposes. The 'drapability' of natural fibre geotextiles allows them to conform closely to the terrain, i.e. to follow the contours of a slope and to stay in intimate contact with the soil. Hence, vegetable fibre geotextiles can be used where vegetation is considered to be the long-term answer to slope protection and erosion control. They have a number of inherent advantages.

- 1 They give protection against rainsplash erosion.
- 2 They have the capacity to absorb several times their own weight as indicated in Fig. 12.13.
- 3 They reduce the velocity of run-off and hence its erosive effect. Because of their thickness and the apertures and depressions of natural-fibre geotextiles function as a series of small check dams and weirs.
- 4 They maintain humidity and moisture in the soil (by covering the ground) and in the air directly above the ground (by retaining water within apertures and within themselves).

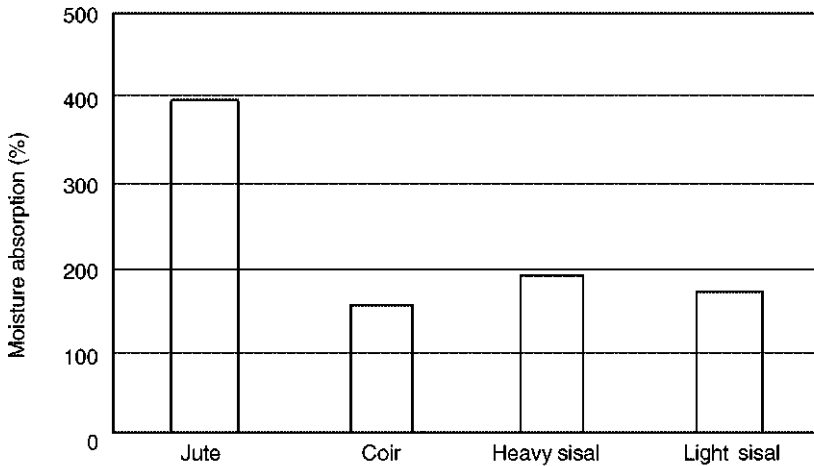

12.13 Water absorption capacity of natural fibres.

- 5 They mitigate against extreme temperature variation of the soil (by providing shade during the day and insulating cover at night).
- 6 They biodegrade, adding useful mulch to the soil, and, because they have not been treated with chemicals, there is no associated ground pollution.


Even though synthetic geotextiles last for a long time in surface erosion control applications, studies have indicated that they are less effective than their natural fibre counterparts (Rickson, 1994). However, some jute-based geotextiles have been found to degrade completely within a year (which is usually too short a time for full development of self-sustaining vegetative cover). On the other hand, coir-based geotextiles have been found to persist and retain their erosion control functions for at least three years.

The vast majority of natural fibre erosion control products are applied to the surface of the ground but there has been some usage of these products to control riverbed erosion. Levillain (2000) described how vegetable fibres were used to protect the Pont de Pierre in Bordeaux when it was threatened by severe erosion of the riverbed adjacent to the foundations of the bridge. The protection employed involved placing prefabricated gabions on top of polymeric geotextiles (acting as a filter) laid on the riverbed. The gabions were then covered with a heavy vegetable fibre 'carpet' for a distance of 35 m upstream and downstream of the bridge foundations over the entire width of the Garonne river.

12.6.2 Erosion control materials

Products can be classified generally as follows.


- 1 *Nettings*. These are two-dimensional woven natural fibres or geosynthetic (polymeric) biaxial mattings (Fig. 12.14). After the proposed slope is seeded

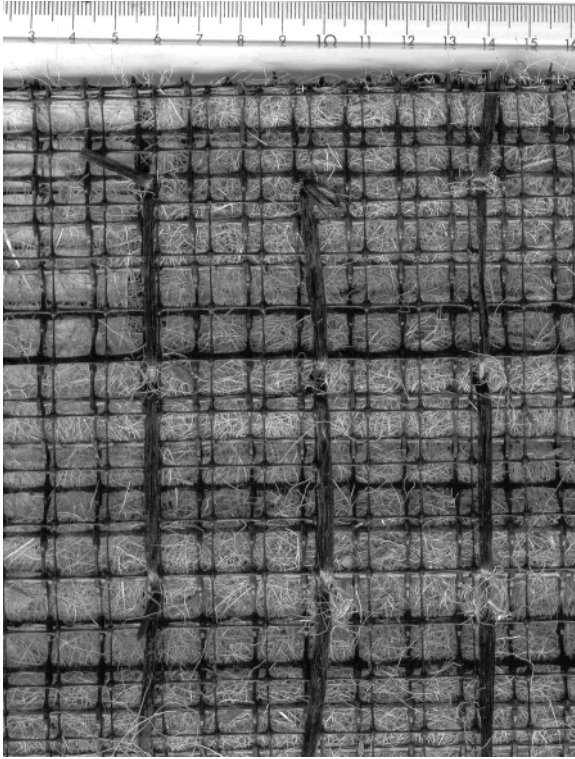


12.14 Composite natural fibre (coir) and geosynthetic erosion control matting.

and/or mulched, these materials are laid and fixed in position. Used with loose mulch they yield good performance for moderate conditions (slope angle, slope length and run-off condition). This type of product generally has a design working life of one or two growing seasons.


- 2 *Meshes*. These are open weave geotextiles formed into a two-dimensional matrix (Fig. 12.15 and Fig. 12.16). The construction of these materials enables erosion control to be provided with or without underlying loose mulch layer. They generally have higher tensile strength than nettings and can be used on steeper slopes.
- 3 *Blankets*. These are constructed of various degradable organic or synthetic fibres that are woven, glued or structurally bound with nettings or meshes (Fig. 12.17). The most widely used erosion control blankets are made from straw, wood shavings, coconut fibre and polypropylene stitched or glued to nettings or meshes. Some materials are available with seeds pre-incorporated into their structure. They are rolled out in intimate contact with the soil surface and anchored with staples or pegs. Applicable to sites requiring

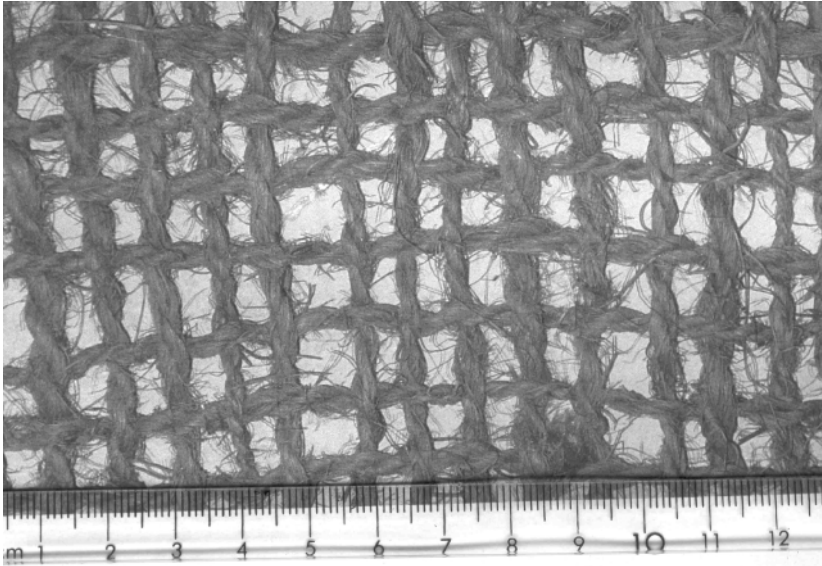

12.15 Coir erosion control mesh.

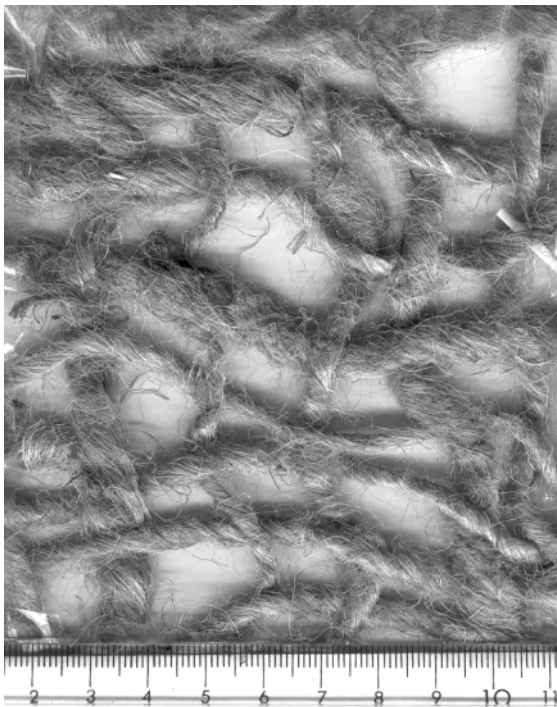

12.16 Jute erosion control mesh.

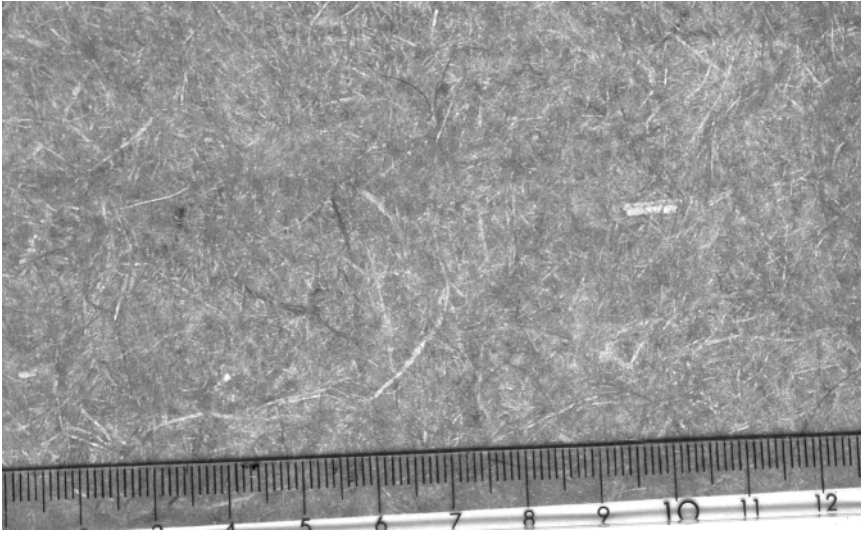

12.17 Erosion control blanket (made from coir fibres).


greater, more durable and/or longer-lasting erosion protection, they can be used on gentle to steep slopes. Products usually have a design functional life span of 1–5 years.

Geotextiles made purely of jute fibres (also known as geojute) have been in use since the 1950s when an open-meshed woven fabric was used in Europe and the USA to cover exposed soil surfaces with a view to promoting vegetation growth and thus arrest soil erosion (Mandal, 1988). Geojute has many limitations as a geosynthetic, primarily because its strength and durability are too limited for harsh applications such as steep slopes, high-altitude slopes or waterways; it degrades particularly quickly in very humid conditions. On the other hand, coir has only been used in geotextiles over the past 25 years approximately but it is a much more durable material; it takes coir around 15 times longer than cotton and around seven times longer than jute to degrade completely.

12.6.3 Erosion control material installation

The material is usually shipped to site in rolls. When wet, the natural fibre materials should never be stored indoors without very good ventilation as otherwise there will be promotion of microbial action, decay and loss of strength. If the material is kept outside before installation, it should be protected against rainfall and kept clear of the ground to provide air circulation.

A drawback to the use of natural fibre geotextiles is that storage for a prolonged period requires significant attention to temperature, humidity, air circulation and

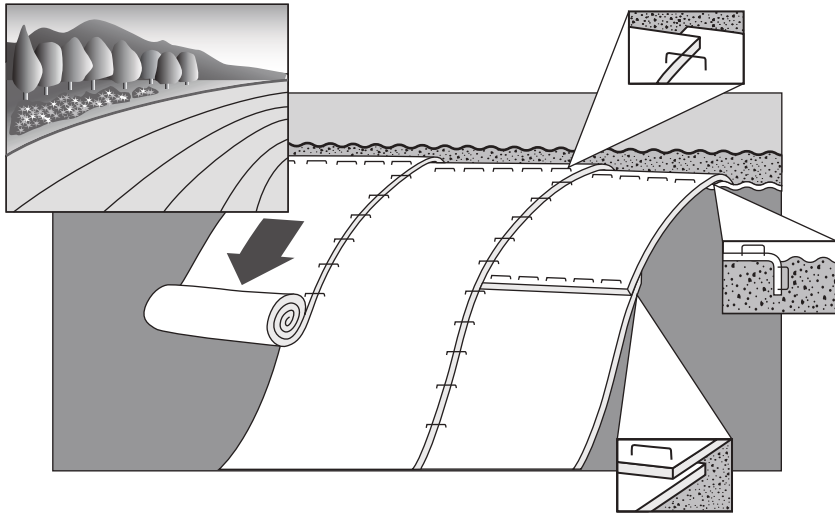

12.18 Installation of erosion control materials (after Rao, 2000).

stacking to minimize risk of moisture gain. Whilst the moisture absorption or retention capacity of natural fibre geotextiles is advantageous once they are in position, it should be borne in mind that, if rolls of material are allowed to absorb water before installation, their weight will increase significantly and they will become difficult to handle and work with.

Before installation of the product, the topsoil on the slope should be worked to a fine tilth free of clods or loose stones. Seed, mulch and fertiliser should be distributed evenly over the prepared soil (an alternative is to apply a hydromulch, i.e. a wet mix of mulch and seeds which is sprayed on to the protected surface). Wherever possible the geotextile should be applied by unrolling down the slope; however, if required the geotextile can be run along the slope. The geotextile is secured with staples or pegs (at least 150 mm long) driven into the ground (Fig. 12.18). At the crest and toe of the slope the fabric is usually anchored by burying it in a trench (about 500 mm wide and 300 mm deep) and additional anchorage is achieved by driving in a row of staples or pegs along the crest and toe. Longitudinal edges of rolls are overlapped by 100 mm and stapled or pegged at 500–1000 mm centres according to the risk of lifting of the fabric (possibly due to the exposed nature of a particular site). Roll junctions are made by lapping the end of the upslope roll 200 mm over the end of the downslope roll and securing the overlap with a row of closely spaced pegs or staples (at around 200 mm centres) as illustrated in Fig. 12.18.

12.7 Basal reinforcement of embankments on soft soil

One of the standard and most effective ground improvement techniques used with soft soil subgrades is surcharging or preloading. This process usually involves

constructing a temporary embankment which loads the ground and induces consolidation and settlement. The imposed load is left in place until the voids ratio of the ground has been sufficiently reduced and then it is removed. Basal reinforcement (usually in the form of geotextiles composed of man-made fibres) is frequently needed to enable an economic stable embankment to be built on such weak subgrades. As the foundation soil consolidates, owing to the weight of the embankment, it gains in shear strength. Hence, this basal reinforcement is a classic example of a decreasing need for functionality (in this situation, the input of a restraining horizontal force) of a geotextile with time. LLGs would be an extremely effective method of providing the basal reinforcement if readily available indigenous vegetable fibres could be used to manufacture these materials. A practical example of the technical, social and human benefits of the foregoing approach would be the use of coir and banana fibres (both readily available in Sri Lanka) to make reinforcing geotextiles to enable railway embankments to be rebuilt on the very weak, highly compressible soils created in the coastal areas of Sri Lanka by the tsunami of December 2004 (Sarsby, 2005; Indraratna *et al.*, 2005).

12.7.1 Analytical approach

The Factor of Safety FOS_U of an unreinforced embankment slope is equal to the ratio of the total resisting moment (due to the shear strength of the soil) to the total disturbing moment (due to the weight of the potentially unstable soil mass), i.e.

$$FOS_U = \frac{M_R}{M_D} \quad [12.1]$$

If the potentially unstable soil mass is subdivided into a series of vertical slices, then

$$M_R = \sum TR \quad [12.2]$$

and

$$M_D = \sum WR \sin \beta \quad [12.3]$$

where

T = shearing resistance on the base of a vertical slice of material

R = radius of the circular failure surface

W = weight of the slice

β = inclination of the base of the slice

Thus

$$FOS_U = \frac{\sum TR}{\sum WR \sin \beta} \quad [12.4]$$

If soil reinforcement is incorporated into the interface between the clay soil and the embankment then it will provide an additional resisting moment M_T which helps to maintain stability of the slope, so that the global factor of safety FOS_G of the reinforced situation is


$$FOS_G = \frac{M_R + M_T}{M_D} = \frac{\Sigma TR + M_T}{\Sigma WR \sin \beta} \quad [12.5]$$

If the horizontal force provided by the reinforcement is H and its lever arm about the centre of rotation of the potentially unstable mass is L , then

$$FOS_G = \frac{\Sigma TR + HL}{\Sigma WR \sin \beta} = \frac{\Sigma T}{\Sigma W \sin \beta} + \frac{L}{R} \frac{H}{\Sigma W \sin \beta} \quad [12.6]$$

Construction of the embankment will induce excess pore pressures in the foundation soil and, as these dissipate, the shearing resistance T will increase. Consequently, if a constant global factor of safety is maintained, the force H to be provided by the reinforcement will decrease. To quantify this behaviour, a parametric study of the time-dependent reinforcement requirements of an embankment built on top of normally consolidated saturated soft clay was undertaken. The embankment was assumed to be composed of free-draining fill and a range of typical face slopes (of vertical:horizontal from 1:2 down to 1:5) was analysed. Consolidation of the foundation soil (assuming that the embankment fill was placed instantaneously) was accounted for by using one-dimensional consolidation theory and the pore pressure regime in the foundation (from the onset of loading due to the embankment until consolidation was complete) was represented by a series of isolines for each consolidation period.

A rotational stability analysis was used to backcalculate the reinforcement force H required to achieve a particular Factor of Safety at any given time after construction of an embankment. To undertake the back calculation, a target global Factor of Safety was first selected. For each specific embankment configuration, i.e. slope angle, typical values of geotechnical parameters, consolidation time, etc., a value of the basal reinforcement force H was assumed and a rotational failure analysis was undertaken (using computer software incorporating the Bishop simplified method) to determine the most critical failure circle and the resultant global Factor of Safety. If this backcalculated Factor of Safety was not equal to the defined target value, then the initially assumed basal reinforcement force was altered and the failure analysis was performed anew. This cycle of assumption and analysis was repeated until the assumed reinforcement force provided the target global Factor of Safety. The plot of this force against time then defines the 'time-strength envelope' required of reinforcement to be used in this situation. Global Factors of Safety of 1.0, 1.2 1.5 and 2.0 and four different slopes of vertical:horizontal equal to 1:2, 1:3, 1:4 and 1:5 were considered (Mwasha, 2005).

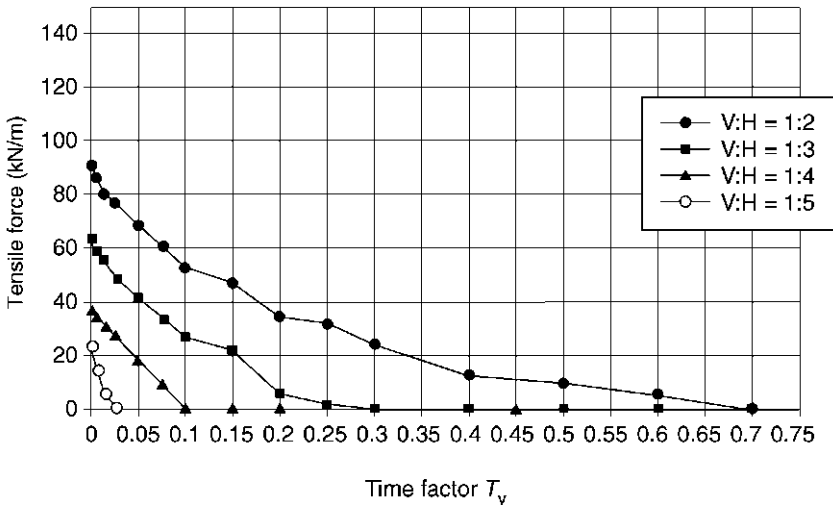


12.19 Time–strength envelopes for a global factor of safety of unity: V, vertical; H, horizontal.

12.7.2 The time–strength envelope

For each case analysed, the tensile force in the basal reinforcement shows a progressive decrease with time after embankment construction; Fig. 12.19 shows the variation in computed horizontal reinforcement force needed to achieve a global Factor of Safety of unity for slopes ranging from 1:2 to 1:5. The curves shown in this figure represent the ‘time–strength envelopes’ that have to be satisfied by any LLG used as basal reinforcement. For a global Factor of Safety of unity, the following points are evident:

- 1 The stabilizing force to be provided by the geotextile drops rapidly with time as the foundation soil consolidates.
- 2 For the steepest slope (1:2), the tensile force to be provided by the geotextile falls to 50% of its initial value within a time factor of 0.15 approximately (for a typical clay foundation with a C_v of $1 \text{ m}^2/\text{year}$ this would correspond to just under $1\frac{1}{2}$ years).
- 3 For the steepest slope, the basal reinforcement becomes totally redundant at a time factor of about 0.7 (equivalent to around 6.5 years of consolidation). For flatter slopes, the reinforcement only has to have a very short working life, i.e. around 2.5 years, 0.9 years and 0.3 years for 1:3, 1:4 and 1:5 slopes, respectively.

All the time–strength envelopes in Fig. 12.19 indicate an approximately exponential decrease in the required horizontal force with time factor (which is directly proportional to the time that has elapsed since the start of consolidation of the

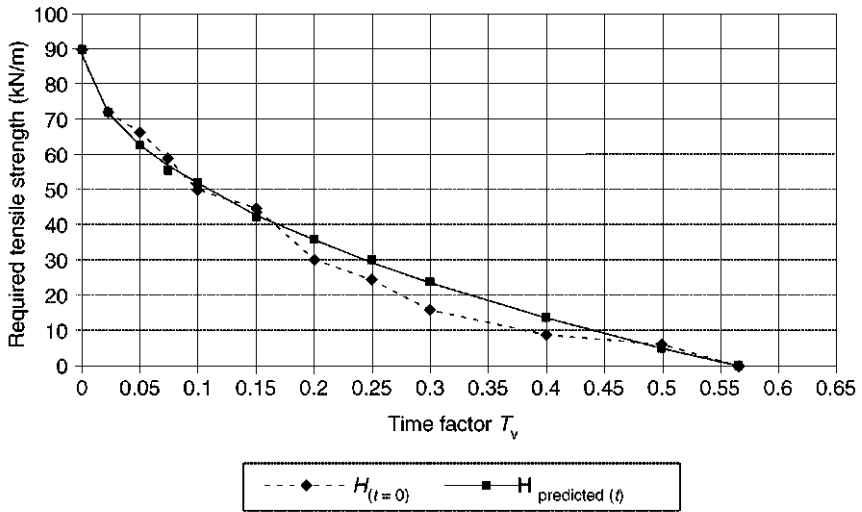

12.20 Comparison between a backcalculated time–strength envelope and the empirical equation.

foundation soil). Consequently, it has been proposed (Sarsby, 2006) that for practical purposes these envelopes could be represented by an equation of the form

$$H = H_{(t=0)} - ST_v^n \tag{12.7}$$

where

$H_{(t=0)}$ = force required before any consolidation


S, n = factors which may be affected by slope angle, strength properties of the embankment fill and the foundation soil, etc.

From the computer parametric study, it was found that accurate upper bound curves to all the individual time–strength envelopes could be represented by one empirical equation, i.e.

$$H = H_{(t=0)} - 120T_v^{0.5} \tag{12.8}$$

The similarity between the time–strength envelope produced by back analysis and the curve represented by Equation [12.8] is shown in Fig. 12.20 (for a 1:2 embankment slope). The actual effect of slope angle and material properties was accounted for by the value of $H_{(t=0)}$ whilst S and n were essentially constant for the conditions considered in the parametric study.

Whilst the foregoing points support the concept of LLGs, consideration has to be given as to how to incorporate a suitable Factor of Safety into the definition of a design time–strength envelope. For instance, the global Factor of Safety may be defined as

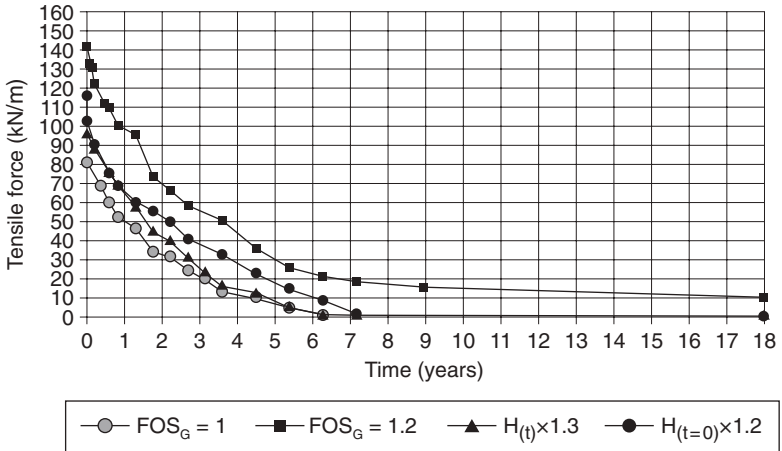

12.21 Influence of the Factor of Safety on the time–strength envelope.

$$FOS_G = \frac{M_R + HLF_R}{M_D} \tag{12.9}$$

where F_R is a partial factor applied to geotextile strength.

For the steepest slope likely in practice, i.e. 1:2, the back analysis was applied to several design philosophies and combinations of global Factor of Safety and partial factor and the results are shown in Fig.12.21.

Method 1. $FOS_G = 1$ with $F_R = 1$ at all time values (the initial case shown in Fig. 12.19).

Method 2. $FOS_G = 1.2$ (this is a typical practical global Factor of Safety) with $F_R = 1.0$ at all time values. The form of the time–strength envelope is very similar to that determined for an FOS_G value of unity and, within 2 years of embankment construction, the force that the reinforcement needs to provide has fallen to 50% of the original value. However, the basal geotextile is needed to continue to provide some permanent stabilizing force even after the foundation soil has fully drained (18 years after the end of construction for a C_v value of 1 m²/year). Although it is recognized that the magnitude of this permanent force is very small (around 10 kN/m and only about 8% of the initial tensile force needed), it is needed permanently and so does not accord completely with the concept of LLGs.

Method 3. $FOS_G = 1$ with $F_R = 1.3$ at all time values. With this method of analysis, the stability of the slope is generally greater than is suggested by an FOS_G of unity because there would be a ‘reserve’ of strength within the reinforcement. However, this ‘reserve’ would disappear abruptly at the end of the working life of the geotextile and the slope would then

be only just stable for some period of time (until further consolidation and strengthening of the foundation had occurred).

Method 4. The time–strength envelope designated as $H_{(t=0)} \times 1.2$ was generated to incorporate both a partial factor and a global Factor of Safety. The initial step was to calculate the value of H , before any consolidation occurred, for a global Factor of Safety of unity. This value of H was then increased by 20% and the actual global Factor of Safety FOS_G^* that this would represent at time zero was calculated. The full time–strength envelope was then back-calculated for this value of FOS_G^* .

It is felt that Method 4 is the best way of incorporating the Factor of Safety into the reinforcement design as it ensures stability throughout the consolidation period and yet permits the reinforcement to cease to contribute any restraining force within a reasonable time span.

12.7.3 Reinforcement selection

Pritchard *et al.* (2000) reported the outcome of work undertaken at the Bolton Institute (UK) to develop commercial forms of vegetable fibre geotextile for use as soil reinforcement. In developing these forms, a prime requirement was that they should be capable of being manufactured on conventional textile machines (with a minimum of modification of the machine). A variety of novel geotextile structures was created using flax, sisal and coir fibres (Table 12.18).

The novel materials created at Bolton were intended specifically for soil reinforcement purposes and so they were designed to provide the following:

Table 12.18 Novel vegetable fibre geotextiles (adapted from Pritchard *et al.*, 2000)

Fabric	Values at maximum load			Surface mass (g/m ²)	Thickness (mm)
	Strain %	Stress (MN/m ²)	Load/width (kN/m)		
Knitted; flax, sisal inlay (strength direction)	8.2	39	207	1753	5.3
Knitted; flax grid, sisal (strength direction)	7.4	33	144	1614	4.4
Plain weave; sisal warp, flax weft (warp direction)	9.6	50	180	1290	3.6
Plain weave; sisal warp, coir weft (warp direction)	16.3	15	113	1895	7.6
6 x 1 woven weft rib; sisal warp, coir weft (warp direction)	8.4	14	171	3052	12.1

- 1 The highest possible strength in one direction, since practical soil reinforcement situations such as slopes, retaining walls, etc., usually correspond closely to a plane strain condition (Sarsby, 2000).
- 2 Very high efficiency of transfer of shear stress within the surrounding fill into the reinforcement (where it would be balanced by the tensile strength of the reinforcement). The ability of the reinforcement to impart a confining tensile force to the soil fill is the key component in the principle of soil reinforcement. The efficiency of the 'bond' is readily indicated by the coefficient of interaction, α , i.e. the ratio of the effective friction coefficient $\tan \delta'$ of a soil–reinforcement interface to the effective friction coefficient $\tan \phi'$ of the

Table 12.19 Comparison of required and available time–strength envelopes

Slope		Tensile force (kN/m) required for the following times after embankment construction					
		0 years	1 years	2 years	3 years	4 years	5 years
1:2	Required for global Factor of Safety of unity	90	54	32	22	12	8
	Knitted; flax grid, weft sisal inlay; two layers	115	58	32	22	12 ^a	9 ^a
	Plain weave, sisal warp, flax weft; two layers	135	75	38	25	17 ^a	14 ^a
1:3	Required for global Factor of Safety of unity	65	25	5	0		
	Woven weft rib; sisal warp, coir weft; one layer	72	37	18	9		
	Knitted; flax grid, weft sisal inlay; one layer	83	43	23	12		
1:4	Required for global Factor of Safety of unity	38	0				
	Plain weave; coir warp, flax weft; two layers	48	42				
	Knotted; coir grid; two layers	44	42				
1:5	Required for global Factor of Safety of unity	21	0				
	Plain weave; coir warp weft; two layers	24	20				
	Knotted; coir grid; one layer	22	21				

^aExtrapolated value.

surrounding soil. For soil sliding on a solid surface, the value of α is typically around 0.5–0.6. For soil sliding on an efficient conventional geosynthetic reinforcement (such as a geogrid), the α value would be unity, or even slightly above unity (Sarsby and Marshall, 1984). The value of α depends very much on the degree of interlock between the fill and the reinforcement and this is controlled primarily by the relative size of the fill particles and apertures or depressions in the reinforcement (Jewell *et al.*, 1984.)

- 3 Some degree of protection (against on-site installation damage) to the fibres which are intended to provide the high tensile strength of the reinforcement. The construction work on a real site involves the placement and compaction of a variety of particle sizes and shapes on top of the fibres through the use of heavy plant. This is likely to lead to crimp, shear, tearing, etc., of some of the geotextile fibres.


Figures 12.22 and Fig. 12.23 show two of the vegetable fibre geotextile forms made by Pritchard (1999).

The strengths of the novel structures (given as load per unit width in Table 12.18) are in the same range as strengths provided by ‘lower strength polyester woven geotextiles used for soil reinforcement’ (Rankilor, 2000).

After the reinforcement time–strength envelope has been back calculated, geotextiles can be selected that will satisfy this strength versus time profile. Table 12.19 contains data on the measured time–strength envelopes of prototype vegetable fibre geotextiles (as manufactured by Pritchard, 1999) which can satisfy the reinforcement strength requirements for embankment slopes from 1:2 to 1:5. For shallow slopes (1:4 and 1:5), the time periods for which basal reinforcement is needed are very short and many vegetable fibre geotextiles are capable of providing the required strength–time profile. For the steepest embankment considered (1:2), the basal reinforcement needs to provide some restraining force for a number of years. Nevertheless, the required time–strength envelope can be easily achieved by using more than one layer of vegetable fibre geotextile.

Values of the coefficient of interaction for the novel structures created at Bolton were determined in accordance with the provisions of Part 8 of BS 6906 (British Standards Institution, 1991) using a 300 mm by 300 mm direct shear box with the geotextiles confined within sand or gravel. The applied normal stress range was up to 200 kN/m² (which corresponds to approximately 11 m of fill on top of the reinforcement). The values of measured friction angle and coefficient of interaction α given in Table 12.20 demonstrate clearly that the surface of the vegetable fibre geotextiles was very efficient at transmitting stresses between the fill and the reinforcement. Ali (1992) had previously obtained α values close to unity for coir and jute ropes used as reinforcement of tropical soil.

The foregoing data confirm both the concept of LLGs and the proposition that suitable geotextiles can be made using readily available vegetable fibres, in this case, sisal, coir and flax.

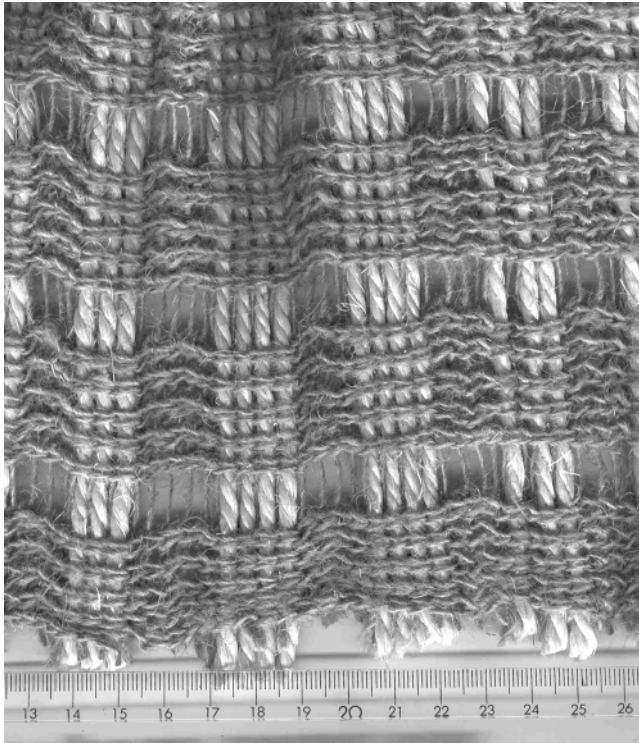

12.22 Novel geotextile with the form of a collection of linear reinforcements.


Table 12.20 Shearing interaction between soil and novel vegetable fibre geotextiles (adapted from Pritchard *et al.*, 2000)

Fabric	Maximum friction angle ^a with sand (deg)	α for sand fill	Maximum friction angle ^b with gravel (deg)	α for gravel fill
Knitted; flax, sisal inlay	40.9	1.01	50.5	0.86
Knitted; flax grid, sisal	38.8	0.94	50.9	0.87
Plain weave; sisal warp, flax weft	40.0	0.98	49.8	0.84
Plain weave; sisal warp, coir weft	42.1	1.06	53.4	0.95
6x1 woven weft rib; sisal warp, coir weft	42.0	1.05	50.9	0.87

^aMaximum friction for sand fill, 40.5°.

^bMaximum friction angle for gravel fill, 54.7°.

*Max friction for sand fill = 40.5°, max friction angle for gravel fill = 54.7°

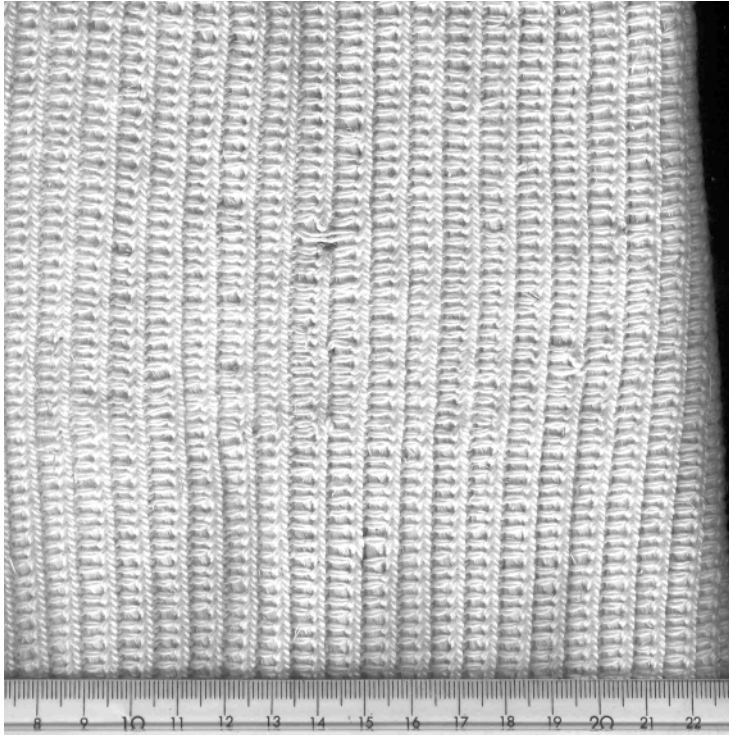

12.23 Novel geotextile with the form of a 'corrugated sheet'.

12.8 Conclusions

The use of natural fibres in composite construction can be traced back many centuries. Since the creation of man-made polymeric fibres, perceptions that natural fibres have low apparent tensile strength and a very short working life (particularly when in contact with soil and water) have led to the virtual demise of their use in construction. However, there have been sporadic attempts at their use as technical materials within construction.

The key to developing geosynthetics from natural fibres is the concept of designing by function, i.e. identifying the functions and characteristics required to overcome a given problem and then manufacturing the product accordingly. When correctly designed, natural fibre materials can compete with synthetic materials and sometimes they will even have superior performance.

There are numerous advantages to be gained from the development of vegetable fibre geotextiles using indigenous materials.

- 1 The raw materials employed, i.e. vegetable fibres, are 'environmentally friendly'.

- 2 They have low unit cost at the source of production.
- 3 Natural fibres have significant initial strength and are resistant to harsh environments
- 4 They introduce additional uses of by-products or new uses for waste products.
- 5 They represent a renewable resource.

It has been shown that the basal reinforcement requirements for an embankment built on soft clay can be satisfied by vegetable fibre geotextiles. These geotextiles can be made from fibres (such as coir, sisal and flax) which are readily available in developing countries. These new materials represent an extremely cost-effective and socially beneficial alternative to geotextiles made from synthetic compounds because they utilize indigenous renewable resources and provide widespread local employment.

There is a need to develop an assurance quality ethos in the use of bio-based products in world markets especially where they are replacing traditional products made from other resources. This requires the need to develop codes and specifications of each desired bio-based composite product. Such codes will assure the user of the composites that the product will perform in a certain way and they will develop consumer confidence.

12.9 References

- Ali, M. (1992), 'Tropical soil reinforcement using low cost natural fibres', MSc Thesis, Bolton Institute, Bolton, UK.
- Anon. (1927), 'The value of sisal hemp for the manufacture of marine cordage', *Reports of Recent Investigations at the Imperial Institute, Bulletin of the Imperial Institute*, **25**, pp. 359–368.
- Anon. (1935), 'Empire fibres for marine cordage. Tests of tarred and untarred cordage made from East African sisal', *Report of Exposure Tests Carried Out by the Admiralty 1933–1934*, Imperial Institute, London, pp. 1–11.
- Askew, M. F. (2000), 'Summary report for the European Union – fibre crops', in *IENTICA Report 1495*, Interactive European Network for Industrial Crops and their Applications, York, Chapter 5, pp. 23–38, <http://www.ienica.net/reports>.
- Azziz, W. (2000), 'Further development of natural fibre geotextiles for soil reinforcement', MPhil Thesis, Bolton Institute, Bolton, UK.
- Beckman, W. K. and Mills, W. H. (1957), 'Cotton fabric reinforced roads', *Engineering News Record*, **115**(14), pp. 453–455.
- Bisanda, E. T. N. and Anselm, M. P. (1992), 'Properties of sisal–CNSL composite', *Journal of Materials Science*, **27**, pp. 1690–1700.
- Booth, C. A., Davies, K. and Fullen, M. A. (2005), 'Environmental and socio-economic contributions of palm-leaf geotextiles to sustainable development and soil conservation', *Ecosystems and Sustainable Development*, **81**, pp. 649–658.
- British Standards Institution (1991), *BS 6906 Methods of Test for Geotextiles*, British Standards Institution, London.
- Byrne, C. (2000), 'Technical textile market – an overview', in *Handbook of Technical Textiles* (Eds A. R. Horrocks and S. C. Anand), Woodhead Publishing Ltd, Chapter 1, Cambridge, pp. 1–23.

- Chand, N., Santhayanarayana, K. G., Tiwary, R. K. and Rohatgi, P. K. (1986), 'Mechanical characteristics of sun hemp fibres', *Indian Journal of Textiles Research*, **11**, pp. 86–98.
- Chand, N., Tiwary, R. K. and Rohatgi, P. K. (1988), 'Resources structure properties of natural cellulosic fibres – an annotated bibliography', *Journal of Material Science*, **23**(2), pp. 381–387.
- Davis, B. (2001), 'The DRA all-fiber model: unique tool to help chemical companies' long term planning', *Special Focus, Global Fibres and Furs Stocks Report 001*, Organic Exchange, California, USA, pp. 8–10.
- Ellison, W. D. (1944), 'Studies of raindrop erosion', *Agricultural Engineering*, **25**, 131–136.
- Esau, K. (1977), *Anatomy of Seed Plants*, 2nd edition, Wiley, New York.
- Gray, D. H. (1991), 'Influence of ground cover on surface erosion', *Presented at the North American Geotextile Seminar*, Washington, DC, 1991.
- Hamlyn, P. F. (1990), 'Why micro-organisms attack textiles and what can be done to prevent this happening', *Textiles*, **19**, pp. 46–50.
- Han, J. S. and Rowell, J. K. (1997), 'Chemical composition of fibers', in *Paper and composites from agro-based resources* (Eds R. M. Rowell, R. A. Young and J. K. Rowell), CRC Press, Boca Raton, Florida, Chapter 5, pp. 83–134.
- Ivessalo-Pfaffli, M.-S. (1995), *Fiber Atlas*, Springer, Berlin.
- Indraratna, B., Khabbaz, H., Puswewala, A. and Bandara, W. A. A. W. (2005), 'Effects of tsunami on coastal ground conditions and appropriate measures for rail track rehabilitation', *Proceedings of the International Symposium on Tsunami Reconstruction with Geosynthetics* (Ed. D. T. Bergado), Asian Center for Soil Improvement and Geosynthetics, Pathumthani, pp. 51–71.
- Ingold, T. S. and Thomson, J. C. (1990), 'A design approach for preformed erosion control systems', in *Proceedings of the 4th International Conference on Geotextiles, Geomembranes and Related Products*, The Hague, The Netherlands, 1990, A. A. Balkema, Rotterdam, pp. 375–380.
- Jewell, R., Milligan, G., Sarsby, R. W. and DuBois, D. (1984), 'Interaction between soil and geogrids', in *Proceedings of the SERC Symposium on Polymer Grid Reinforcement*, Thomas Telford, London, pp. 18–30.
- Jones, C. J. F. P. (1996), *Earth Reinforcement and Soil Structures*, Thomas Telford, London.
- Kumar, J. P. S., Rao, G. V. and Banerjee, P. K. (2001), 'Production method and evaluation of a jute-coir braided prefabricated vertical drain', *Coir Geotextiles – Emerging Trends* (Eds G. V. Rao and K. Balan), The Kerala State Coir Corporation, Alappuzah, Kerala, pp. 147–165.
- Leflaive, E. (1988), 'The use of natural fibres in geotextile engineering', in *Proceedings of the 1st Indian Geotextiles Conference on Reinforced Soil and Geotextiles*, New Delhi, India, 1988, Indian Geotextiles Society, Bombay, pp. 81–84.
- Levillain, J. P. (2000), 'A method of installing a filter geotextile on the bed of a 20 m deep river' (in French), *Recontre Geosynthétiques*, **99**, pp. 163–168.
- Lightweight Structures BV (2005), 'Natural fibre composites – from upholstery to structural components', Centre for Lightweight Structures, <http://lightweight-structures.com>
- MacMillan, W. G. (2005), 'Improvement of rot-retardant properties of jute and jute goods', *IJGS Technical Paper 1/05*, International Jute Study Group, Dhaka, Bangladesh.
- Mandal, J. N. (1988), 'The geojute edge', in *Proceedings of the 1st Indian Geotextiles Conference on Reinforced Soil and Geotextiles*, New Delhi, India, 1988, Indian Geotextiles Society, Bombay, pp. 31–34.
- Mandal, J. N. (1989), 'Geojute', *International Geotextile Society News*, **5**(3), p. 12.
- Mandal, J. N. and Murti, M. V. R. (1989), 'Potential use of natural fibres in geotechnical

- engineering', in *Proceedings of the 6th International Workshop on Geotextiles, Geotextiles in India, Geotextiles and Geomembranes*, Bangalore, 1989, Elsevier, Amsterdam, pp. 251–254.
- Mitchell, D. J., Barton, A. P., Fullen, M. A., Hocking, T. J., Zhi, W. B and Yi, Z. (2003), 'Field studies of the effects of jute geotextiles on runoff and erosion in Shropshire, UK', *Soil Use and Management*, **19**, pp. 182–184.
- Morgan, R. P. C., Morgan, D. D. V. and Finney, H. J. (1984), 'A predictive model for the assessment of soil erosion risk', *Journal of Agricultural Engineering Research*, **30**, pp. 245–253.
- Mwasha, A. P. (2005), 'Limited life basal reinforcement for an embankment built on saturated soft clay', PhD Thesis, Wolverhampton University, Wolverhampton, UK.
- Mwasha, A., Sarsby, R. W. and Karri, R. S. (2002), 'Potential for using sisal fibre geotextiles in East Africa', in *Proceedings of the 9th IAEG Congress in Engineering Geology for Developing Countries*, Durban, South Africa, October 2002.
- Mukherjee, P. S. and Satyanarayana, K. G. (1984), 'Structure and properties of some vegetable fibres — Part 1: sisal fibre', *Journal of Materials Science*, **21**, pp. 51–56.
- Pritchard, M. (1999), 'Vegetable fibre geotextiles', PhD Thesis, Bolton Institute, Bolton, UK.
- Pritchard, M., Sarsby, R. W. and Anand, S. C. (2000), 'Textiles in civil engineering. Part 2 — natural fibre geotextiles', in *Handbook of Technical Textiles* (Eds A. R. Horrocks and S. C. Anand), Woodhead Publishing, Cambridge, Chapter 14, pp. 372–406.
- Ramanatha, A. T. V. and Girish, M. S. (1999), 'Performance of a model retaining wall using coir fibres', in *Proceedings of the Indian Geotechnical Conference*, December 1999, Calcutta, India, pp. 33–41.
- Rankilor, P. R. (1990), 'Designing textiles into the ground', in *Textile Horizons, Handbook of Technical Textiles* (Eds A. R. Horrocks and S. C. Anand), Woodhead Publishing, Cambridge, pp. 358–371.
- Rao, G. V. (2000), 'Classification of erosion control products', in *Coir geotextiles — Emerging Trends*, The Kerala State Coir Corporation, Alappuzah, Kerala, pp. 107–14.
- Rao G V and Balan K (2000), Improving the environment by vegetation growth, in *Coir geotextiles — Emerging Trends*, The Kerala State Coir Corporation, Alappuzah, Kerala, pp. 81–106.
- Rickson, R. J. (1994), 'Use of natural fibres in soil erosion control matting', in *Proceedings of the Joint Conference of Pira International, Non-wood Fibres for Industry*, Vol. 2, March 1994, Pira international, Leatherhead, Surrey, Paper 27.
- Rowell, R. M. and Jacobson, R. E. (2002), 'Use of coir in composite materials', in *Proceedings of the International Coir Convention*, Food and Agricultural Organization of the United Nations and the Common Fund for Commodities, Rome, pp. 75–95.
- Sarsby, R. W. (1997), 'Vegetable fibre geotextiles', *Presentation to the Ministry of Agriculture, Fisheries and Food*, April 1997, London.
- Sarsby, R. W. (2000), *Environmental Geotechnics*, Thomas Telford, London
- Sarsby, R. W. (2005), 'Limited life Geotextiles (LLGs) for soil reinforcement', in *Proceedings of the International Symposium on Tsunami Reconstruction with Geosynthetics* (Ed. D. T. Bergado), Bangkok, Thailand, 2005, Asian Institute of Technology, Bangkok, pp. 97–107.
- Sarsby, R. W. (2006), 'Limited life geotextiles for soil reinforcement', *Geotextiles and Geomembranes* (in press).
- Sarsby, R. W., Ali, M., de Alwis, R., Khaffaf, J. H. and McDougall, J. M. (1992), 'The use of natural and low cost soil reinforcement', in *Proceeding of the International Conference*

- on Nonwovens*, New Delhi, India, December 1992, Textile Institute of India, New Delhi, pp. 297–310.
- Sarsby, R. W. and Marshall, C. B. (1984), 'Interaction between geogrids and granular soil', in *Proceedings of the 8th European Conference on Soil and Foundation Engineering*, Helsinki, Finland, 1984, A. A. Balkema, Rotterdam, p. 1194.
- Schuhe, A. (2000), cited in Askew, H. F., 'Summary report for the European Union – fibre crops', in *IENICA Report 1495*, Interactive European Network for Industrial Crops and their Applications, York, <http://www.ienica.net/reports>.
- Shamte, S. (2000), 'Overview of the sisal and henequen industry: a producer's perspective: alternative applications for sisal', in *Proceedings of the Food and Agricultural Organization of the UN and the Common Fund for Commodities Seminar*, Paris, 2000, Technical Paper 7, pp. 59–63.
- Theisen, M. S. (1992), 'The role of geosynthetics in erosion and sediment control: an overview', *Geotextiles and Geomembranes*, **11**, pp. 535–550.
- Wibisono, G. (2000), 'The effect of water on the erodibility of fibre reinforced or stabilised kaolin', MSc thesis, University of Birmingham, Birmingham, UK.